

# Pavement Performance Modeling – A Case Study

Saranya Ullas, B.G Sreedevi, Sreelatha T

**Abstract—** Pavement deterioration is a complex process. It involves not only structural fatigue but also many functional distresses of pavement. It results from the interaction between traffic, climate, material and time. Deterioration is the term used to represent the change in pavement performance overtime. The ability of the road to satisfy the demands of traffic and environment over its design life is referred to as performance. Due to the great complexity of the road deterioration process, performance models are the best approximate predictors of expected conditions. In this study main distresses were identified from the selected road stretches. Regression models are then developed using SPSS (Statistical packages for social sciences) package. T test is used to check the reliability of the model.

**Index Terms—** Deterioration, Distresses, Performance models, Structural fatigue.

## I. INTRODUCTION

It is necessary to provide a good road network for the development of any country. India has the second largest highway and road networks system on the world. The total length of roads in the country exceeds 3.01 million kilometers. There is a great need for the effective and efficient management and maintenance of the road network. The funding available for periodic maintenance and management system is limited. In order to determine the most economical strategies, most essential input is development of deterioration models for structural and functional conditions of flexible pavements. Pavement performance is a function of its relative ability to serve traffic over a period of time ( Highway Research Board, 1962). Due to the great complexity of the road deterioration process, performance models are the best approximate predictors of expected conditions.

## II. OBJECTIVES OF THE STUDY

The main objectives of the present study are

- i) To evaluate the functional and structural condition of flexible pavements.
- ii) To develop performance prediction models using SPSS package.
- iii) To test the reliability of model using T- test.
- iv) To develop a model for determination of Riding Comfort Index (RCI).

Manuscript published on 30 August 2013.

\*Correspondence Author(s)

Saranya Ullas, Department of Civil Engineering,, Rajiv Gandhi Institute of Technology, Kottayam, India.

Sreedevi B.G, Director, National Transportation Planning and Research centre, Trivandrum, India

Prof. Sreelatha T, Department of Civil engineering , Rajiv Gandhi Institute of Technology, Kottayam, India

© The Authors. Published by Blue Eyes Intelligence Engineering and Sciences Publication (BEIESP). This is an open access article under the CC-BY-NC-ND license <http://creativecommons.org/licenses/by-nc-nd/4.0/>

## III. LITERATURE REVIEW

Large numbers of studies have been conducted globally for developing pavement performance models. Pavement performance model is an equation that relates some extrinsic and intrinsic variables and performance indicators.

Pavement performance models are of three types namely distress characteristics based models, pavement performance rating models and models based on environmental factors. Regression can be either linear or non linear. When more than one variable is included in the deterioration model, multiple linear regression or non-linear regression is resorted to.

Different techniques available for developing pavement deterioration models include straight line extrapolation, regression (empirical), mechanistic- empirical, polynomial constrained least squares, S- shaped curves, probability distribution and Markovian. Regression technique is empirical in nature and it tries to build a relationship between the pavement condition and its causative factors. The reliability of a regression model is measured by its goodness of fit, in terms of co-efficient of determination ( $R^2$  value).

Mathew et al.(2008) developed deterioration models for ravelling initiation and progression, pothole progression, roughness progression and edge failure using neural network and regression techniques. The ANN models were compared and found to be more suitable to the rural roads as compared with the conventional empirical statistical models.

Sreedevi et al.(2011) conducted Field performance indicators for NRMB in a tropical setting. Pavement performance indicators for road sections constructed using Natural Rubber Modified Bitumen and Ordinary bitumen operating under identical conditions has been derived from periodic field data collection and analysis.

Study on decision support system for performance based maintenance management of highway pavements was done by Muralikrishna and Veeraragavan(2011). Deterioration models were developed for deflection progression and roughness progression. One set of data was used for the validation process, done by chi-square test.

Reddy et al (2005) developed flexible pavement preservation framework for an integrated asset management. In this study methodology integrates pavement condition data management, pavement performance and its standards to generate pavement preservation program. Riding Comfort Index (RCI) has been established to determine the preservation needs. Various maintenance management tools were derived as part of this study.


## IV. STUDY AREA SELECTION

The scope of the study was limited to five stretches distributed on two roads three from Kottayam- Kumili Road and two from Varkala- Kallambalam.

Study area stretches were selected based on the category of the road, terrain and traffic conditions, geographical location etc. Homogenous sections were selected based on the factors like traffic, pavement layer details, type of surfacing, general surface condition, subgrade soil conditions and terrain type. Figure 1 shows the location of study area and table I details of study stretches.

**Table I Details of study stretches**

Sl No	Name of the Road	Category	No of Homogenous Sections with chainage	Terrain
1	Kottayam-Kumili	NH	HS-I (118-119) HS-II(141-142) HS-III(180-181)	Plain Plain Hilly
2	Kallambalam-Varkala	ODR	HS-I HS-II	Plain Plain

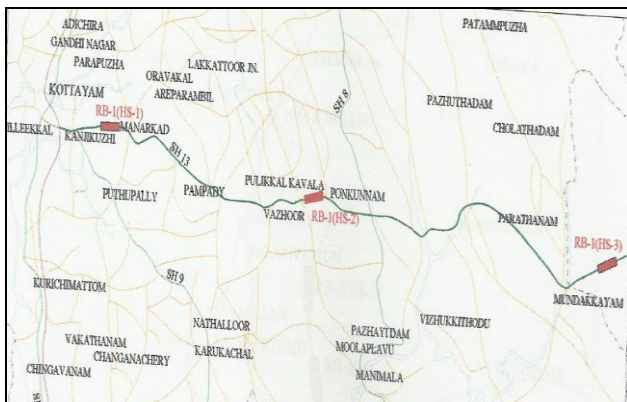

a) Kottayam – Kumili Road stretch



b) Varkala – Kallambalam Road stretch

**Fig.1 Locations of study stretches**

## V. DATA COLLECTION

Data collection was done by taking out five representative sections each of length 1km from the study roads. Eleven sets of data were already available from previous studies. Additional one set was collected in this year.

### A. Pavement Construction history data

Pavement history data collected in this study include Pavement layer details, time of maintenance or strengthening etc. The surface layer details during the first set of data collection are shown in the table II below:

**Table II Pavement layer details of study roads**

Study Stretch	Pavement Layer details in the year 2003
Kottayam – Kumili Road	250mm WBM + 50mm BM + 40 mm BC
Varkala – Kallambalam	200mm WBM + 70mm BM + 40mm BC

### B. Structural condition data

The structural condition data collected for the study include road inventory data, CBR value and deflection measurement using Benkelman Beam. Vehicle Damage Factor obtained from previous studies were used as a performance parameter.

#### Road inventory data

In the road inventory data details of pavement type, terrain, carriage way width, pavement drainage characteristics, land use etc are taken.

#### California Bearing Ratio

Field investigation and laboratory tests were conducted on the sub grade soil in order to determine CBR value. Soil samples were taken to laboratory in sealed containers for moisture content determination and for conducting CBR tests.

#### Benkelman Beam Deflection Method

Benkelman beam is a device used to measure the rebound deflection of pavement. It is the most commonly used instrument and is simple and cheap. Deflections were measured at 20 points in each kilometre, staggered at 50 meter interval in both directions with truck having rear axle load of 8.17 tonnes and tyre pressure of 5.6 kg/cm<sup>2</sup>. The measurements are taken as per the procedure given in IRC:81-1997. The deflection progressions of two roads are shown in the figure 2.



**Fig. 2 Deflection Progression of Kottayam – Kumili road**

### C. Functional condition data

#### Condition Survey

Functional condition data were collected by walk survey associated with actual measurements. One set of condition data was collected in this year. A representative section of 1000 m length was selected from each stretch. The different types of distress observed on these roads included ravelling, cracking, potholes and fretting. Rutting was absent on these roads.

Fretting is not considered as major distress, therefore it gets eliminated. The distresses were measured in terms of their severity. The length and width of each were measured with tape. Analysis was carried out by converting it in to percentages of total carriageway affected.

### Roughness survey

Roughness of pavement is an indication of its riding quality and level of service. The fifth wheel bump integrator was used for the roughness measurement. The vehicle was driven through the test sections and bumps were measured. With the fifth wheel bump integrator the value obtained is in mm/km. The data obtained from fifth wheel bump integrator is converted to standard roughness value (IRI in m/km) using calibration equation. The roughness progression of Kottayam Kumili road during last ten years was shown in the figure 3 below.

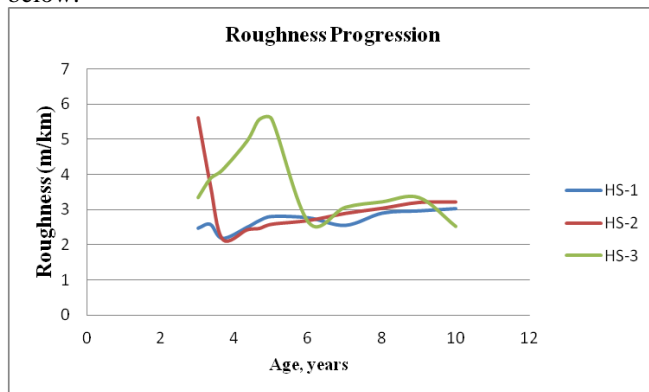


Fig. 3 Roughness progression in Kottayam – Kumili Road

The basic statistics of performance parameters are shown in the table III below. The performance parameters along with minimum, maximum, mean and standard deviation of each parameter are listed below.

Table III Statistics of performance parameters

Parameter	Minimum	Maximum	Mean	Standard deviation
Cracking area(%)	0.000	5.800	0.133	0.790
Deflection (mm)	0.410	1.980	1.114	0.447
Pothole area(%)	0.000	0.976	0.160	0.310
Roughness(m/km)	2.160	5.601	3.077	0.754
Ravelling	0	6.097	0.753	1.326
MSN	2.531	5.595	4.279	0.960
VDF	1.292	4.612	2.590	1.250
Age	3	10	5.816	2.293

## VI. ANALYSIS AND RESULTS

Total eleven sets of data were used for the modeling purpose. One set was collected as part of the present work.

Remaining sets were available from previous study. Detailed structural and functional data collected were analyzed. Main distresses were identified and models were developed for main distresses and deflection.

### A. Modified Structural Number

Pavement strength was expressed in terms of Modified Structural Number (MSN). The concept of structural number was first introduced as a result of the AASHO Road test. It is a measure of total thickness of the road pavement weighted according to the 'strength' of each layer and calculated as follows:

$$SN = \sum a_i d_i \quad (1)$$

i = summation over layers

$a_i$  = a strength coefficient for each layer

$d_i$  = is the thickness of each layer measured in inches

The strength coefficients suggested for different pavement materials are shown in the table IV below:

Table IV Strength Coefficients

Layer/Specification	Strength Coefficients
Bituminous Concrete (BC) 40mm	0.3
Bituminous Concrete (BC) 25mm	0.28
Semi Dense Bituminous Concrete (SDBC) 25mm	0.25
Dense Bituminous Macadam(DBM)	0.28
Premix Carpet (PC) 20 mm( only in the case of overlaid pavements which have PMC as original surfacing)	0.18
Bituminous Macadam(BM)	0.18
Water Bound Macadam(WBM Gr I,II,or III)	0.14
Wet mix macadam / (Lime cement) stabilized	

(Source: Guidelines for maintenance of primary, secondary and urban roads)

The AASHO Road Test was constructed on a single uniform subgrade therefore the effect of different subgrades could not be estimated and the structural number could not include a subgrade contribution. Pavements of a particular structural number but built on different subgrades will therefore not carry the same traffic to a given terminal condition. To overcome this problem and to extend the concept to all subgrades, a subgrade contribution was derived by Hodges et al., and a modified structural number defined as follows:-

$$MSN = SN + 3.51 \log_{10}(CBR_s) - 0.85 (\log_{10} CBR_s)^2 - 1.43 \quad (2)$$

$CBR_s$  = California Bearing Ratio of the subgrade.

This modification has been used extensively and forms the basis for defining pavement strength in many pavement performance models.

### B. Riding Comfort Index

In order to determine the riding quality of pavement an index called riding quality index was developed. The first step was to classify the unevenness values in to different range. Range selection was based on the data collected.



RCI is primarily a function of pavement unevenness and is measured on a scale of 0 to 5 (Table V). RCI of zero indicates well constructed new pavement and five represents an extremely rough pavement. If the unevenness index value of a particular pavement stretch is known, the RCI value can be obtained directly.

**Table V : Riding Comfort Index values**

Unevenness Index (mm/km)	Riding Comfort Index
<2500	0
2500-3500	1
3500-5000	2
5000-7000	3
7000-10000	4
>10000	5

### C. Regression Models

Regression models are empirical models and were developed using Statistical Packages for Social Sciences (SPSS). Models were developed for

#### Cracking progression

A common defect in thick bituminous surfaces is formation of cracks. Oxidation of binder makes the bituminous surface brittle and cause cracking on the surface of the pavement. Cracks on pavement surface weaken the pavement structure. The various factors influencing cracking progression were identified as cracking initiation, deflection, vehicle damage factor and modified structural number.

$$Cr = 0.985XCr_i + 0.269XDef - 0.764X \left( \frac{VDF}{MSN} \right) + 0.186 \quad (3)$$

$$R^2 = 0.977$$

$$SE = 0.367$$

#### Deflection

Pavement deforms elastically under the wheel load application. Deflection was not a measure of pavement deterioration, but it has some influence on the rate of pavement deterioration. Therefore, it is important to predict the deflection value. Performance and life of the flexible pavements are closely related to rebound deflection under the wheel loads. The influencing factors selected for deflection prediction includes vehicle damage factor, modified structural number and initial deflection.

$$Def = 0.358XDef_i + 0.009Xe^{VDF} - 0.002Xe^{MSN} + 0.653 \quad (4)$$

$$R^2 = 0.879$$

$$SE = 0.107$$

#### Pothole Progression

Pothole is defined as any localized loss of material or depression in the surface of a pavement. The performance parameters of pothole progression are taken as Age, VDF, MSN and pothole initiation.

$$Pt = 1.075XPt_i + 0.013XAge - 0.226X \left( \frac{VDF}{MSN} \right) + 0.109 \quad (5)$$

$$R^2 = 0.644$$

$$SE = 0.381$$

#### Roughness progression

Roughness was modeled as a function of roughness initiation, raveling area, pothole area, vehicle damage factor, modified structural number and pavement age.

$$RG_t = -0.159 * RG_i + 0.347 * RV * \left( \frac{VDF}{MSN} \right)^{Age} + 3.24 * Pt * \left( \frac{VDF}{MSN} \right)^{Age} + 1.171 * Cr + 0.553 * \left( \frac{VDF}{MSN} \right)^{Age} + 3.211 \quad (6)$$

$$R^2 = 0.748$$

$$SE = 0.725$$

### Riding Comfort Index Model

The assessment of riding quality is considered to be the most important component of pavement surface condition. Here riding quality of pavements in the form of Riding Comfort Index (RCI) has been correlated with the unevenness index values and an equation was developed.

$$RCI = 2.9897 \ln(u) - 22.902 \quad (7)$$

$$R^2 = 0.873$$

Where,

Age = Pavement age in years

Cr = cracking area in percentage at time t

Cr<sub>i</sub> = Initial cracking area in percentage

Def = Deflection at time t in mm

MSN = Modified Structural Number

Pt = Pothole area in percentage at time t

Pt<sub>i</sub> = Initial pothole area in percentage

RCI = Riding Comfort Index (RCI)

RG<sub>i</sub> = Initial roughness in m/km

RG<sub>t</sub> = Roughness at time t in m/km

RV = Ravelling area in percentage at time t

u = Unevenness in mm/km

VDF = Vehicle damage factor

### D. Validation of the models

Developed deflection growth model and roughness progression model were validated with one set of data collected. The final set of data collected was used for the validation purpose. It was not possible to validate the distresses models due to periodic maintenances. T- test was done to check the reliability of the model. The T-values observed at 5% level of significance is well below critical values hence the models are reliable (Table VII).

**Table VI Comparison of actual and regression predicted values**

Study stretches	Deflection (mm)		Roughness (m/km)	
	Actual	Regression model (Predicted)	Actual	Regression model (Predicted)
HS -1	0.82	0.80	3.02	2.99
HS -2	1.1	1.10	3.25	3.01
HS-3	1.88	1.84	2.92	2.71
HS-1 VK	0.62	0.66	2.86	2.84
HS-2 VK	0.74	0.80	2.88	2.87

Table VII T –test results

Models	DF	Calculated values	Critical values
Deflection Model	4	2.16	2.776
Roughness Model	4	1.77	2.776

## VII DISCUSSIONS

Detailed pavement condition survey on all the study stretches showed that the main distresses were pothole, ravelling and cracking. Rutting was absent on these roads. Percentage of fretting was high on all road stretches. But fretting is not considered as a major distress. It may further leads to ravelling. It is very difficult to distinguish between fretting and ravelling. Thus fretting may be sometimes noted as ravelling.

Deflection values were getting lowered after maintenance work on all the study stretches. Deflection values obtained are well within the limits. Roughness values were also getting lowered after the maintenance works.

## VII. CONCLUSION

Detailed literature review and pavement evaluation studies were conducted on selected road stretches. The different parameters affecting the pavement performance were identified. It includes Modified Structural Number (MSN) and Vehicle Damage Factor (VDF). Non linear models regression models were formulated for ravelling initiation, cracking progression, deflection growth, pothole progression and roughness. SPSS predicted values are nearer to observed values. Hence these models are suitable for the performance predictions of selected roads. The reliability of deflection growth model and roughness progression models were checked by T-test.

## ACKNOWLEDGMENT

The authors are acknowledged to Salini P.N (Scientist B,NATPAC), Wilson K.C (Scientist B, NATPAC) for their valuable suggestions and supports during the work. The authors wish to thank Dr. Padmini A.K (H O D, Civil Engineering Dept, RIT, Kottayam), Dr Bino I Koshy (Professor, RIT, Kottayam), for their overall guidance and support. Authors profusely thank the staff of NATPAC for their assistance in data collection.

## REFERENCES

1. Gupta A, K. Praveen, and R.Rajat (2012), “ A Critical Review of Flexible Pavement Performance Models Developed for Indian perspective”, Indian Highways, Indian Road Congress, New Delhi,40(3) pp.41-60.
2. IRC:81-1997, *Guidelines for Strengthening of Flexible Road Pavements Using Benkelman Beam Deflection Technique*, Indian Road Congress, New Delhi, 1997.
3. Mathew, B.S., Reshmy, D.S. and Issac, K.P. (2008), “Performance Modelling of Rural Road Pavements Using Artificial Neural Network”, Indian Highways, Indian Roads Congress, New Delhi, 36(1), pp.31-39.
4. Muralikrishna P and Veeraragavan.A (2011), “ Decision Support System For Performance Based Maintenance Management Of Highway Pavements”, Journal of Indian Road Congress, New Delhi, pp.155-167.
5. Reddy ,B.B, Sharma,R.S., and Veeraragavan,A.(2005). “Development of flexible pavement preservation framework for an integrated Asset management.”, Journal of Indian Roads Congress, Volume 66-1 , April 2005 , 383-418

6. Reddy,B.B., and Veeraragavan,A. (1998), “Methodology for Sample size Determination in Pavement Performance Data Collection” , Indian Highways, Indian Road Congress, New Delhi, 26(11), pp.15-27.
7. Sreedevi B.G, Salini P. N and Sathish B Nair (2011), “Field performance indicators for NRMB in A tropical setting”, Indian Highways, January 2011. pp -47-57.

## AUTHOR PROFILE



**She has obtained** her B Tech Degree in Civil Engineering from Rajiv Gandhi Institute of Technology, Kottayam. She is pursuing her M Tech in Transportation Engineering from the same institution. Her area of interest is in Pavement Evaluation.



**Smt. B.G. Sreedevi** is currently working as Director, of National Transportation Planning & Research Centre (NATPAC) an R&D Centre of Govt. of Kerala. She is a Post Graduate in Civil Engineering from Indian Institute of Technology Madras and also possess Post Graduation in Urban and Highway Engineering from Vinayaka Mission Deemed University (VDDU). She also has

obtained a Post Graduate Diploma in Management from All India Management Association (AIMA). The field of experience and expertise includes Highway Engineering, Water Transport, Management Information System, Road Safety, S&T Management and Administration. Has published 7 research papers in referred journals and has got more than 65 publications in seminar/ workshop proceedings and other compendiums.



**Prof. Sreelatha T** is working as an Assistant Professor in Department of Civil Engineering at Rajiv Gandhi Institute of Technology, Kottayam. She is post graduated from National Institute of Technology (NIT), Calicut. Her area of interest is in Pavement

Engineering.