

# Design and Finite Element analysis of Thick-walled Laminated Composite Pressure Vessel



Sarada Prasad Parida, Pankaj Charan Jena

**Abstract:** Composite materials in general offer a high potential for manufacturing of structures with featuring an interesting mechanical performance, mainly with regards to specific stiffness, specific strength, damage tolerance and energy absorption capability. In current analysis, glass fibre reinforced in epoxy resin to form a laminated composite walled pressure vessel (filament winding) is considered for design. The purpose of this work is primarily to perform finite element analysis (FEA) of a composite walled pressure vessel (CPV) under different loads. Different design stresses and strains are evaluated using Lamé's equation. These outcomes are tabulated and examined with the results of the steel walled pressure vessel used for LPG. It is found that CPV is a suitable vessel for LPG storage and it can be replaced current LPG steel walled vessel to CPV.

**Keyword:** design, cylinder, composite walled, vessel

## I. INTRODUCTION

Composite materials in general offer a high potential for manufacturing of structures featuring an interesting mechanical performance, mainly with regard to specific stiffness, specific strength, damage tolerance and energy absorption capability. Composite pressure vessels were originally developed for aerospace applications. Nowadays, these are utilized in broad field of applications such as water treatment stations and petroleum industry. The current state of the art composite pressure vessels are light, safe.

The purpose of this work is primarily to perform finite element study of composite pressure vessel subjected to various constraints of loads and to investigate the possibility of replacing current LPG steel vessels with cpvs. The analysis is carried out using the finite element method.

Tauchert [1] optimized fiber distribution in cylindrical fiber reinforced composite pressure vessel using minimum strain energy criterion. They have presented results by considering variation of radii, elastic moduli, and global volume fractions. Ecklod [2] used anisotropic elastic theory to study the effect uniaxial and combined loading on filament wound thick composite cylinder. Adaliet la. [3] optimized the burst pressure with respect to weight for different fiber orientation and thickness using membrane theory of shells. Cohen et al. [4-5] studied and presented the effect volume fraction of fiber, stacking sequence of laminate, winding time and tension with failure pressure. For the purpose authors developed a computer program and validated with the experimental investigation. Xu and Yu [6] conducted shake down analysis and determined the elasto-plastic stress limits for thick walled cylinders subjected to internal pressure. Naser and Osama [7] have stated that the composite LPG cylinders are as replacements of conventional steel cylinder by ANSYS with lower stress level and higher displacement. Antunes et al. [8] made glass polypropylene pressure vessel by filament winding process cascaded with thin layer of steel to study the burst pressure by FEM. Yue and Li [9] modelled composite cylinders for CNG storage and evaluated deformed cloud diagrams for stress and strain when subjected to different internal pressures. Taheri [10] studied and presented the various manufacturing techniques used for the manufacturing of fiber reinforced composites used as pipes and risers in oil and gas industry. Lepikhin et al. [12] presented an overview of correlations of stress-strain with different parameter for anisotropic composite cylinders in dynamic loading from different experimental studies. Hemmatnezhad et al. [13] fabricated GFRP composite cylinders by filament winding process and determined the dynamic characteristics in vibration theoretically based on Sanders' thin shell theory and by FEM.

$F_R$	Normal force along radial direction
$F_\Theta$	Normal force along Tangential direction
$F_{R\Theta}$	Shear force
$M_R$	Bending moment along radial direction
$M_\Theta$	Bending moment along Tangential direction
$M_{R\Theta}$	Bending moment along R $\Theta$ plane
$\sigma_{RR}$	Radial stress
$\sigma_{\Theta\Theta}$	Tangential stress
$\sigma_{R\Theta}$	Shear stress
$Z_k$	Thickness of kth layer
$Z_{k-1}$	Thickness of k-1 th layer
$n$	Number of layer
$[\epsilon^0]_{R,\Theta}$	Normal strain component matrix
$[\kappa]_{R,\Theta}$	Shear strain component matrix
$q_{RR}, q_{SS}, q_{\Theta\Theta}, q_{R\Theta}, q_{RS}, q_{\Theta S}$	Transformed stiffness of orthotropic composite cylinders in respective R, S, $\Theta$ directions
$q_{ij}$	stiffness of individual lamina in i and j directions
$[A],[B],[D]$	Components of compliance matrix
$E_1, E_2$	Modulus of elasticity of individual lamina along warp and fill direction
$G_{12}$	Modulus of rigidity
$\gamma_{12}, \gamma_{21}$	Poissons ratio along warp and fill direction
$P$	Internal pressure
$R_o$	Outer diameter
$R_i$	Inner diameter
$H$	Wall thickness
$\gamma$	Poissons ratio
$\delta_R$	Radial displacement

Manuscript published on 30 August 2019.

\*Correspondence Author(s)

**Pankaj Charan Jena**, Sarada Prasad Parida, Department of Production Engineering at Veer Surendra Sai University of Technology, Burla, Odisha, India, sarada800@gmail.com

**Pankaj Charan Jena** \*, Department of Production Engineering at Veer Surendra Sai University of Technology, Burla, Odisha, India-768018, E-mail: [pankajcharanjena@gmail.com](mailto:pankajcharanjena@gmail.com)

© The Authors. Published by Blue Eyes Intelligence Engineering and Sciences Publication (BEIESP). This is an open access article under the CC-BY-NC-ND license <http://creativecommons.org/licenses/by-nc-nd/4.0/>




Guz et al.[14] reviewed the practical applications of thick composite pipes subjected to outer pressure in oil and gas industry and analytically demonstrated the failure analysis by stress distribution through the wall thickness for different lay ups of fibres. Davies et al. [14] demonstrated the use of glass/epoxy and carbon/epoxy composite pressure vessel in underwater applications with implosion pressure of 600bar in 6000m depth. Ahmad and Hoa[15] experimentally determined the flexural stiffness of thick walled tubes indigenously manufactured by fiber placement machine. Ahmadi [16] used Reddy’s layer wise theory and approached an analytical method to determine inter-laminar stresses from elastic equations subjected to uniform and non-uniform internal pressure. Ramos et al. [17] studied the mechanical behaviour of thick anisotropic fiber reinforced composite cylinder analytically by exact 3-D elastic solution approach and the results obtained were compared with the results of FEA study. Arhant et al. [18] designed and fabricated thermoplastic composite pressure vessels and presented that thermoplastic composites pressure vessels in undersea application can be the replacements of thermoset composites. For validity of the result the experimental data are matched with the results obtained from FEA study for different stacking sequence of fiber and internal pressure.

**II. MODELLING OF THICK WALLED CYLINDERS**


The pressure vessels or gas cylinders which are generally used for storing fluids i.e. liquid or gas under pressure are of thick cylinders. In this case the cylinder wall is taken as of four layered composite material. The whole procedure of study is presented through the following flow chart (Figure1). The stress strain relationship for an orthotropic composite material can be determined using laminated shell theory. Shells are three dimensional bodies closed by curved surface as shown in the Figure 2.

**Table-I:** Elastic Properties of Epoxy –Glass

Material	Properties	Values
Glass fiber	Fiber longitudinal modulus in l direction $E_{fl}$ (GPa)	78
	Fiber transverse modulus in t direction $E_{ft}$ GPa	78
	Fiber shear modulus $G_f$ (Gpa)	30
	Density $\rho_f$ (kg/m3)	2650
	Fiber Poisson ratio $\nu_{fl}$	0.3
Epoxy resin	Elastic modulus $E$ (Gpa)	4
	Shear modulus $G$ (Gpa)	1.43
	Density $\rho_m$ (kg/m3)	1250
	Poisson ratio $\nu$	0.4

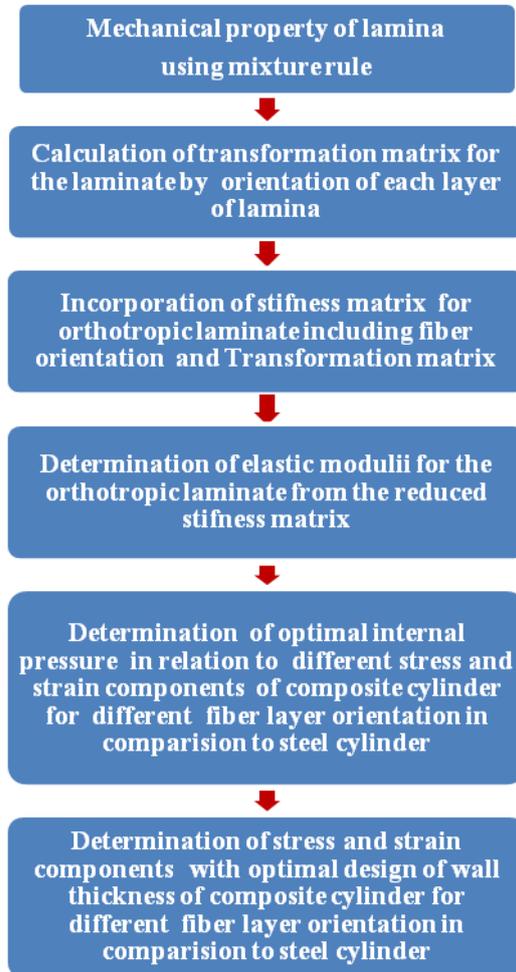

**Fig 1:** Detail steps of current analysis in flow chart.

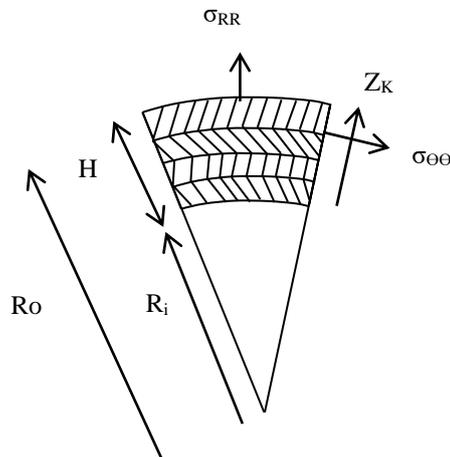

**Fig 2:** Schematic view of orthotropic composite walled cylinder.

$$\begin{bmatrix} F_R \\ F_\Theta \\ F_{R\Theta} \end{bmatrix} = \sum_{l=1}^n \int_{Z_{k-1}}^{Z_k} \begin{bmatrix} \sigma_R \\ \sigma_\Theta \\ \sigma_{R\Theta} \end{bmatrix} z dz \quad (1)$$

$$\begin{bmatrix} M_R \\ M_\Theta \\ M_{R\Theta} \end{bmatrix} = \sum_{l=1}^n \int_{z_{k-1}}^n \begin{bmatrix} \sigma_R \\ \sigma_\Theta \\ \sigma_{R\Theta} \end{bmatrix} dz \quad (2)$$

$$[F]_{R,\Theta} = \left[ \sum_{R,\Theta}^k [q] \int_{k_{k-1}}^k (z_k - z_{k-1}) \right] [\epsilon^0]_{R,\Theta} + \frac{1}{2} \left[ \sum_{R,\Theta}^k [q] \int_{k_{k-1}}^k (z_k^2 - z_{k-1}^2) \right] [\epsilon^0]_{R,\Theta} \quad (3)$$

$$[F_{R,\Theta}] = [A]_{R,\Theta} [\epsilon^0]_{R,\Theta} + [B]_{R,\Theta} [k]_{R,\Theta} \quad (4)$$

$$[M_{R,\Theta}] = [B]_{R,\Theta} [\epsilon^0]_{R,\Theta} + [D]_{R,\Theta} [k]_{R,\Theta} \quad (5)$$

The laminate compliance matrix is given

$$\text{by } A_{ij} = \sum_{k=1}^n q_{ij}^k (z_k - z_{k-1}) \quad (6)$$

$$B_{ij} = \frac{1}{2} \sum_{k=1}^n q_{ij}^k (z_k^2 - z_{k-1}^2) \quad (7)$$

$$D_{ij} = \frac{1}{3} \sum_{k=1}^n q_{ij}^k (z_k^3 - z_{k-1}^3) \quad (8)$$

$$q_{RR} = c^4 q_{11} + s^4 q_{22} + 2c^2 s^2 q_{12} + 4c^2 s^2 q_{66}$$

where  $q_{\Theta\Theta} = s^4 q_{11} + c^4 q_{22} + 2c^2 s^2 q_{12} + 4c^2 s^2 q_{66}$

$$q_{Rs} = c^3 s q_{11} - s^3 c q_{22} - cs(c^2 - s^2) q_{12} - 2cs(c^2 - s^2) q_{12} q_{66}$$

$$q_{ss} = c^2 s^2 q_{11} - c^2 s^2 s q_{22} - 2c^2 s^2 s q_{12} + (c^2 + s^2) q_{12} q_{66}$$

$$q_{\Theta s} = s^3 c q_{11} - c^3 s q_{22} - cs(c^2 - s^2) q_{12} - 2cs(c^2 - s^2) q_{12} q_{66}$$

$$q_{11} = \frac{E_1}{1 - \gamma_{12} \gamma_{21}}$$

$$q_{22} = \frac{E_2}{1 - \gamma_{12} \gamma_{21}} \quad q_{12} = q_{21} = \frac{\gamma_{21} E_1}{1 - \gamma_{12} \gamma_{21}} = \frac{\gamma_{12} E_2}{1 - \gamma_{12} \gamma_{21}}$$

$$q_{66} = G_{12}$$

$$\begin{bmatrix} \epsilon^0 \\ k \end{bmatrix} = \begin{bmatrix} a & b \\ c & d \end{bmatrix} \begin{bmatrix} F \\ M \end{bmatrix}$$

$$[a] = [A]^{-1} - \left\{ [B^*] \times [D^*]^{-1} \right\} [C^*]$$

$$[b] = [B] \times [D^*]^{-1}$$

$$[c] = -[D^*]^{-1} \times [C^*]$$

$$[d] = [D^*]^{-1}$$

$$B^* = -[A]^{-1} \times [B]$$

$$C^* = [B] \times [A]^{-1}$$

$$D^* = [D] - \left\{ [B] \times [A]^{-1} \right\} [B]$$

In this case the composite cylinder is of four layers of lamina. Hence it may be assumed as a thick composite cylinder. The tangential and radial stresses components may be written using lames equation as;

$$\sigma_{\Theta\Theta} = \frac{R_i^2 R_o^2}{z^2} \left( \frac{P}{R_o^2 - R_i^2} \right) - \left( \frac{P R_i^2}{R_o^2 - R_i^2} \right) \quad (9)$$

$$\sigma_{RR} = \left( \frac{P R_i^2}{R_o^2 - R_i^2} \right) - \frac{R_i^2 R_o^2}{z^2} \left( \frac{P}{R_o^2 - R_i^2} \right) \quad (10)$$

$$\sigma_{R\Theta} = \left( \frac{P R_o^2}{R_o^2 - R_i^2} \right)$$

Maximum wall thickness is given by

$$H = R_i \left[ \sqrt{\frac{\sigma_{\Theta\Theta} + P}{\sigma_{\Theta\Theta} - P}} - 1 \right] \quad (11)$$

Also the strain displacement relationship for a thick cylinder can be expressed as

$$\delta_R = P R_o \left[ \sum_{i=1}^k \frac{1}{E_i} \left( \frac{R_{i+1}^2 + R_i^2}{R_{i+1}^2 - R_i^2} + \gamma \right) \right] + P R_o \left[ \sum_{i=1}^k \frac{1}{E_i} \left( \frac{R_{i+1}^2 + R_i^2}{R_{i+1}^2 - R_i^2} - \gamma \right) \right] \quad (12)$$

### III. NUMERICAL MODELLING

The beams were discretized using solid Tet 8 node 285 finite elements, available in ANSYS14.0. It consists of 8 nodes and several numbers of layers varying according to the requirement. In this particular study the element is designed as four layers of equal thickness. This type of symmetry is called as mirror symmetry. Four possible orientations of plies of 0°, 90° and 45° of the four layers are manipulated. The choice of solid Tet 8 node 285 element types is assumed to be valid as the composite material taken as a layered one.

A thick cylinder of internal diameter of 128mm and 160mm external diameter with 360 mm length and semi spherical end are taken for the study. The mechanical properties of the constituent materials taken for the study are presented through Table-I.

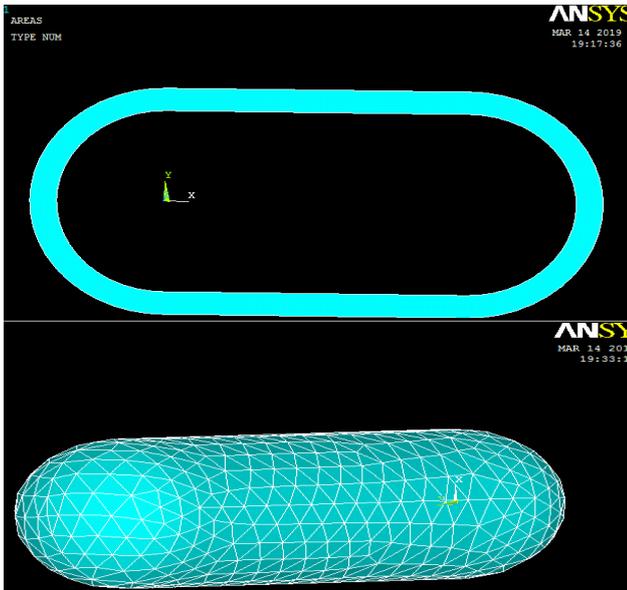


Fig 3(a):FEA model of pressure vessel.

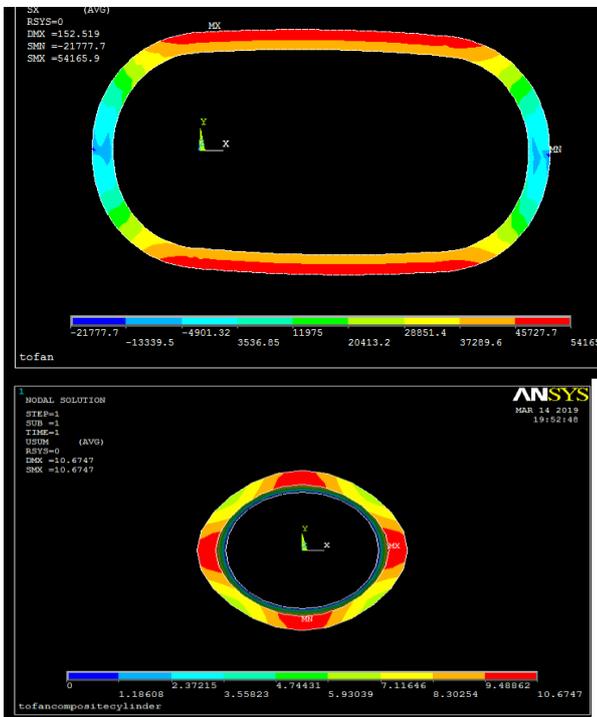


Fig3(b): Shows the radial displacements of FEA models of Pressure vessel.

IV. RESULT AND DISCUSSION

For the comparative study of the steel thick cylinder with the composite cylinder, an internal pressure of 120MPa is taken. Also, it is tried to find the best configuration of the fibre orientation among the designed four fiber orientations of 0°,45° and 90° the composite cylinders from here known as the sample cylinders and are presented in the Table. The results obtained are presented in Table-II.

The variation of hoop stress, radial stress, major principal stress, minor principal stress, resultant stress intensity and von mises stress intensity for the thick cylinders of different composite sample cylinder and steel cylinder subjected to 120MPa internal pressure are presented in Fig.4. From the graph it is very much clear that thick wall steel cylinder has

higher properties than the other test specimens in all aspect of the study. However from other four composite cylinders sample-4 having ±(0 ° /90 °) fibre orientation has superior property with less stress intensity. So the composite cylinder with ±(0 ° /90 °) may be taken for the study.

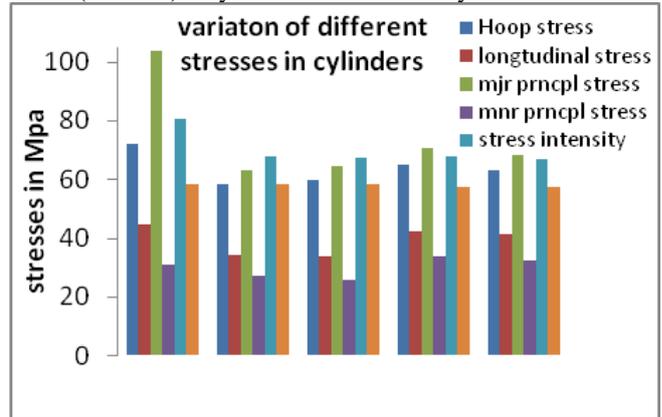


Fig. 4: variation of stress for different cylinder samples.

Fig.5 represents the longitudinal displacement of four composite cylinders samples along with the thick-walled steel cylinder. From the graph it can be observed that all of the samples are nearly equal longitudinal displacement. Hence the effect of fibre orientation does not play any important role on longitudinal displacement of the cylinders. Change of internal pressure also causes the change in observed stress parameters and longitudinal displacement of the thick cylinders. For the study the internal pressures are varied from 100MPa to 170MPa and the change in stress values and longitudinal displacement of thick steel cylinder and composite cylinder are determined. Figure 6 and Figure 7 represent the variation of hoop stress, longitudinal stress, three mutual principal stresses, resultant stress intensity and von mises stress intensity with change in internal pressures from 100MPa to 170MPa for steel cylinder and composite cylinder. From both of the graph it is quite clear that with increase in internal pressure different types of stresses developed inside the cylinder also increases. However, von mises stress intensity increases rapidly or more exponentially than other stress components.

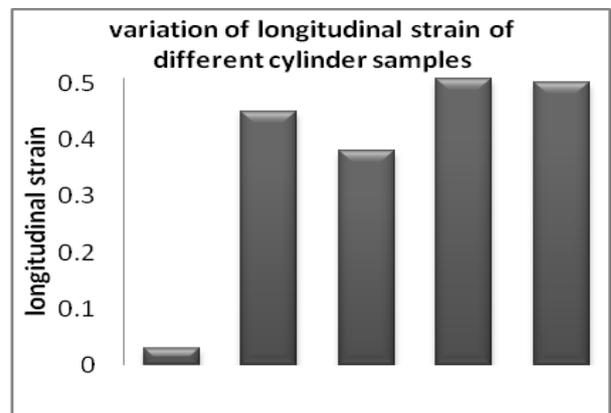


Fig.5: variations of longitudinal strain for different cylinder samples.



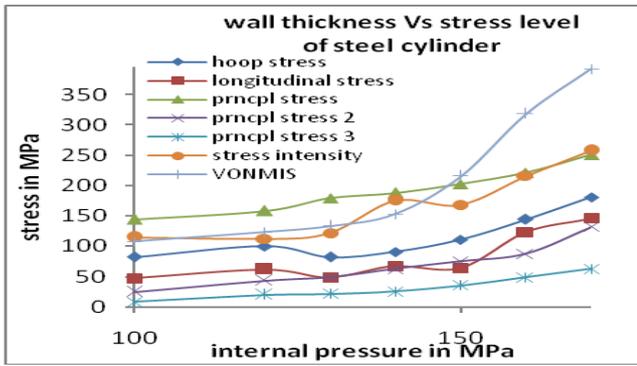


Fig.6: variation of internal pressure on steel cylinder.

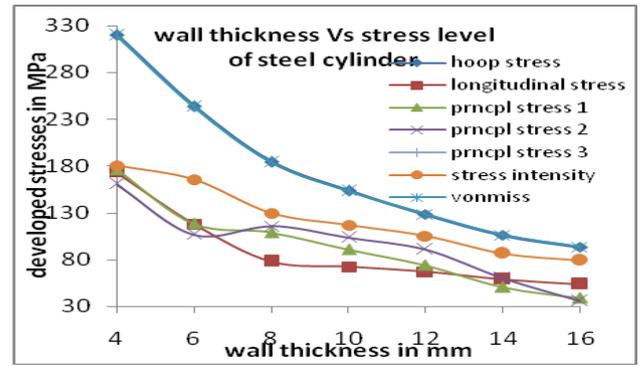


Fig. 9: variation of stresses with wall thickness for steel cylinder.

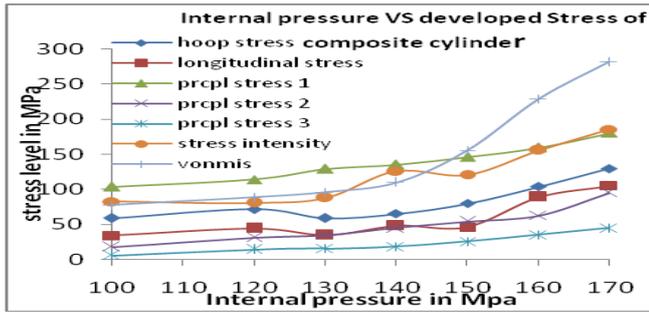


Fig.7: variation of stresses with internal pressure of composite cylinder.

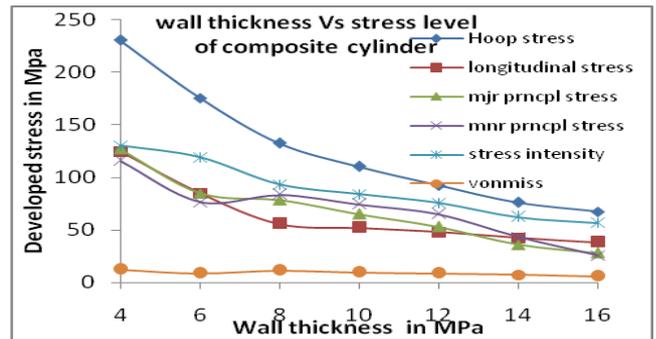


Fig.10: variation of stresses with wall thickness for composite cylinder.

Figure 8 represents the variation of the longitudinal displacement with the variation of internal pressure both for composite cylinder and steel cylinder. From the curve it is quite clear that with increase in internal pressure, longitudinal displacement increases. Also from the graph it can be seen that the longitudinal displacement increases gradually upto 130MPa internal pressure. Then further increase in internal pressure longitudinal displacement increases rapidly or exponentially. The effect of wall thickness on the stresses developed in the cylinder subjected to 120MPa internal pressure is studied. for the study the wall thickness of the cylinders is taken as 4mm, 6mm, 8mm, 10mm, 12mm, 14mm and 16mm respectively. Figure 9 represents the variation of the different stresses namely hoop stress, longitudinal stress, major principal stress, minor principal stress, resultant stress intensity and vonmisse stress intensity of the steel cylinder with the variation of the wall thickness. It can be seen that with increase in wall thickness the value of hoop stress, longitudinal stress, principal stresses, resultant stress intensity and von misses stress intensity decreases. The same nature of variation of the stresses for the composite cylinder is presented in fig.10.

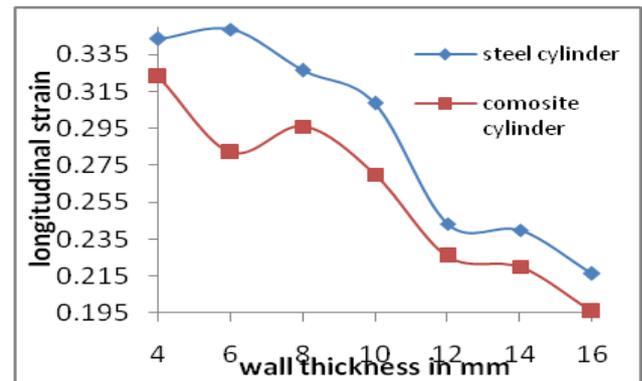


Fig. 11: variations of stresses with wall thickness of composite cylinder. Fig.11represents the variation of the longitudinal displacement of steel and composite cylinder with the variation of the wall thickness.

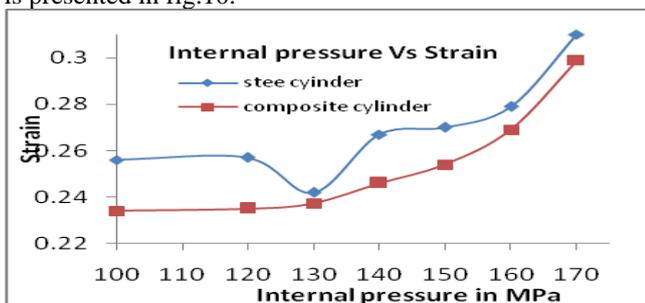


Fig.8: variation of longitudinal displacement with internal pressure.

**Table-II. Stresses of steel and composite cylinders. From the graph it is quite clear that with increase in wall thickness of the thick cylinder, the longitudinal displacement decreases rapidly.**

Samples		Stresses Developed in the Specimens							Deformation in mm ( $\Delta l$ )
		Normal stress in MPa		Principal stresses in MPa			Stress intensity (SI) in MPa	VonMises Stress in MPa	
		$\sigma_{\theta}$	$\sigma_r$	$\sigma_1$	$\sigma_2$	$\sigma_3$			
Steel		72	44.5	104	31	14.2	80.67	58.5	0.03
composite	sample-1(0°/45°) <sub>2s</sub>	58.2	34.07	62.9	27.22	11.89	67.63	58.58	0.45
	sample-2±(0°/45°)	59.8	33.65	64.6	25.6	11.3	67.6	58.5	0.38
	Sample-3(0°/90°) <sub>2s</sub>	65.1	42.5	70.9	33.7	12.82	67.66	57.36	0.508
	Sample-4±(0°/90°)	63.2	41.5	68.2	32.5	13.5	66.86	57.58	0.502

## IV. CONCLUSION

The steel cylinder has superior property than the composite cylinders. However, it can be observed that von mises stress intensity which plays a crucial role in the design of pressure vessel is nearly equal for the steel cylinder and all composite cylinders. But the compressive stress or hoop stress is quite lower. Also, from all of the fiber orientations taken for the study ± (0°/90°) lamina orientation may be considered for the study. All the test samples have negligible and nearly equal longitudinal deformation for all of the internal pressures and wall thicknesses. With increase in internal pressure the developed stress values developed inside the cylinder increases. Also, the longitudinal displacements are found to be increasing with the increase in internal pressures. Also, it is observed that with increase in the wall thickness decreases the developed stress values and longitudinal displacement.

## REFERENCE

1. Tauchert, T.R. Optimum Design of A Reinforced Cylindrical Pressure Vessel, *Journal of Composite Materials*, 1981, 15: pp.390-402.
2. Eckold, G.C. (1985). A Design Method for Filament Wound GRP Vessels and Pipework, *Composites*, 16:pp. 41-47
3. Adali, S., Summers, E.B. and Verijenko, V.E. Optimization of Laminated Cylindrical Pressure Vessels under Strength Criterion, *Composite Structures*, 1993, 25(3): pp.305-312
4. Cohen D., Influence of Filament Winding Parameters on Composite Vessel Quality and Strength, *Compos Part A-AppSciManufac* 1997; pp.1035-47
5. Cohen D., Mantell. S.C., Zhao. L., The Effect of Fiber Volume Fraction on Filament Wound Composite Pressure Vessel Strength. *composites Part B*; 32; 2001; pp.413-429
6. Xu S.Q & Yu, M.H. "Shakedown Analysis of thick walled cylinders subjected to internal pressure with the inified strength criterion", *International Journal of Pressure vessels & piping*, 2005; Vol 82, ; pp.706-712.
7. Naser, S.A.I, and Osama, M.A.H., Composite LPG Cylinders asan Alternative to Steel Cylinders: Finite Element Approach, *International Conference on Manufacturing and Materials Processing (ICMM 2006)*, Kuala Lumpur, Malaysia, 2006, ; pp.363-368
8. Antunes . P. J., Dias G. R., Nunes J. P. and Van Hattum . F. W. J., Finite Element Modelling of Thermoplastic Matrix Composite Gas Cylinders, *Journal of Thermoplastic Composite Materials*, Vol. 21—September 2008 , ; pp. 411
9. Yue Z., Li. X., Numerical Simulation of All-Composite Compressed Natural Gas (CNG) Cylinders for Vehicle, *Procedia Engineering* 37 , 2012 ; pp.31 – 36
10. TaheriF., Advanced fiber-reinforced polymer (FRP) composites for the manufacture and rehabilitation of pipes and tanks in the oil and gas industry. In: Bai J, editor. *Advanced fiber-reinforced polymer (FRP) composites for structural applications*. Sawston: Woodhead Publishing Limited., 2013; pp. 662-704
11. Lepikhin, P. P. , Romashchenko, V. A. , and Bakhtina, E. V., *Methods And Findings of Stress-Strain And Strength Analyses of Multilayer Thick-Walled Anisotropic Cylinders Under Dynamic Loading*

(Review). Part 1. Experimental Studies, *Strength of Materials*, Vol. 45, No. 1, January, 2013

12. Hemmatnezhad, M., Rahimi . G.H., Tajik M., Pellicano F., Experimental, numerical and analytical investigation of free vibrational behavior of GFRP-stiffened composite cylindrical shells, *Composite Structures*, 120.10.1016/j.comstruct.2014.10.011.
13. Guz I.A., Menshykova M., Paik J.K., Thick-walled composite tubes for offshore applications: an example of stress and failure analysis for filament-wound multi-layered pipes, *Ships and Offshore Structures*, 2015
14. Davies P., choqueuse D., Bigourdan B., Chachot P., Composite Cylinders for Deep Sea Applications: An Overview, *Journal of Pressure Vessel Technology*, Dec 2016, Vol. 138 / 060904-1
15. Ahmad, M.I.G., Hoa, S.V., Flexural stiffness of thick walled composite tubes , *Composite Structures*, Volume 149, 1 August 2016, ; pp.125-133
16. Ahmadi, I., Interlaminar stress analysis in general thick composite cylinder subjected to nonuniform distributed radial pressure, *Mechanics of Advanced Materials and Structures*, Volume 24, 2017 - Issue 9, ; pp.773-788
17. Ramos, I., Park, Y.H., Sanchez, J.U., Analytical and Numerical Studies of a Thick Anisotropic Multilayered Fiber-Reinforced Composite Pressure Vessel , *J. Pressure Vessel Technology*, 141(1), 011203 (Dec 07, 2018)
18. Arhant, M. ,Briancon, C., Burtin, C., Davis, P., Carbon/polyamide 6 thermoplastic composite cylinders for deep sea applications, *Composite Structures* Volume 212, 15 March 2019, ; pp.535-546.

## Authors Profile

### First Author



**Mr. Sarada Prasad Parida** is presently pursuing PhD in the Department of Production Engineering at Veer Surendra Sai University of Technology, Burla, Odisha, India. His research interest includes Mechanical Vibration, FEM and Composite Material.

### Corresponding Author

**Dr. Pankaj Charan Jena** (Ph.D in Mechanical Engineering, Ja davpur University, Kolkata, India) is working as Associate Professor, Department of Production Engineering, Veer Surendra Sai University of Technology, Burla, Odisha, India. His current research interests include Composite Material Design and Modeling, control, dynamics and fault diagnosis using Artificial Intelligence.

