

Lime Based Dry Mixes with Carbonate Aggregates

Y.V. Pukharenko, T.V. Kharitonova

Abstract: *The use of carbonate rocks as aggregates for cement concretes and mortars is limited due to their insufficient strength and the threat of corrosion. The use of quarry dust from crushing carbonate rocks are technically and economically feasible in building compositions based on air-hardening lime. The results of the study of the effect of replacing a part of quartz sand in lime mortar by limestone and dolomite fine aggregates on the basic physical and mechanical properties of lime mortars for restoration are presented in the paper. The matrix of planning experiments, which allows increasing the informativity of the research results in order to reduce the number of experiments in the search for optimal values, is proposed. The efficiency of replacement of the quartz sand with quarry dust of carbonate rocks in the production of dry mixes for restoration is shown.*

Key words: *air lime, limestone, dolomite, dry mixtures for restoration.*

I. INTRODUCTION

The main binder in the composition of restoration mortars is air lime. This is due to the observance of the principle of historicism in relation to these materials as well as the design features of architectural monuments – cultural heritage [1-3]. High deformability and vapor permeability of lime-based mortars as well as their good adhesion to the ceramic brick determine the operational reliability of plaster and masonry mortars in the construction and finishing of massive structures of artificial and natural stone [4,5].

The modern practice of restoration is characterized by the active development of the direction of dry mixtures produced in accordance with the requirements for restoration materials – the authenticity of the material composition as well as physical and mechanical properties [6]. It should be noted that the economic component (minimizing the cost of production) and the high relevance of increasing the durability of materials is important to consider in addition to the need to ensure the principles of restoration in the production of dry mixtures [2, 7-10].

The main task in the design of dry mixes for restoration is the selection of components that meet the following requirements: low cost, year-round availability, technical and historical validity of their use in the composition of restoration renders [11-13]. Based on the above-mentioned the use of quarry dust from crushing carbonate rocks namely limestone and dolomite as fine aggregate in lime renders for restoration is appropriate. The developed deposits of

limestones and dolomites are widespread in the territory of the Russian Federation and, in particular, in the Northwest region [14,15]. Dolomite and limestone quarry dust can be attributed to the affordable and inexpensive potential raw materials. Drying and classification is required for dry mix technology. But these operations are also necessary for the traditional fine aggregate for renders – quartz sand [15-17].

The use of carbonate rocks in the composition of the aggregate of mortars was noted by a number of researchers in terms of compliance with the principle of historicism with respect to the material composition [18-21].

The validity of the widespread use of carbonate aggregates in the composition of lime dry mixtures consists in the affinity of the matrix and filler grains as well as lower density of carbonate rocks in comparison with quartz sand [22]. Historical masonry and plaster mixes, as a rule, are characterized by the strength class from M25 to M75. Accordingly the use of limestone is not limited to its lower strength in comparison with quartz sand [23-27].

Thus, the use of quarry dust of carbonate rocks as a fine aggregate in restoration dry mixtures seems reasonable from the historical, technical and economic side. The aim of this study is to assess the effect of limestone and dolomite introduced instead of the quartz sand on the properties of the lime dry mixture.

II. MATERIALS AND METHODS OF RESEARCH

Hydrated lime from Rosizvest Company (Rossosh city), limestone of fractions 0-2,5, quartz-feldspar sand, dolomite flour with grain size of 0.01-0.1mm were used in experiments.

Quantitative assessment of the effect of replacing quartz sand with carbonate fine aggregates was carried out on the basis of three-level two-factor experiment. Limestone consumption in per cent of the aggregate mass (X1) and dolomite consumption in per cent of the aggregate mass (X2) were considered as the studied factors. Limestone consumption has varied from 0 to 80% with the variation step of 40%. Dolomite consumption has varied from 0 to 20% with the step of variation of 10%.

III. FULL-FACTOR EXPERIMENT PLANNING MATRIX

The developed matrix of planning full-factorial experiment, which allows to obtain the regression equation as well as to differentially assess the impact of individual factors at each level of variation, is a feature of this study.

Revised Manuscript Received on September 07, 2019

Y.V. Pukharenko, Dr. Sci. Tech., Professor, Saint Petersburg State University of Architecture and Civil Engineering, Saint-Petersburg, Russia

T. V. Kharitonova, PhD-student, Saint Petersburg State University of Architecture and Civil Engineering, Saint-Petersburg, Russia.

Lime Based Dry Mixes with Carbonate Aggregates

The large informativity of the results obtained with minimum number of experiments is achieved according to Table 1.

The limit of compressive strength (R_{comp} , MPa), adhesion to brick (Ad, MPa) and water vapor permeability (PR, mg/m²·h·Pa) were determined as functions of the response. The change of the workability of mixtures by cone immersion was estimated depending on the ratio between the fine aggregates since all mixtures were carried out at the constant water-to-solid ratio equal to W/S=19%. The amount of hydrated lime was 15% by weight of the dry mixture.

Table 1 Planning matrix of two-factor three-level experiment

No.	X ₁	X ₂	N ₂	X ₁	X ₂	N ₂	X ₁	X ₂
Chart at X ₂ at the lower level			Chart at X ₂ at the middle level			Chart at X ₂ at the top level		
1	-1	-1	7(5)	-1	0	13(6)	-1	1
2	0	-1	8	0	0	14(12)	0	1
3	1	-1	9	1	0	15	1	1
Chart at X ₁ at the lower level			Chart at X ₁ at the middle level			Chart at X ₁ at the top level		
4(1)	-1	-1	10(2)	0	-1	16(3)	1	-1
5	-1	0	11(8)	0	0	17(9)	1	0
6	-1	1	12	0	1	18(15)	1	1

Note: repeated experiments are shown in parentheses to improve the accuracy of the variance determination. Number of parallel experiments are 6.

IV. RESULTS AND DISCUSSION

The use of carbonate aggregates causes the proportional decrease of the workability of the compositions. Complete replacement of quartz sand with the fine aggregate of limestone (80%) and dolomite (20%) is accompanied by the decrease of the amount of cone immersion from 8.5 mm to 15 mm. Replacement of sand by 20% of dolomite leads to the decrease of the workability up to 2.5cm. Mixture with the content of 60% of quartz sand and 40% of limestone is characterized by the decrease of the workability of 1.8 cm as shown in Figure 1. Thus, the use of dolomite fine aggregate is associated with more intense decrease of fresh mortar workability.

The increase of lime mortar strength is observed in case of quartz sand amount decreases. Thus, the strength increases in two times with the introduction of 10% of dolomite and 80% of limestone instead of quartz sand. The same result can be achieved with the introduction of 20% of dolomite and 40% of limestone instead of quartz sand as shown in Figure 2.

Determination of adhesion to the brick surface was made using full-bodied ceramic brick with strength class of 125 and water absorption of 10% by weight. The brick surface was previously polished and the brick was kept in water until full saturation before applying the fresh mortar.

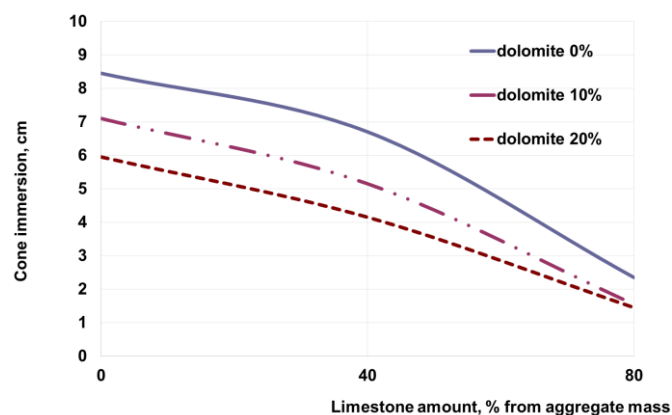


Figure 1. Influence of limestone and dolomite ratio on fresh mortar workability

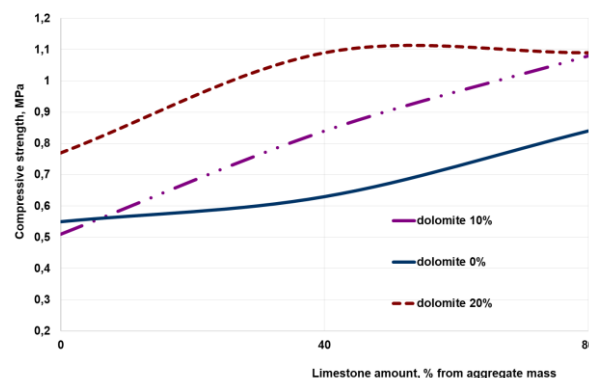


Figure 2. Influence of limestone and dolomite ratio on the compressive strength

Increasing the proportion of carbonate rocks in the aggregate mix has positive effect on the adhesion strength to the brick surface as shown in Figure 3. The greatest increase of adhesion takes place at the maximum content of limestone of 80%. The share of dolomite effects the increase of adhesion as well.

It should be noted that the nature of the separation of the mortar from the brick at the values of the adhesion strength up to 0.06 MPa is adhesive and at larger values of the adhesion strength is cohesive.

Unambiguous dependences could not be identified in relation to the vapor permeability of the studied mortars. It can be argued that the influence of the type of filler on the vapour permeability is not traced and the observed changes in numerical values are associated with the error of the method of determination as one can see in Figure 4. This conclusion is confirmed by high dispersion of values in each series of experiments.

The regression equation for the compressive strength of the compositions studied can be considered to demonstrate the advantages of the proposed experimental planning matrix and to find the best decisions.

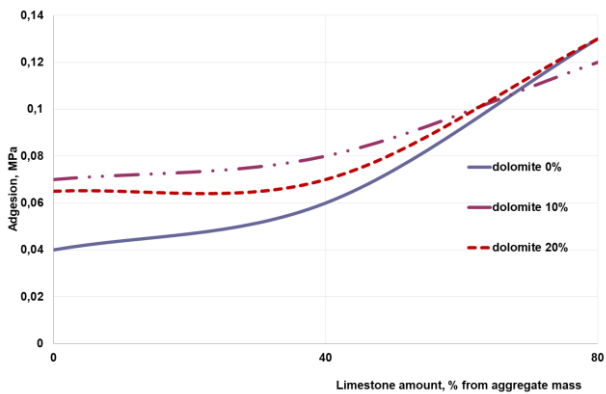


Figure 3. Influence of limestone and dolomite ratio on adhesion strength to the brick surface

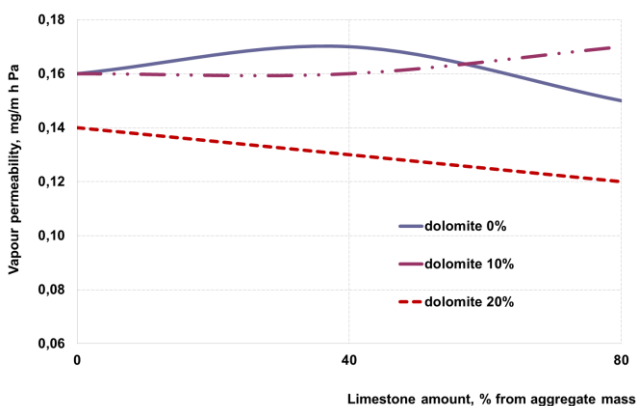


Figure 4. Influence of limestone and dolomite ratio on the vapour permeability of the studied mortars

The regression equation of a full-factorial experiment of type 3^2 for estimation of the ultimate strength taking into account the significance of the coefficients is as follows:

$$R_{comp} = 0.82 + 0.2 \cdot X_1 + 0.16 \cdot X_2 \quad (1)$$

The analysis of the obtained regression equation shows that the strength of the samples increases with increasing amount of both limestone and dolomite. The influence of factors on the strength, estimating by the coefficients, is almost the same. Maximum strength is achieved when the values of the factors corresponding to the upper level. Similar conclusions were obtained earlier in the analysis of strength dependence graphs at the fixed value of one factor and the variation of the other according to Figure 2. Such graphical analysis can be used in the search for rational compositions reducing the cost of experiments through the step study. In case of early detection of the lack of the required result, the search in the intended direction can be stopped without conducting the experiment in full.

In addition, one can note another feature of the use of graphical analysis of the results of the experiment. Smoothing of the results (the model does not exactly repeat the experiment) occurs at building a mathematical model in the form of a regression equation. It is almost impossible to reproduce the family of dependencies obtained experimentally. In particular, the maximum value of strength is obtained at the values of the factors when one of them is at the upper level and the second at the main (zero) level in our case of consideration.

V. CONCLUSION

The efficiency of replacement of quartz sand with quarry dust of carbonate rocks in the production of dry mixes for restoration was shown. The results of replacing a part of quartz sand in lime mortar by limestone and dolomite fine aggregates on physical and mechanical properties of lime mortars were obtained in the paper. The matrix of planning experiments, which allows increasing the informativity of the research results in order to reduce the number of experiments in the search for optimal values, was proposed. Thus, the use of limestone and dolomite as fine aggregate for lime mortars (dry mixtures) can increase the compressive strength in two times, the strength of adhesion to ceramic bricks in three times. In this case, the vapour permeability remains unchanged and it is characterized by high values (about 0.15 mg/m·h·Pa).

REFERENCES

1. Yu.A. Belentsov and O.M. Smirnova, Influence of Acceptable Defects On Decrease of Reliability Level of Reinforced Concrete Structures. *International Journal of Civil Engineering and Technology*, 9(11), 2018, pp. 2999–3005.
2. Shangina, N., Pukharenko, Y., Kharitonov, A., & Kharitonova, T. (2017). Dry mixes for the restoration: basic principles of design. In *MATEC Web of Conferences* (Vol. 106, p. 03021). EDP Sciences.
3. Kharitonov A., Belentsov Y., Matveeva L., Shangina N. Brickwork structure influence on reliability of structures being constructed. *IOP Conf. Series: Earth and Environmental Science* 90(1) 012086 (2017).
4. Koňáková, D., Čáchová, M., Vejmelková, E., Keppert, M., Jerman, M., Bayer, P., ... & Černý, R. (2017). Lime-based plasters with combined expanded clay-silica aggregate: Microstructure, texture and engineering properties. *Cement and Concrete Composites*, 83, 374-383.
5. Kharitonov A., Korobkova M., Smirnova O. The influence of low-hard dispersed additives on impact strength of concrete. *Procedia Engineering* (2015) 108: 239–244.
6. De Nardi, C., Brito de Carvalho Bello, C., Ferrara, L., & Cecchi, A. (2019). Self-healing lime mortars: an asset for restoration of heritage buildings. In *Sustainable Materials Systems and Structures SMSS 2019* (Vol. 128, pp. 652-659). FRA.
7. O.M. Smirnova, Development of Classification of Rheologically Active Microfillers for Disperse Systems With Portland Cement and Super plasticizer. *International Journal of Civil Engineering and Technology*, 9(10), 2018, pp. 1966–1973.
8. O.Smironova. Compatibility of shungisite microfillers with polycarboxylate admixtures in cement compositions. *ARNP Journal of Engineering and Applied Sciences*. 2019. Vol. 14, No. 3, pp.600-610.
9. Pavia, S., & Brennan, O. (2019). Portland cement-lime mortars for conservation. In *Historic Mortars* (pp. 129-142). Springer, Cham.
10. O.M. Smirnova, Technology of Increase of Nanoscale Pores Volume in Protective Cement Matrix, *International Journal of Civil Engineering and Technology*, 9(10), 2018, pp. 1991–2000.
11. Nogueira, R., Pinto, A. P. F., & Gomes, A. (2018). Design and behavior of traditional lime-based plasters and renders. Review and critical appraisal of strengths and weaknesses. *Cement and Concrete Composites*, 89, 192-204.
12. O.M. Smirnova and D.A.Potyomkin, Influence of Ground Granulated Blast Furnace Slag Properties on The Superplasticizers Effect, *International Journal of Civil Engineering and Technology*, 9(7), 2018, pp. 874–880.
13. Shaybadullina, Arina, Yuliya Ginchitskaya and Olga Smirnova. "Decorative Coating Based on Composite Cement-Silicate Matrix." *Solid State Phenomena*. Vol. 276. Trans Tech Publications, 2018, pp. 122-127.
14. L.F. Kazanskaya and O.M. Smirnova. Supersulphated Cements with Technogenic Raw Materials. *International Journal of Civil Engineering and Technology*, 9(11), 2018, pp.3006–3012.

15. Smirnova, O. Concrete mixtures with high-workability for ballastless slab tracks. *Journal of King Saud University-Engineering Sciences*, 2017, 29(4), 381-387
16. Upadhyaya, S., Nanda, B., & Panigrahi, R. (2019). Experimental Analysis on Partial Replacement of Fine Aggregate by Granite Dust in Concrete. In *Sustainable Construction and Building Materials*. vol 25. pp. 335-344. Springer, Singapore.
17. Kharitonov A., Ryabova A., Matveeva L., Shangina N., Belentsov Y. Research on Long-Term Strength of Glass-Fiber Reinforced Concrete. International Scientific Conference Energy Management of Municipal Transportation Facilities and Transport EMMFT 2017 pp. 640-646.
18. Smirnova O.M. Obtaining the High-performance Concrete for Railway Sleepers in Russia. *Procedia Engineering*, Volume 172, 2017, Pages 1039-1043
19. Mednikova E. Yu., Rappoport P. A., Selivanova N. B. Old Russian mortars. *Soviet archaeology*. 1983. No. 2. 2., pp. 152-161.
20. O. M. Smirnova, Rheologically Active Microfillers for Precast Concrete, *International Journal of Civil Engineering and Technology*, 9(8), 2018, pp. 1724–1732.
21. Lobzova R. V., Nosov, K. S., Petrographic characterization of mortars Russian fortresses of the XVI-XVII. *Vestnik RUDN, series of Engineering studies*. 2009. No. 2. 1. pp. 91-98..
22. Smirnova O.M. Compatibility of Portland cement and polycarboxylate-based superplasticizers in high-strength concrete for precast constructions. *Magazine of Civil Engineering*, No. 6, 2016. pp.12-22.
23. Barnat-Hunek, D., Siddique, R., Klimek, B., & Franus, M. (2017). The use of zeolite, lightweight aggregate and boiler slag in restoration renders. *Construction and Building Materials*, 142, 162-174.
24. Groot, C. J., & Gunneweg, J. T. (2019). Choosing Mortar Compositions for Repointing of Historic Masonry Under Severe Environmental Conditions. In *Historic Mortars* (pp. 143-154). Springer, Cham.
25. Smirnova O.M., Kharitonov A.M., Belentsov Y.A. Influence of polyolefin fibers on the strength and deformability properties of road pavement concrete. *Journal of Traffic and Transportation Engineering (English Edition)*. 2019. 6(4): 407-417.
26. Kharitonov, A. M., Y. M. Tikhonov, and Y. A. Belentsov. "Influence of concrete strength evaluation method accuracy on reliability levels of geotechnical structures." *Geotechnics Fundamentals and Applications in Construction: New Materials, Structures, Technologies and Calculations* (2019): 135.
27. O.M. Smirnova, Evaluation of Superplasticizer Effect in Mineral Disperse Systems Based on Quarry Dust, *International Journal of Civil Engineering and Technology*, 9(8), 2018, pp. 1733–1740.
28. Heravi A.A., Smirnova O., Mechtcherine V. Effect of strain rate and fiber type on tensile behavior of high-strength strain-hardening cement-based composites (HS-SHCC). *RILEM Bookseries*. 2018. V. 15. pp.266-274.
29. Kazanskaya L., Privalov N., Privalova S. (2019), Fine ground granulated blast furnace slag for saving quantity of binder, *E3S Web of Conferences* 110:01055.
30. Petrova, T., Smirnova, O. Influence of fine mineral fillers on properties of plasticized cement compositions. In *Modern Building Materials, Structures and Techniques*. Proceedings of the International Conference, 2010, Vol. 10, p. 250. Vilnius Gediminas Technical University, Department of Construction Economics & Property.
31. Kazanskaya L.F., Belentsov Yu.A. (2019), Methods of Assessing the Strength of Masonry to Ensure the Reliability of Reconstructed Structures. *International Journal of Innovative Technology and Exploring Engineering*, 8(10), pp. 3435-3439

AUTHORS PROFILE



Y.V. Pukharenko, Dr. Sci. Tech., Professor, Head of Department Building Materials and Technology, Saint Petersburg State University of Architecture and Civil Engineering, Saint-Petersburg, Russia.

Author and co-author of more than 282 published scientific and educational papers including 4 collective monographs, 240 scientific papers, 19 educational works, 26 inventions.
https://www.spbgasu.ru/Universitet/Vuz_v_lichah_2/name%D0%9F/id195/



T.V. Kharitonova, PhD-student, Saint Petersburg State University of Architecture and Civil Engineering, Saint-Petersburg, Russia.

Research interests: technology of dry mixes, restoration materials