



# The Effect of TiO<sub>2</sub> in Glass Fiber Reinforced Polymer

R. Ganesh, V. Balaji,

**Abstract:** Composite materials serve as an alternative to the conventional metals. These materials used in various applications like automotive, aerospace, marine industries, etc. so, there is a requirement for detailed base of structural design. Air craft industries use composite material in their major structural works instead of the metals as composites have low weight density. The major key area of these structural work is fabricating the joint of composites. The data base for these joint strengths is more important.

In this research work, the effect of Titanium Di Oxide filler materials in the GFRP and on the lap joint Bidirectional ply Glass Fiber Reinforced Polymer is fabricated for changing the performance characteristics of composite. Tensile and flexural test has been carried for the above specimen. Investigation of the effect of the lap joint specimens has been carried experimentally. The results of the specimens are compared.

**Keywords :** Titanium Di Oxide, GFRP, Lap joint, Tensile strength, Flexural strength.

## I. INTRODUCTION

The composites are the alternate of the engineering metals. Composites are made of fiber reinforcement in matrix with addition of fillers. The fiber reinforcement enhances the mechanical characteristics such as tensile strength, compression strength, flexural strength, impact strength, etc.

Because of its high specific strength and stiffness, these glass fiber reinforced polymers are used in aerospace industries. And also, it has good thermal and electrical resistant properties. The factors affecting characteristics of composites are types of reinforcement, matrix, fillers used.

Composite materials are also fabricated inclusion of filler material for reducing cost, for improving the physical, mechanicals performance characteristics. Sometimes many combinations of filler materials are added to improve the functional performance. Several techniques have been used for fabricating composite materials such as hand layup method, vacuum bag moulding, filament winding etc. Hand layup tech is easiest and cost-effective manufacturing method for fabricating composites,

In air craft industries, for fabricating structural part, one of the key process called joining process. Joint structure has to have good mechanical properties to prevent failure. In particular the strength of joint must be good enough. The joint strength can also be tested through universal testing machine.

The properties of materials and joints has to be investigated and to be recorded for database for the materials. possible.

## II. SELECTION OF MATERIALS

### A.Epoxy resin Matrix

Epoxy resins have at least two epoxide groups is termed as oxirane group. Variable chain length causes high pure polymer during polymerization.



Fig. 1.Epoxy Resin. (8912 VBR)

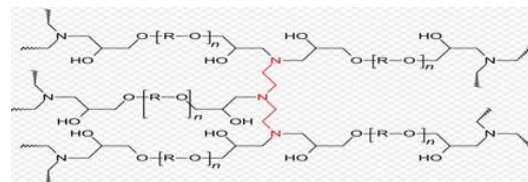


Fig. 2. Polymer cross chain link of Epoxy

### B.Properties of epoxy

. Because of its high strength in polymer groups, it has been used in many applications widely. It has been uses in many electrical and electronics application due to its high electrical resistance property. And also it is chemically inert. These materials also have good adhesive properties and it can be used to adhere dissimilar metals.

### C. E-glass fiber

High strength and high stiffness of glass fiber causes this fiber has been used in variety of applications. By melt spinning technique, these fibers are fabricated. Drawing a molten glass through a platinum nozzle is producing these fibers.

Revised Manuscript Received on October 30, 2019.

\* Correspondence Author

**R.Ganesh\***, Mechanical department, Vel Tech Rangarajan Dr.Sagunthala R&D Institute of Science and Technology, Chennai, India. Email: ganeshr\_07@rediffmail.com

**V.Balaji**, Mechanical department, Vel Tech Rangarajan Dr.Sagunthala R&D Institute of Science and Technology, Chennai, India. Email: balajivasudev@gmail.com

© The Authors. Published by Blue Eyes Intelligence Engineering and Sciences Publication (BEIESP). This is an [open access](http://creativecommons.org/licenses/by-nc-nd/4.0/) article under the CC-BY-NC-ND license <http://creativecommons.org/licenses/by-nc-nd/4.0/>



Fig. 3.E- Glass fiber

#### D.Properties of E glass fiber

These E glass fibers having simple manufacturing technique and raw materials are abundantly available. Due to this reason, it is available in low cost.

Due to its high strength and high stiffness it has the capability to use in composite materials. it is chemically inert and has good heat resistance. It serves as good electrical insulation.

#### E. Titanium dioxide

Titanium dioxide is used as a pigment, it is also known as titanium white.



Fig. 4.Titanium Di Oxide

. The table 1 shows the physical properties of these nanoparticles.

Table- I: Physical properties

Properties	Metric
Density	4.3 g/cm <sup>3</sup>
Molar value	79.9438 g/mol

### III. MANUFACTURING PROCESS

#### A.Abbreviations and Acronyms

Hand lay up techniques is used to prepare the thermosetting polymer matrix composite in the mould which has the similar shape of product.

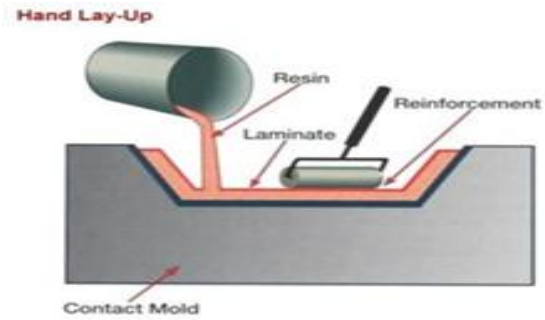


Fig. 5.Hand Layup process

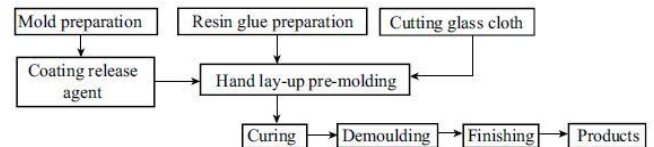


Fig. 6.Process Flow in Hand Layup Technique

### IV. EXPERIMENTAL WORK

#### A.Preparation of specimen for tensile strength

Tensile strength is the property of material to resist breaking of material under tensional force.

As per ASTM –D-638-III, the specimen has been prepared for tensile test. MCS 60 UTE-60 universal testing machine has been used to perform the test.

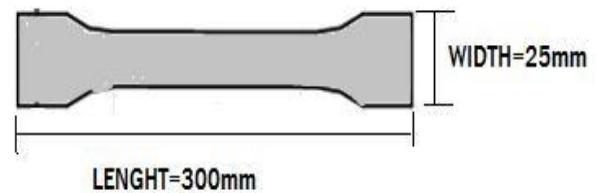


Fig. 7.Tensile strength single plate specimen

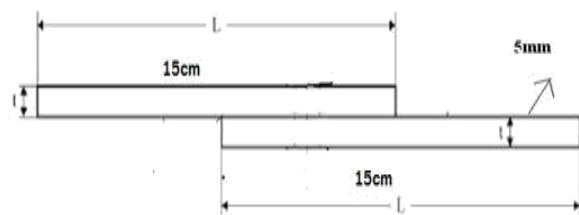


Fig. 8.Tensile strength Lap joint composite specimen

#### B.Preparation of specimen for flexural strength

Flexural strength is a material property the stress in a material just before it yielding.

By using three point bend test on universal testing machine UTE-60T for the specimen of size as per ASTM D-790-2003 has been prepared.

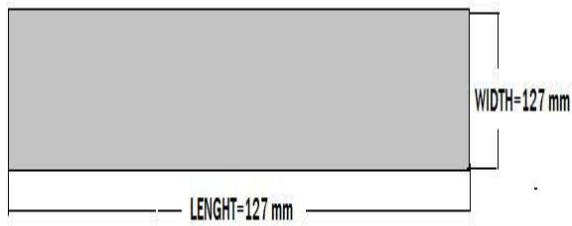


Fig. 9. Flexural strength single plate composite specimen



Fig. 10. Flexural strength Lap joint composite specimen

## V.RESULT AND DISCUSSION

### A.Results of specimen for Tensile strength and Maximum flexural load

The Table - II shows the various compositions of fillers in GFRP single plate and its tensile strengths and flexural loads are compared.

Table- II: Tensile strength and Flexural Load values of Single plate specimen

Percentage of filler mixed with matrix	Tensile strength in MPa	Maximum flexural load in KN
TiO <sub>2</sub> (0%)	68.31	0.32
TiO <sub>2</sub> (5%)	85.77	0.42
TiO <sub>2</sub> (10%)	50.88	0.17

The Table - III shows the various compositions of fillers in GFRP lap joint plate and its tensile strengths and flexural loads are compared.

Table- III: Tensile strength and Flexural Load values of Lap joint specimen

Percentage of filler mixed with matrix	Tensile strength in MPa	Maximum flexural load in KN
TiO <sub>2</sub> (0%)	7.77	0.74
TiO <sub>2</sub> (5%)	13.48	0.41
TiO <sub>2</sub> (10%)	14.24	0.76

### B.Stress strain curve for the single plate specimens tested

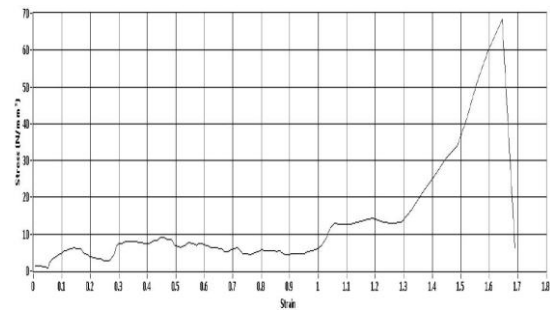


Fig. 11. Tensile stress strain curve of specimen with out TiO<sub>2</sub>

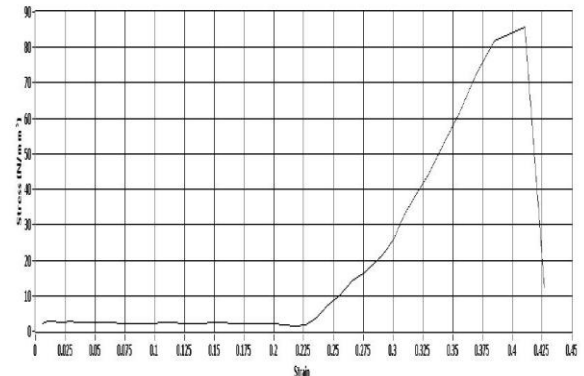


Fig. 12. Tensile stress strain curve of specimen with 5% TiO<sub>2</sub>

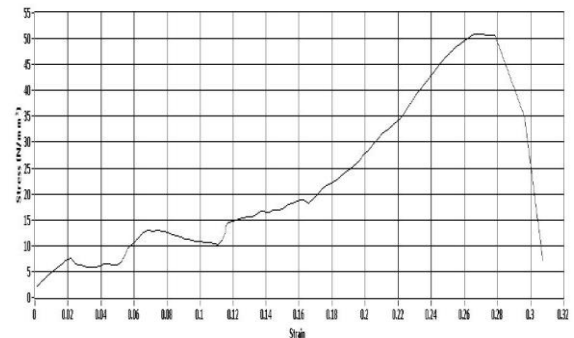


Fig. 13. Tensile stress strain curve of specimen with 10% TiO<sub>2</sub>

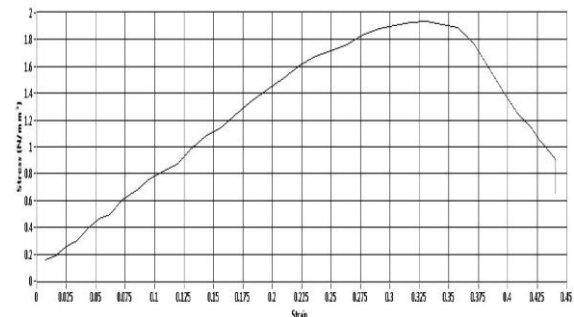


Fig. 14. Flexural stress strain curve of specimen with out TiO<sub>2</sub>

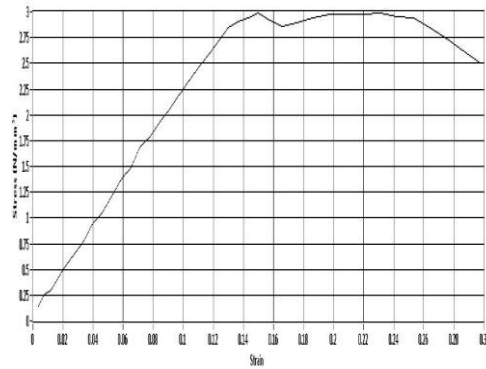


Fig. 15. Flexural stress strain curve of specimen with 5% TiO<sub>2</sub>

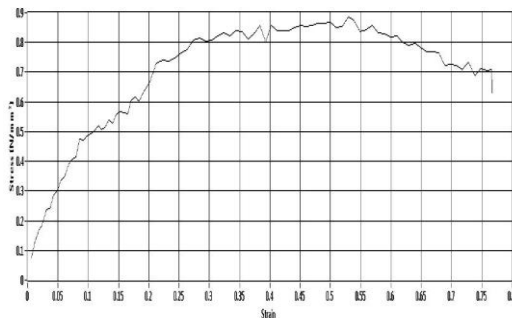


Fig. 16. Flexural stress strain curve of specimen with 10% TiO<sub>2</sub>

#### C.Stress strain curve for the Lap joint specimens tested

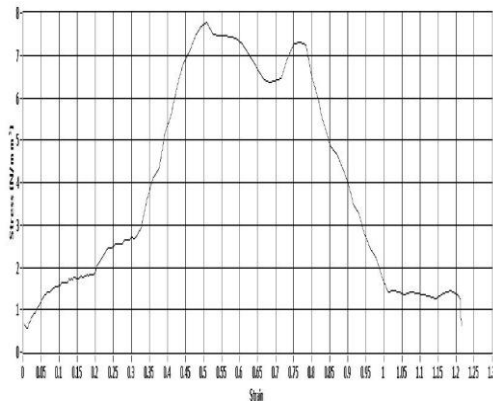


Fig. 17. Tensile stress strain curve of specimen with out TiO<sub>2</sub>

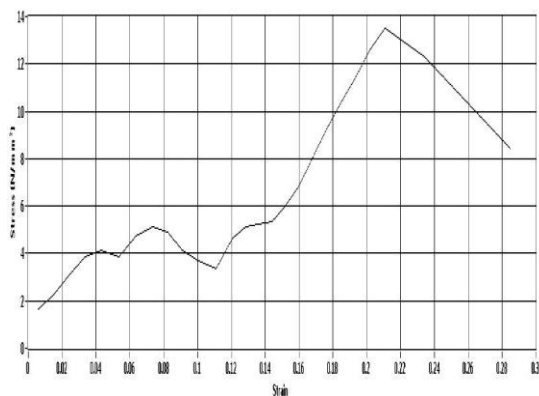


Fig. 18. Tensile stress strain curve of specimen with 5% TiO<sub>2</sub>

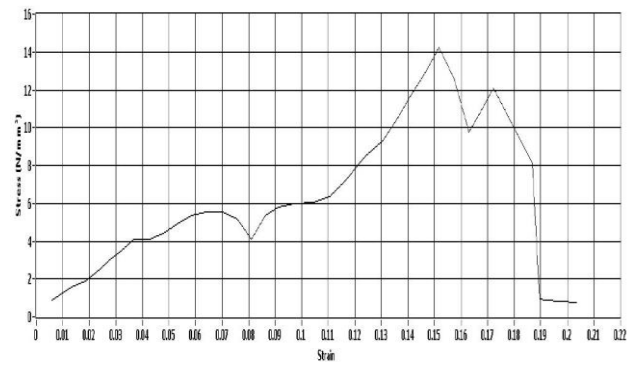


Fig. 19. Tensile stress strain curve of specimen with 10% TiO<sub>2</sub>

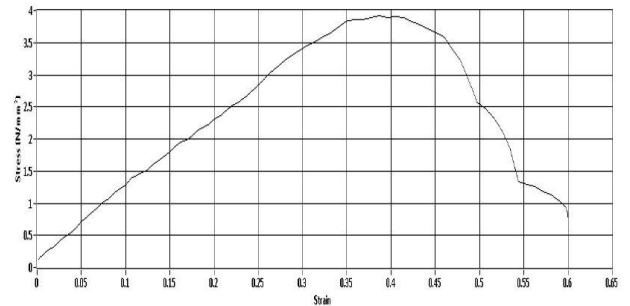


Fig. 20. Flexural stress strain curve of specimen with out TiO<sub>2</sub>

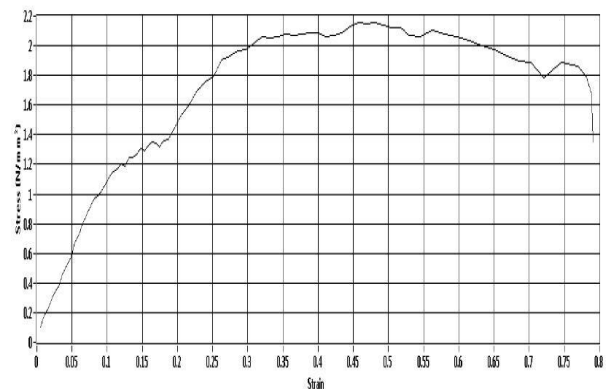


Fig. 21. Flexural stress strain curve of specimen with 5% TiO<sub>2</sub>

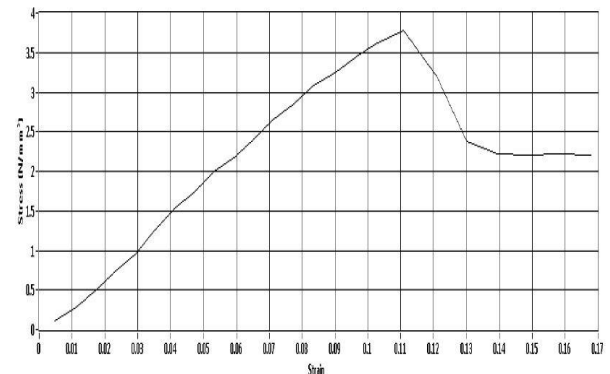


Fig. 22. Flexural stress strain curve of specimen with 10% TiO<sub>2</sub>



## VI. CONCLUSION

In this work, GFRP were fabricated and the materials were machined according to ASTM standard to prepare specimens of single plate and lap joint. The tensile strength test and Flexural strength test were carried on the specimens of single plate and lap joint of different composition of TiO<sub>2</sub> fillers. The Experimental 1 results for GFRP with different composition of TiO<sub>2</sub> (0%, 5%, 10%) are obtained.

From this work, the tensile strength and flexural load are maximum of 85.77MPa and 0.42KN respectively for the 5% of TiO<sub>2</sub> GFRP when compared with other compositions (TiO<sub>2</sub> (0%, 10%)) results were obtained.

Then the tensile strength of the for 10% of TiO<sub>2</sub> GFRP lap joint is maximum of 14.24MPa with other compositions. And the flexural strength of TiO<sub>2</sub>(10%) GFRP is maximum of 0.76 KN.

According to the results of tensile and flexural, 5%&10% TiO<sub>2</sub> GFRP is suitable for Aircraft and Automobile application than 0%TiO<sub>2</sub> GHRP.

## ACKNOWLEDGMENT

The authors like to thank honorable Chairman of Veltech Rangarajan Dr.Sagunthala R&D Institute of Science and Technology, Chennai. For providing the research facilities and support to paper this article. The authors like extend their gratitude to Dr. R.Velu and Dr.P.Anand for their continuous support in conducting the experiment.

## REFERENCES

1. K. Kalaichelvan Effect Of Adhesive Thickness Area Of Single Lap Joints In Composite Laminate Using Acoustic Emission Technique And Fea, 2007
2. J. Mahesh Patil And M.Salih Hybrid (Bonded/Bolted) Composite Single-Lap Joints And Its Load Transfer Analysis International Edition Of Advanced Engineering Technology 2003.
3. Logesh, K. & Raja, V.K.B. (2017) Formability analysis for enhancing forming parameters in AA8011/PP/AA1100 sandwich materials. Int J Adv Manuf Technol 93: 113.  
<https://doi.org/10.1007/s00170-015-7832-5>
4. Venkatasudhahar M, Velu R, Logesh K. Investigation on the effect of flyash on tensile , flexural and impact strength of hybrid 2018;8:117–22.
5. R.Ganesh, Manimaran,A., Logesh, K. “Experimental study on investigation of sic in glass fiber reinforced lap joint” International Journal of Mechanical and Production Engineering Research and Development, Volume 08,issue 3,pp893-900,(November 2017).
6. Zheng Wang ,Link Li, Meng Gong. Measurement of dynamic modulus of elasticity and damping ratio of wood-based composite using the cantilever beam vibration technique, journal of construction and building materials. Vol. 28, 2012, pp. 831-834..
7. R.Ganesh, K.Karthik, A.Manimaran, “Effect of silicon carbide on single lap joint glaass fiber reinforcent polymer matrix composite” international journal of mechanical engineering & technology (ijmet),, Volume 09,issue 6,pp403-408,(June 2018).
8. Tamer Sinmazçelik.et.al (2011) A review: Fiber metal laminates, background, bonding types and applied test methods. Materials and Design 32 (2011) 3671–3685
9. Manex Martinez-Agirre, Maria Jesus Elejabarrieta. Dynamic characterization of high damping Viscoelastic materials from vibration test data. Journal of Sound and Vibration, Vol. 330, 2011, PP. 3930–3943.
10. R. Eslami-Farsani.et.al.(2016) Properties Modification of Fiber Metal Laminates by Nano fillers. International Journal of Materials and Metallurgical Engineering. Vol:10, No:7, 976-980.

## AUTHORS PROFILE



**R. Ganesh** working as Assistant Professor at Vel Tech Rangarajan Dr.Sagunthala R&D Institute of Science and Technology, Chennai, India.



**V. Balaji** working as Assistant Professor at Vel Tech University, Chennai, India.