

Effect of Stiffener Size on Ultimate Strength of GFRP Blade Stiffened Composite Plates

Pranesh F, Vignesh Kumar K, Sandeep Bharadwaj V, Rahima Shabeen S

Abstract: The ultimate strength of blade stiffened composite plates with various sizes of the stiffener is studied numerically using ANSYS software. The GFRP stiffened composite plates were modeled in ANSYS as SHELL elements with orthotropic properties. The finite element model of the GFRP stiffened composite plates was analysed to obtain deflection, axial deformation and stress contours and the ultimate load values. The obtained results of the finite element model were validated with that of available experimental data. The validated finite element model was used to study the effect of stiffener size. The stiffener size was varied from 10mm to 100mm. It was observed that smaller size of stiffeners were ineffective in stiffening the plate. The optimum size of stiffener was found to be 50mm to 75 mm. .

Keywords : Blade stiffener, GFRP, Stiffened Plates, Strength.

I. INTRODUCTION

GFRP composites have properties of better corrosion resistance and high strength to weight ratio. Stiffened plates are used for application in ship structures and bridge decks. Plates are thin compression members and hence are prone to buckling. The presence of stiffeners in the plate helps in subdividing the plate into smaller units, thereby decreasing the b/t ratio of the plate and increasing the load carrying capacity. Blade stiffeners are simple rectangular flats which are either attached to the plate by co-curing or fabricated integrally with the plate.

Studies have been done of GFRP stiffened composite plates by many researchers. Boni et al (2012) compared numerical and experimental results of buckling and post-buckling behavior. Akula (2014) analyzed composite stiffened panel subjected to axial compression using FEM. Shi et al (2014) studied the failure of stiffened composite panels subjected to environmental effects under axial compression. Bhaskar and Pydah (2014) analyzed orthotropic stiffened plates. Pydah and Bhaskar (2015) presented an analytical approach for simply supported blade-stiffened rectangular plates accounting for transverse shear deformation and rotary inertia. Yetman et al (2015) investigated the skin stiffener debonding of hat stiffened panels under compressive loading. Sudirsasstry et al (2015) analysed stiffened composite panels with straight, T and I shaped stiffeners under uniform axial compression. Jin et al (2015) analyzed hat stiffened composite panels. Zhu et al

(2015) studied the effect of stiffener stiffness on buckling and post buckling behavior of stiffened composite panel. Ricco et al (2015) studied the skin-stringer debonding in stiffened composite panels under compression. Mo et al (2016) studied buckling and post-buckling behavior of hat-stringer stiffened composite panel subjected to axial compression. Kolanu et al (2016) studied the compression behavior of GFRP blade, T and hat stiffened panels. Vosoughi et al (2017) analyzed stiffened laminated composite panels with the aim of optimizing the buckling load. Tan et al (2018) studied the effect of impact damage on single T-stiffened composite panels. Anita et al (2017) studied the behavior of GFRP stiffened composite plates with rectangular cutouts. Ravikumar et al (2018) predicted the buckling load of stiffened and unstiffened composite panels using ANSYS 14.0. Zhang et al (2018) analyzed eccentrically stiffened plates. Behera et al (2018) analyzed stiffened composite plates.

The aim of this paper is to study the ultimate load and failure mode of blade stiffened composite plates with different sizes of stiffeners.

II. FINITE ELEMENT ANALYSIS

A. Specimen Details

GFRP stiffened composite plates with blade stiffeners were considered for the study. The experimental data available in literature (1) is considered for the present numerical study. The size of the stiffened composite plate considered is 1160 mm (Breadth) x 960mm (Length). The spacing between the stiffeners is 300 mm. The layup structure was $[0]_6$. The material properties of GFRP laminate were also taken from literature (1) and are given in Table I.

B. Finite Element Modeling

The stiffened composite plate was modeled in ANSYS, finite element software. The plate and the stiffener were modeled as SHELL181. SHELL181 is a 4-noded shell element with finite rotation capabilities. The plate and the stiffener were divided into rectangular elements with aspect ratio 0.8 to 1.0. The plate and the stiffener were considered integral and hence were joined by careful positioning of coincident nodes. The plates were first subjected to buckling analysis. The buckling load was used to introduce imperfection in the model for non-linear analysis. The edges of the plate were considered as simply supported. The longitudinal edges and one of the transverse edges were restrained against translational motion in the z- and y-axis. The x-axis was kept unrestrained to allow axial compression of the plate during axial loading.

Revised Manuscript Received on September 05, 2019.

Pranesh F, Department of Civil Engineering, Anna University, India, praneshfcivil@gmail.com


Vignesh Kumar K, Department of Civil Engineering, Anna University, India, vvkvigneshkumar@gmail.com

Sandeep Bharadwaj V, Department of Civil Engineering, Anna University, India, sandeep123@gmail.com

S. Rahima Shabeen, Department of Civil Engineering, Anna University, India, rahima.shabeen@gmail.com

Effect of Stiffener Size on Ultimate Strength of GFRP Blade Stiffened Composite Plates

The other transverse edge was restrained against translational motion in x, y and z- direction. Load was applied along the axial direction as pressure load. The FE model is shown in Fig. 2. Large displacement static analysis method is used because FRP plate when subjected to loads suffers large displacement. For the final solution, Arc-length method is chosen by giving the maximum and minimum multiplier values.

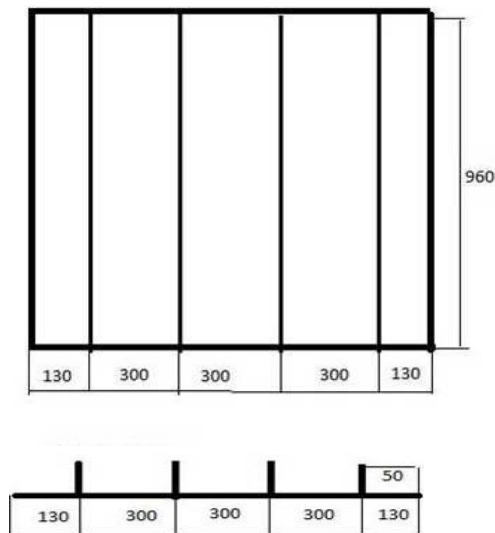

All dimensions in mm

Fig. 1. Geometry of Stiffened Composite Plate

Table- I: GFRP Material Properties

| Properties | Values |
|--------------------------------------|-------------------------|
| Tensile strength -warp direction | 250 MPa |
| Tensile strength - weft direction | 211 MPa |
| Longitudinal modulus, E_1 | 15800 MPa |
| Transverse modulus, E_2 | 15333 MPa |
| Shear modulus (G_{12}) | 2806 MPa |
| Flexural modulus | 15388 N/mm ² |
| Major Poisson's ratio (ν_{12}) | 0.1386 |
| Minor Poisson's ratio (ν_{21}) | 0.1248 |

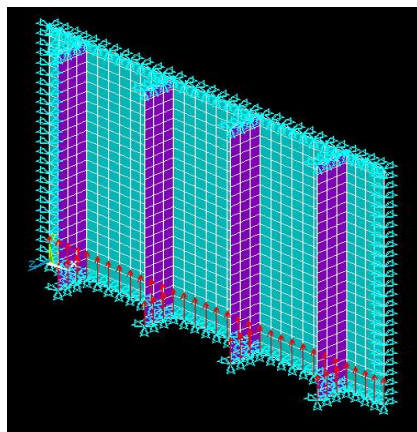


Fig. 2. FE Model of Stiffened Composite Plate

C. Validation

The data available in literature was used for validation of the model. The Ultimate load obtained from experiment and FE analysis is shown in Table II. The out-plane deformation contours are shown in Fig. 2. It is observed that the FE model predicts the ultimate load behavior of stiffened composite plate very well and hence can be used for further analysis.

Table- II: GFRP Material Properties

| Description | Experiment | Finite Element Analysis |
|-----------------|----------------------------------|----------------------------------|
| Failure Load | 252 kN | 250 kN |
| Type of Failure | Plate buckling between Stiffener | Plate buckling between stiffener |

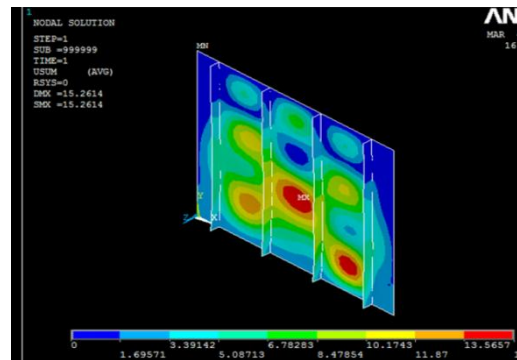


Fig. 2. Out of plane Deformation of FE A50

D. Parametric Study

The validated finite element model is used to predict the effect of stiffener size on the ultimate load and failure mode. The parametric study is conducted on stiffened composite of same the overall size : 1160mm (B) x 960 mm (L) and stiffener spacing of 300mm. The thickness of the stiffener is kept constant at 5mm and the height of the the stiffener is varied as 10mm, 25mm, 75mm, and 100mm. The dimensions of the plates considered for parametric study is shown in Table 2.

Table- II: Details of Specimens

| Specimen | Stiffener height | Thickness | h/t |
|----------|------------------|-----------|-----|
| A10 | 10 mm | 5 mm | 2 |
| A25 | 25 mm | 5 mm | 5 |
| A50* | 50 mm | 5 mm | 10 |
| A75 | 75 mm | 5 mm | 15 |
| A100 | 100 mm | 5 mm | 20 |

*validated based on experimental data

III. RESULTS AND DISCUSSIONS

The ultimate load of plates with various stiffener size is shown in Table III. The ultimate load increases by almost twice when the size of the stiffener is increased from 10 mm to 50 mm. When the size of the stiffener is increased from 50 mm to 75mm and 75 mm to 100mm, there is a marginal increase in ultimate load.

The out-of-plane deformation contours and stress contours for specimen A10 is shown in Fig. 3 and Fig. 4 respectively. It is observed that the stiffened plate buckles under overall buckling. The stiffener seems inadequate to stiffened the plate and subdivide into smaller units.

Table- III: Failure Loads and Mode of Failure

| Specimen | Failure Load | Type of Failure | Region of Maximum Stress |
|----------|--------------|--|--------------------------|
| A10 | 106.8 kN | Overall plate buckling | On the plate |
| A25 | 176.8 kN | Overall plate buckling | On the stiffeners |
| A50 | 252 kN | Plate buckling between the stiffeners | On the stiffeners |
| A75 | 266.3 kN | Plate buckling between the stiffeners | On the stiffeners |
| A100 | 279 kN | Plate buckling between the stiffeners and Stiffener Buckling | On the stiffeners |

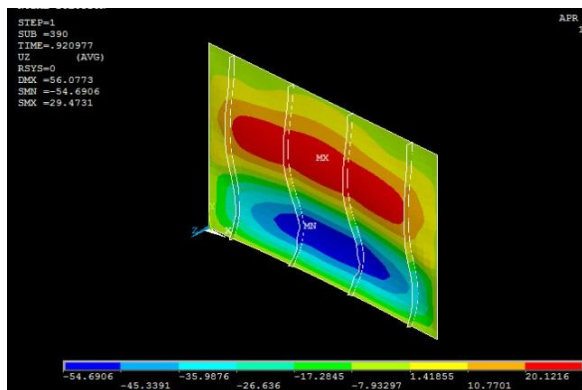


Fig. 3. Out of plane Deformation of A10

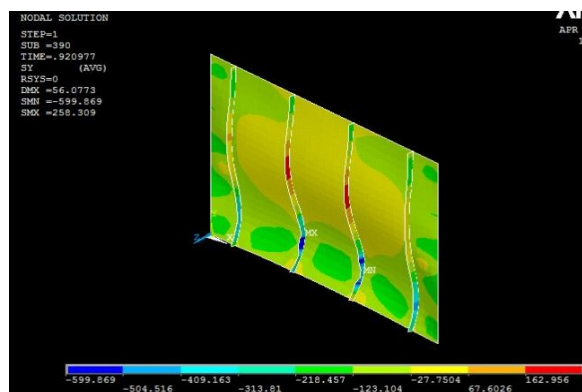


Fig. 4. Stress Contours of A10

The out-of-plane deformation contours and stress contours for specimen A25 is shown in Fig. 5 and Fig. 6 respectively. Overall buckling of the plate is observed and the stiffeners buckle along with the plate. The stiffeners do not have the adequate stiffness to subdivide the plate into plates of smaller b/t.

The out-of-plane deformation contours and stress contours for specimen B75 is shown in Fig. 7 and Fig. 8 respectively. Plate buckling between the stiffeners is observed. The Stiffeners stiffened the stiffened composite plate.

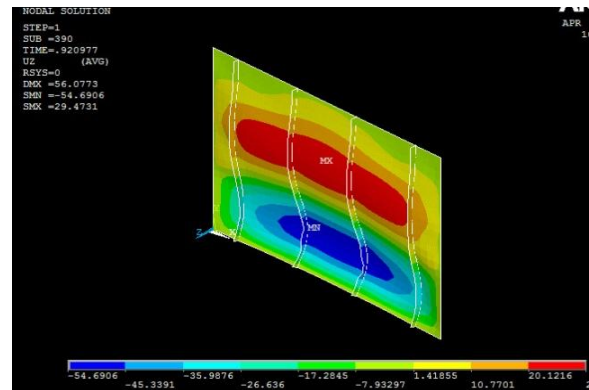


Fig. 5. Out of plane Deformation of A25

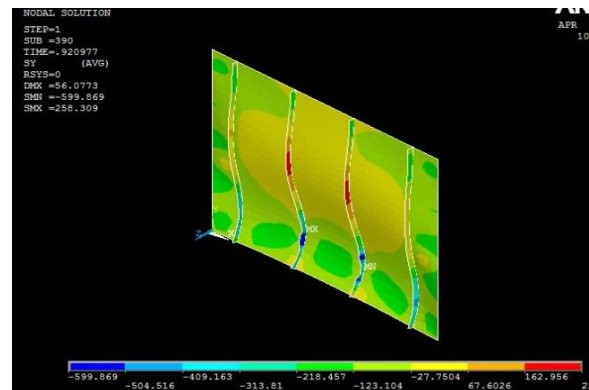


Fig. 6. Stress Contours of A25

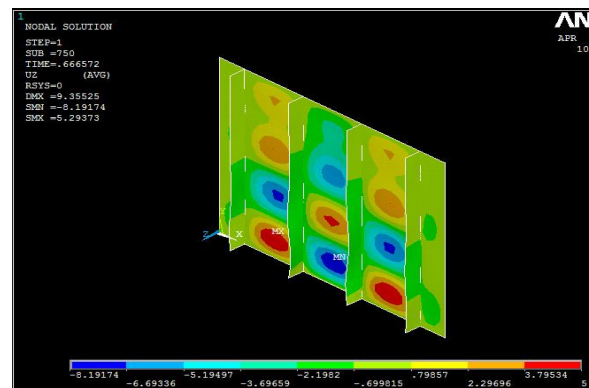


Fig. 7. Out of plane Deformation of A75

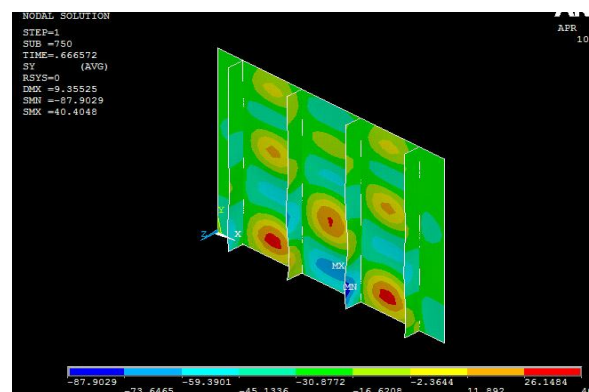


Fig. 8. Stress Contours of A75

The out-of-plane deformation contours and stress contours for specimen B100 is shown in Fig. 9 and Fig. 10 respectively. Buckling of the stiffener is observed.

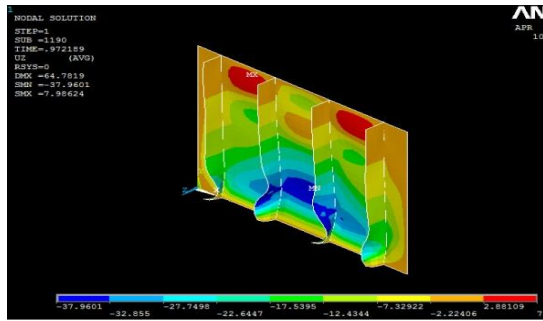


Fig. 9. Out of plane Deformation of A100

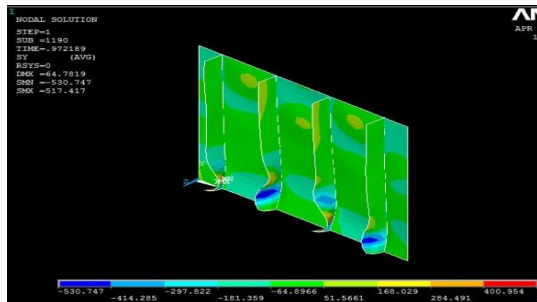


Fig. 10. Stress Contours of A100

IV. CONCLUSION

Numerical analysis of blade stiffened GFRP composite plates with various sizes of stiffeners was done using ANSYS and the following conclusions were made from the study within the limitations of the study.

- 1) FRP composite plate stiffened with 10mm and 25mm stiffeners undergo overall plate buckling, so the presence of stiffeners does not adequately stiffen the plate.
- 2) FRP composite plate stiffened with 50mm and 75mm stiffeners undergoes plate buckling in between the stiffeners.
- 3) Stiffener buckling is observed in FRP composite plate stiffened with 100mm stiffeners.
- 4) Smaller sized stiffeners are ineffective and increasing the stiffener to a larger size makes the stiffener buckle. Hence the optimum size of stiffener is 50 mm to 75mm.
- 5) Hence, it can be concluded that stiffener size has an influence on ultimate load and mode of failure of GFRP stiffened composite plates.

REFERENCES

1. Alagusundaramoorthy, P. and Shabeen, S. Rahima, "Strength of stiffened composite plates with opening", *Conference RINA, Royal Institution of Naval Architects - International Conference on Ship and Offshore Technology 2009 - ICSOT India 2009*: Developments in Ship Design and Construction, 2009, pp 601-620.
2. Akula, V.M.K., "Multiscale reliability analysis of a composite stiffened panel", *Composite Structures*, 116, 2014, pp. 432-440.
3. Behera, R.K., Patro, S.S., Sharma, N. and Joshi, K.K., "Eigen-frequency analysis of stiffened laminated composite plates using finite elements", *Materials Today Proceedings*, 5:2018, pp 20152-20159.
4. Bhaskar, K. and Pydah, A., (2014). "An elasticity approach for simply-supported isotropic and orthotropic stiffened plates". *International Journal of Mechanical Sciences* 89, 2014, pp. 21-30.
5. Bhaskar, K. and Pydah, A., (2015). "Accurate discrete modelling of stiffened isotropic and orthotropic rectangular plates." *Thin-Walled Structures* 97, 2015, pp. 266-278.
6. Jin, B.C., Li, X., M, Rodrigo, M., Pun, A., Joshi, S., and Nut, S., "Parametric modeling, higher order FEA and experimental investigation of hat-stiffened composite panels". *Composite Structures* 128, 2015, pp. 207-220.

7. Kolanu, N.R., Prakash, S.S., and Ramji, M., "Experimental study on compressive behavior of GFRP stiffened panels using digital image correlation". *Ocean Engineering* 114, 2016, pp. 290-302.
8. Kumar, P. R., Gupta, G., Shamili, G.K. and Anitha, D., "Linear buckling analysis and comparative study of un-stiffened and stiffened composite plate". *Materials Today Proceedings* 5(2), 2018, pp. 6059-6071.
9. Masood, S.N., Vishakh, R., Viswamurthy, S.R., and Gaddikeri, K.M., (2018). "Influence of stiffener configuration on post-buckled response of composite panels with impact damages." *Composite Structures* 194, 2018, pp. 433-444.
10. Mo, Y., Ge, D., and Zhou, J., "Experiment and analysis of hat-stringer-stiffened composite curved panels under axial compression." *Composite Structures* 123, 2015, pp. 150-160.
11. Priyadarshini, S.A., Prasad, A.M. and Sundaravadevelu, R., "Analysis of GFRP stiffened composite plates with rectangular cutout". *Composite Structures* 169, 2017, pp.42-51.
12. Riccio, A., Raimondo, A., and Scaramuzzino, F., A robust numerical approach for the simulation of skin-stringer debonding growth in stiffened composite panels under compression. *Composites: Part B* 71, 2015, pp. 131-142.
13. Shi, X., Li, S., Chang, F. and Bian, D., Postbuckling and failure analysis of stiffened composite panels subjected to hydro/thermal/mechanical coupled environment under axial compression. *Composite Structures* 118, 2014, pp. 600-606.
14. Sudhirsasthy, Y.B., Budarapu, P.R., Madhavi, N., and Krishna, Y., "Buckling analysis of thin wall stiffened composite panels." *Computational Materials Science* 96, 2015, pp. 459-471.
15. Tan, R., Guan, Z., Sun, W., Liu, Z., and Xu, J., "Experiment investigation on impact damage and influences on compression behaviors of single T-stiffened composite panels." *Composite Structures* 203, 2018, pp. 486-497.
16. Vosoughi, A.R., Darabi, A., Anjabin, N., and Topal, U., "A mixed finite element and improved genetic algorithm method for maximizing buckling load of stiffened laminated composite plates." *Aerospace Science and Technology* 70, 2017, pp. 378-387.
17. Yetman, J.E., Sobey, A.J., Blake, J.I.R., and Sheno, R.A., Investigation into skin stiffener debonding of top-hat stiffened composite structures. *Composite Structures* 132, 2015, pp. 1168-1181.
18. Zhang, S. and Xu, L., (2018). "Exact static analysis of eccentrically stiffened plates with partial composite action." *Composite Structures* 98, 2018, pp. 117-125.
19. Zhu, S., Yan, J., Chen, Z., Tong, M., and Wang, Y., "Effect of the stiffener stiffness on the buckling and post-buckling behavior of stiffened composite panels – Experimental investigation." *Composite Structures* 120, 2015, pp. 334-345.

AUTHORS PROFILE



Pranesh K did his Bachelors in Engineering from College of Engineering, Guindy, Anna University. His research interests include composite materials and finite element analysis.



Vignesh Kumar K did his Bachelors in Engineering from College of Engineering, Guindy, Anna University. His research interests include composite materials and finite element analysis.



Sandeep Bharadwaj V did his Bachelors in Engineering from College of Engineering, Guindy, Anna University. His research interests include composite materials and finite element analysis.



S. Rahima Shabeen is an Assistant Professor at College of Engineering Guindy, Anna University. She did her Ph.D from IIT Madras. Her interests include FRP composites. She has published papers on FRP composites. She is a member of various organizations like FRP institute, Indian Concrete Institute, INSDAG.