

# Assessment of NR/EPDM Blend Ratio using Graphical Method

Kannayeram G, Megala V, Prakash NB, Muniraj R, Sundar B

**Abstract:** In this proposed work, Natural Rubber (NR) and Ethylene Propylene Diene Monomer (EPDM) are blended using Graphical method in 50:50 ratio. The blends are characterized by electrical characteristics like surface resistivity, arc resistance and mechanical properties such as comparative tracking index, elongation at break and tensile strength as per standard ASTM and IEC. Graphical method type of blending overcomes the drawback of Optimal Blend Ratio (OBR) which gives an approximate solution. The composite blended gives good electrical, mechanical characteristics with good weathering resistance.

**Keywords :** Polymeric insulator; Blend composition; Ethylene Propylene Diene Monomer; Natural Rubber.

## I. INTRODUCTION

Polymeric materials have outstanding chemical, physical, mechanical and electrical properties compared with ceramic and glass insulator, hence used in medium/high voltage cable insulation and jacket materials. The electrical and mechanical characteristics of NR and EPDM can be improved by blending two materials in proper ratio [1-4]. EPDM exhibits a saturated polymer back bone structure which results in stable, heat resistance, oxidation resistance, weather ageing, high tensile strength and oil swell resistance properties. Infrared (IR) spectral analysis reveals bonding capability of blends [5].

The effect of NR/EPDM blend ratio to improve electrical and mechanical characteristics is investigated using conventional methods and graphical method. The conventional method gives only approximate solution so there is need for optimization technique. The identification of suitable blend ratio depends upon the applications, such as high tensile strength, high dielectric strength and arc resistance. In practical situations it is difficult to identify the suitable blend ratio for specific application. Optimal blend must provide good mechanical and electrical characteristics. The electrical and mechanical characteristics are tested using suitable experiments and plotted using graphical method for

Revised Manuscript Received on October 05, 2019.

\* Correspondence Author

**Kannayeram G\***, EEE Department, National Engineering College, Kovilpatti, Tamilnadu, India. Email: g.kannayeram@gmail.com

**Megala V**, EEE Department, SRM Institute of Science and Technology, Ramapuram, Chennai, Tamilnadu, India, Email: megala95@gmail.com

**Prakash NB**, EEE Department, National Engineering College, Kovilpatti, Tamilnadu, India. Email: nbprakas@gmail.com

**Muniraj R**, EEE Department, National Engineering College, Kovilpatti, Tamilnadu, India. Email: munirajphd@gmail.com

**Sundar B**, EEE Department, National Engineering College, Kovilpatti, Tamilnadu, India. Email: sundarb@gmail.com

cable applications [6]. Several computational techniques like Particle Swarm Optimization (PSO), Genetic Algorithm (GA) and Improved PSO (IPSO) are used to solve the complex engineering problems. In our future work PSO is used to identify the suitable blend ratio for cable applications [7,8]. PSO has population based evolutionary algorithm with simple concepts, high computation efficiency and easy to implement compared to other algorithm. PSO is initialized with population of random variable. It is associated with random velocity and potential solution called particles. Particles are flown through problem space. In PSO any weightage is assigned randomly to any particular parameter such as electrical/mechanical or both. PSO is implemented for two different sets. One set has equal weightage of key parameters i.e. one electrical & one mechanical and another set consists of unequal weightage of key parameters [9, 10]

## II. SYNTHESIS OF NR/EPDM BLEND

NR and EPDM material were purchased from M/S Joy Rubbers, India. NR is of RNA type. EPDM is in the ratio of 52:48 of ethylene: propylene. Blending is the technology of converting the raw rubber resin into useful materials through the addition of various ingredients [11]. The preparation of NR/EPDM blends were carried out in two roll mixing mill dispersion kneader machine with chamber temperature at 35°C.

Conventional mixing procedures are used for preparation of these blend materials. At initial condition NR is masticate for 3 minutes followed by moulding in electrically headed plate machine for 5 minutes. The compounds are moulded by compression at 70°C using hydraulic hot press machine. Sheet specimens are made by zeon blend compositions hot press machine as listed in Table-I.

Table- I: Sheet Specimens blended compositions

MATERIALS (phr)	Blend 1	Blend 2	Blend 3	Blend 4	Blend 5
NR (%)	100	70	50	30	0
EPDM (%)	0	30	50	70	100
Dicumyl per oxide	2.5	2.5	2.5	2.5	2.5
ZnO	5	5	5	5	5
Stearic acid	2	2	2	2	2
MBT	0.5	0.5	0.5	0.5	0.5
TMTD	1.5	1.5	1.5	1.5	1.5
Sulphur	1.75	1.75	1.75	1.75	1.75

## Assessment of NR/EPDM Blend Ratio using Graphical Method

The commercial graded chemicals like Stearic acid, Zinc oxide (ZnO), Sulphur, Mecapto Benzo Tiazole (MBT), Tetra Methyl Thiuram Disulphide (TMTD) were used as additives to increase vulcanization rate by activating the accelerators. The weightage of additives are expressed in parts per hundred (phr) of rubber shown in Table-I.

### III. EXPERIMENTATION AND CHARACTERIZATION OF NR/EPDM

The test conditions and procedures for the electrical and mechanical characteristics of the polymers used are explained below.

#### A. Tensile Strength and Elongation at Break (EB)

The tensile strength and Elongation at break are determined as per standard ASTM D412. Tensile strength is obtained from the cross head movement at constant rate using universal testing machine. EPDM elastomer possesses good mechanical strength and outstanding resistance to attack by oxygen, ozone and weather [12].

#### B. Arc Resistance

Arc resistance is measured in seconds as per standard ASTM D495. A voltage of 12.5 kV is applied to the sample, whose size is 5 x 5 x 0.3cm. Voltage is increased gradually in steps until the arc occurs between the electrodes. The carbon path developed on the surface of the material leads to conduction.

#### C. Surface and Volume Resistivity

The surface and volume resistivity of the samples are measured as per standards IEC 60093 and ASTM D257 respectively using Million Mega Ohm meter MM-108D by prestige electronics. The thickness and diameter of the specimen are 3mm and 100 mm respectively. A DC supply of 500V is applied for 60 seconds at room temperature between main and guarded electrode to determine surface and volume resistivity.

#### D. Comparative Tracking Index (CTI)

CTI is measured as per standards IEC 60112 by CEAST meter. A 500V is applied to the test specimen of 3mm thickness. Ammonium chloride is used as electrolyte. The solution of ammonium chloride drops are made to fall between the electrodes at 30seconds interval. The voltage corresponding to 50 drops is noted and the corresponding numerical value of voltage is called as comparative tracking index (CTI). The voltage is applied in the range of 150-600V to the samples.

#### E. Dielectric Strength

Dielectric strength of sample is measured as per the standards IEC 60243-1 and ASTM D149. A sample of diameter 100mm and thickness 1mm is placed between the electrodes and the voltage applied is gradually increased at constant rate of 2kV/s till dielectric breakdown occurs. The voltage at which breakdown occurs is noted as dielectric breakdown voltage. Dielectric breakdown strength is calculated from the ratio of dielectric breakdown voltage to the thickness of the specimen.

## IV. RESULTS AND DISCUSSION

The electrical & mechanical parameters of the blend are measured as per given standards and comparison was done to obtain the suitable blend ratio. The characterization is done thorough Graphical method. As one of high voltage insulation

applications, EPDM applied to a polymer housing arrestor, cables, insulating sleeving and tapes, potting and encapsulating purposes[13-17].

In graphical method point of intersection gives approximate blend ratio for the specific application. Disadvantage of graphical method is identification of exact optimal blend from the various blend ratios. Optimal blend ratio is predicted by varying the number of parameters [17-20].

#### A. Results and Discussion on Dielectric Strength

The dielectric strength of different blend ratios are compared with tensile strength of different blend ratios and the comparison shows the impact of natural rubber in the blends. The Fig.1 shows the proportion of natural rubber is increased then the dielectric strength is also increased in the blends. The % decrease in dielectric strength is given as 50% of EPDM =  $(39.1-29.3) / 39.1 \times 100 \% = 25.06$ . The % increase in tensile strength is given as 50% of EPDM =  $(4.58-2.25) / 2.25 \times 100 \% = 103.5$ .

From the Fig.1, 50:50 blend ratio of NR/ EPDM is the best composition for the specific application and it is obtained by intersection of the curves. For above equations 50:50 blend ratio is reduced by 25% and tensile strength is improved by 103%. In Fig.2 the relationship between dielectric strength and percentage elongation at break are plotted. If the content of EPDM increases then the dielectric strength decreases, with increase in % EB.

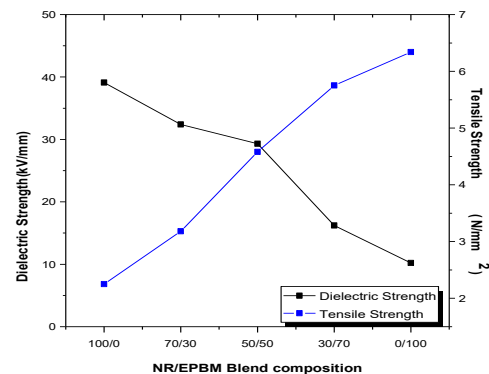


Fig. 1. Effect of Blend Composition on Dielectric Strength and Tensile Strength.


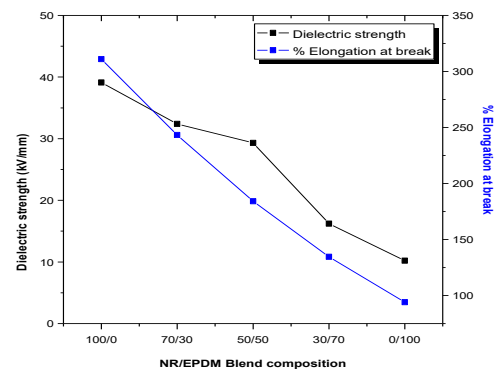



Fig. 2. Effect of Blend Composition on Dielectric Strength and % EB.

**B. Results and Discussion on Arc Resistance**

In Fig.3 the effect of blend composition on arc resistance and tensile strength is shown. EPDM is hydro carbon in nature, it increases the resistance towards electric arc when EPDM content is low [4]. The % decrease in arc resistance is given as 50% of EPDM =  $(612-375) / 612 \times 100 \% = 38.7$ . From the above calculations, arc resistance for 50:50 blend of NR/EPDM is decreased by 39% and tensile strength is increased by 103%. The intersection point gives better dielectric strength and tensile strength.

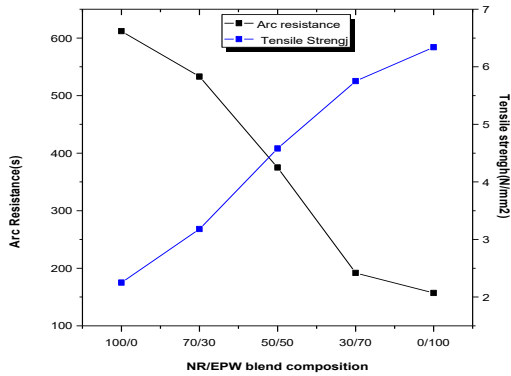

**Fig. 3. Effect of Blend Composition on Arc Resistance and Tensile Strength.**

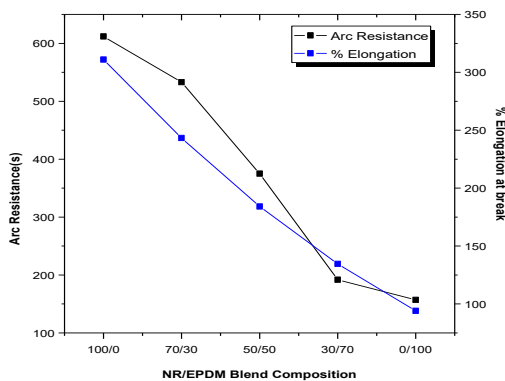


**Fig. 4. Effect of Blend Composition on Arc Resistance and %EB.**


The Fig.4 shows the effect of blend composition on arc resistance and % EB. The increasing EPDM content decreases the % EB and increases the arc resistance.

**C. Results and Discussion on Volume and Surface Resistivity**


The Fig.5 and Fig.6 show the effect of blend composition on volume and surface resistivity with respect to tensile strength. If NR content is increased, it increases the volume and surface resistivity of the material. It is obtain clearly above 70 weight percentage of NR in the blend. Tensile strength is decreased when the NR content is increased in the blend. 50:50 blend ratio of NR & EPDM gives higher volume and surface resistivity.

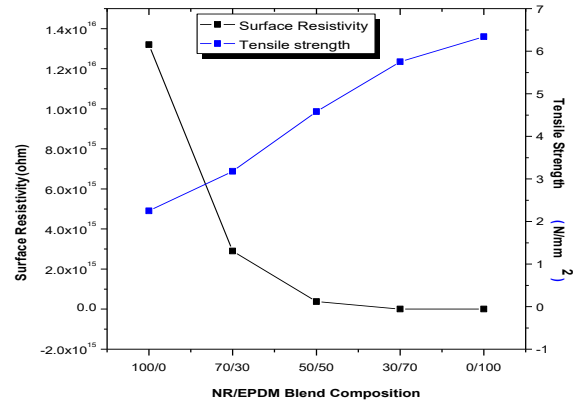

**Fig. 5. Effect of Blend Composition on Surface Resistivity and Tensile Strength.**

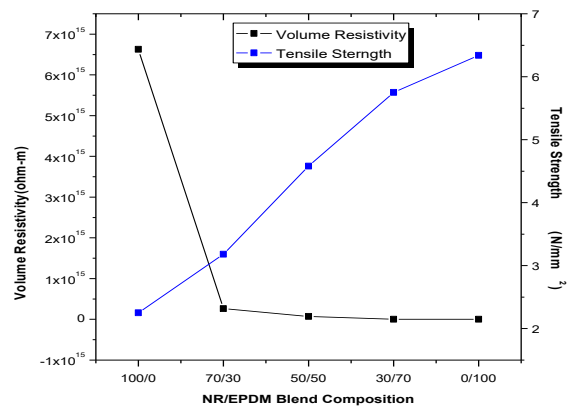

**Fig. 6. Effect of Blend Composition on Volume Resistivity and Tensile Strength.**

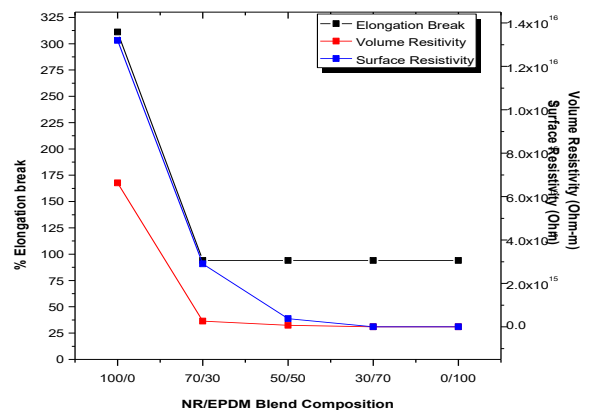


**Fig. 7. Effect of Blend Composition on Volume Resistivity and Tensile Strength.**

From the Fig.7, the decreasing content of EPDM decreases % EB. The surface & volume increases with decreasing of EPDM content.

**D. Results and Discussion on Comparative Tracking Index**

From Fig.8, tensile strength increases with increasing EPDM content. The values of CTI are obtained from the figure 8. If the CTI increases due to increasing proportion of NR. The intersection point gives

optimal blend. The % decrease in CTI is given by 50% of EPDM =  $(551-490) / 551 \times 100 \% = 10$ . From the above calculation, the CTI for 50:50 NR and EPDM blends is reduced by 10% and the tensile strength of the blend is improved by 103%.

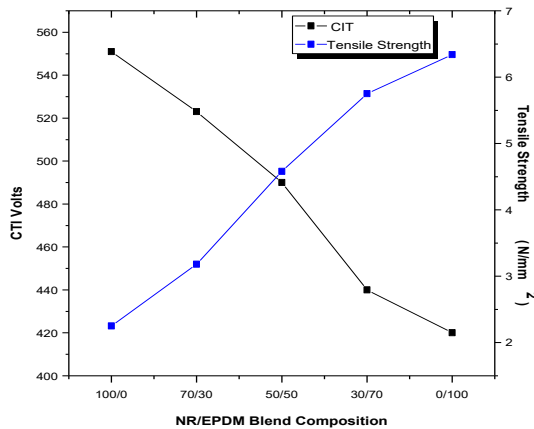

**Fig. 8. Effect of Blend Composition on Comparative Tracking Index and Tensile Strength.**

### V. CONCLUSION

The mechanical properties are increased by increasing EPDM content. NR/EPDM composition gives better mechanical strength and has less effect on electrical properties. The electrical properties are increased by increasing NR content in the blend composition. Adding of EPDM to NR increases the mechanical properties by 103%. The 50:50 blend ratios of NR and EPDM gives better electrical and mechanical characteristics using graphical methods. The intersection point gives approximate optimal solution. The changes in insulation characteristics of 50:50 blend ratio of NR/ EPDM by taking reference from 100% NR

- The tensile strength is increased by 103.5%.
- The dielectric strength is reduced by 25%
- The arc resistance is reduced by 39%.
- The comparative tracking index is reduced by 10%.

### ACKNOWLEDGMENT

The authors would like to thank the Management, Director, Principal, Head of EEE Department, High Voltage Program Coordinator and EEE Department Colleagues of National Engineering College for permitting us to carry out this work and for providing suggestions and guidance for the successful completion.

### REFERENCES

1. R.Deepalaxmi, M.Balaji and V.Rajini,(2013), "Particle swarm optimization based selection of Optimal polymeric blend", IEEE Transactions on Dielectrics and Electrical Insulation Vol. 20, No. 3, pp. 922-930.
2. K. S. Suh, S. K. Park, C. H. Lee, S. W. Kim and S. O. Han, "Space charge distributions in EPDM compounds," in IEEE Transactions on Dielectrics and Electrical Insulation, vol. 4, no. 6, pp. 725-731, Dec. 1997.
3. W. Arayaprane and G.L. Rempel,(2007), "Properties of NR/EPDM Blends with or without Methyl Methacrylate-Butadiene-Styrene

- (MBS) as Compatibilizer", International journal of Materials Structural Reliability, Vol.5, No.1, pp.1-12.
4. R.RajaPrabhu, S.Usa and K.Udhyakumar, "Electrical Insulation Characteristics of Silicone and EPDM blends", IEEE transaction on Dielectrics and Electrical insulation, Vol.14,No.5, pp. 1207-1214, 2007.
5. P.D. Blackmore, D. Birtwhistle, G.A. Cash and G.A. George, (1998 ), "Condition assessment of EPDM Composite insulators using FTIR Spectroscopy", IEEE transaction on Dielectrics and Electrical insulation , Vol. 6, No. 5, pp.132-141.
6. M. Ehsani , H. Borsi , E. Gockenbach ,G. R. Bakhshandeh I, J. Morshedian I, N. Abed ( 2004 ), "Study of Electrical, Dynamic Mechanical and Surface Properties of Silicone-EPDM Blends" International Conference on Solid Dielectrics, Toi, louse, France.
7. R. Eberhart and J. Kennedy, (1995), "A new optimizer using particle swarm theory", IEEE 6th International. Symposia. Micro Machine and Human Science", Japan, pp. 39-43.
8. Ioan,Cristian,Trelea,(2003), "The particle swarm optimization algorithm: convergence analysis and parameter selection", Information Processing Letters 85 Elsevier Science, page no: 317-325.
9. V.P. Sakhivel, R. Bhuvanewari and S. Subramanian,( 2010), "An Improved Particle Swarm Optimization for Induction Motor Parameter Determination", International Journal of Computer Applications., Vol. 1, No. 2, pp. 62-67.
10. C. Ou and W. Lin, (2006), "Comparison between PSO and GA for Parameters Optimization of PID Controller", IEEE International Conference on Automation, Luoyang, China, pp. 2471-2475.
11. M. Brown, "Compounding of ethylene-propylene polymers for electrical applications," in IEEE Electrical Insulation Magazine, vol. 10, no. 1, pp. 16-22, Jan.-Feb. 1994.
12. R. R. Prabu, S. Usa, K. Udayakumar, M. A. Khan and S. S. M. A. Majeed, "Electrical Insulation Characteristics of Silicone and EPDM Polymeric Blends. I," in IEEE Transactions on Dielectrics and Electrical Insulation, vol. 14, no. 5, pp. 1207-1214, October 2007.
13. Y. Kurata, "Evaluation of EPDM rubber for high voltage insulators", IEEE. Conf. Electr. Insul. Dielectr. Phenomena (CEIDP), pp. 471-474, 1995.
14. J. E. Davis, D. E. W. Rees, "Silicone Rubbers, Their Present Place in Electrical Insulation", Proc. IEE, vol. 112, pp. 1607-1613, 1965.
15. M. Ehsani, H. Borsi, E. Gockenbach, G. R. Bakhshandeh, J. Morshedian and N. Abedi, "Study of electrical, dynamic mechanical and surface properties of silicone-EPDM lents," Proceedings of the 2004 IEEE International Conference on Solid Dielectrics, 2004. ICSD 2004., Toulouse, France, 2004, pp. 431-434, Vol.1.
16. M. Ehsani, H. Borsi, E. Gockenbach, G. R. Bakhshandeh and J. Morshedian, "Improvement of electrical, mechanical and surface properties of silicone insulators," The 17th Annual Meeting of the IEEE Lasers and Electro-Optics Society, 2004. LEOS 2004., Boulder, CO, USA, 2004, pp. 623-626.
17. R. R. Prabu, S. Usa, K. Udayakumar, M. A. Khan and S. S. M. A. Majeed, "Theoretical correlations amongst electrical and mechanical characteristics of polymeric housing materials for outdoor insulators," in IEEE Transactions on Dielectrics and Electrical Insulation, vol. 15, no. 3, pp. 771-782, June 2008.
18. G. A. Vignaux Dimensional Analysis in Data Modelling Kluwer Academic Publishers 1992.
19. E. Q. Isaacson M. Q. Isaacson Dimensional Methods in Engineering and Physics Edward Arnold 1975.

### AUTHORS PROFILE



**Kannayeram G** is working as Assistant Professor (Senior Grade) in Electrical and Electronics Engineering of National Engineering College K.R.Nagar, Kovilpatti. He pursued his B.E degree at National Engineering College, in the year 1998 and M.E. (Power Systems) at Jadavpur University, Kolkata, India in the year 2007. He received his Ph.D degree (Electrical Engineering) at Anna University, Chennai in the year 2018. He is active member of Institute of Engineers (I) and Indian Society for Technical Education. He has published more than 20 papers in national and international conferences and Four in international journal.

He has 19 years of teaching and 2 years of industry experience and his interested research areas are FACTS controller tuning, Power system stability, High voltage Engineering and Smart Grids.



**Megala V** received her B.E degree in Electrical and Electronics Engineering from Bharathiyar University, India in 2002 and M.E Degree in Applied Electronics from Government College of Technology, India in 2004. She has 13 years of teaching experience in Engineering College. She is currently working in Electrical and Electronics

Engineering Department, SRM Institute of Science and Technology, Chennai, India. She is a life member of ISTE. Her current research interests include corona discharges, Electromagnetic Interference and Applications of Nano-technology.



**Prakash NB** received B.E Degree in Electrical and Electronics Engineering Department and M.E (Applied Electronics) Degree in Electronics and Communication Engineering Department from Madurai Kamaraj University, Madurai by the year 2000 and 2002. He received his Ph.D Degree under the Faculty of Information and Communication

Engineering (Research area: Medical Image Processing) from Anna University, Chennai by June 2018. He has more than 17 years of teaching experience and has published many papers in the reputed national and international journals and conferences. His area of specialization includes medical image processing, pollution performance analysis in insulators and bushings, embedded systems and power system engineering. He is also an approved research supervisor under the faculty of Information and Communication Engineering of Anna University, Chennai bearing AU New Reference Number: 3340036 (S.No.763). He is also a peer reviewer in Elsevier, Springer, SCOPUS and SCI indexed international journals.



**Muniraj R** received B.E Degree in Electrical and Electronics Engineering Department from Madurai Kamaraj University, Madurai by the year 2004 and M.E (Control and Instrumentation) Degree in Electrical and Electronics Engineering Department from Anna University, Chennai by June 2006. He received his Ph.D

Degree under the Faculty of Electrical Engineering (Research area: Control and Instrumentation Engineering) from Anna University, Chennai by April 2019. He has more than 13 years of teaching experience and has published many papers in the reputed national and international journals and conferences. His area of specialization includes PID Controller tuning, Control and Automation systems, power system engineering. Intelligent Control Algorithms and Instrumentation Engineering.



**Sundar B** received B.E Degree in Electrical and Electronics Engineering Department and M.E High Voltage Engineering Department Degree from National Engineering College, affiliated under Anna University, Chennai by the year 2011 and 2014. He has an industrial experience of more than five years and has worked in coal handling, Dozer maintenance and coal yard

management at Tuticorin Thermal Power Station, Tuticorin. He has published national and international conference during his tenure of studies. His area of interest is insulators, polymeric blending.