

Impact Resistance of Ternary Concrete Using Scba and Silica Fume as Partial Substitute of Cement in Concrete

T. Santhosh kumar, Balaji, kvgd, P.Narasimha Murthy

ABSTRACT: Concrete structures inevitably encounter dynamic loads throughout the planning lifetime of structure. Impact resistance is necessary factor for evaluate the dynamic concert of concrete. To fulfill the necessities of strength and toughness properties of concrete we have a tendency to use the industrial by-products like coal bottom ash, silica fume, metakaolin, etc., as supplementary building material. During this research work the experimental investigation was investigation to gauge the Impact resistance of TBASF concrete mix by cement is partially substitute with silica fume 10% and also the SCBA 0%, 5%, 10%, 15%, 20% and 25%. The Impact resistance of TBASF concrete mix is additionally compared with normal concrete. This study is additionally conducting elaborated investigation of TBASF concrete for mineralogical properties by using Optical microscope and XRD keeping Impact resistance in view. The maximum percentage of SCBA is obtained at 15% replacement of cement.

Keywords: Impact test, SCBA, Silica fume, Optical microscope, XRD.

I. INTRODUCTION:

At present, concrete industry is cursed with the insufficiency of the aggregates and atmosphere pollution from cement production. The cement industry contains an important contribution in global warming on account of combustion of fuel within the cement kiln and also the electricity used for grinding the clinker, emit great amount of CO₂. Cement industry is liable for regarding 5% of world CO₂ emissions. Therefore, it becomes terribly essential and additional important to try to find the substitute for each cement in addition natural aggregates. Aside from it, the continual growth of agro and industrial waste is that the principle reason for several environmental issues and burdens which may be reduced. Groundnut shell from Groundnut, rice husk from Paddy, wheat husk and wheat straw and from Wheat and bagasse from Sugarcane are the wastes of agriculture. In these 3 components cement is that the most significant constituent of concrete. Throughout the cement production one among the greenhouse gases known as greenhouse emission is emitted, which can cause global warming. So as to decrease this global warming a number of the agro wastes are utilized in construction materials. Because of the flexibility of concrete many waste materials realize their approach within the cement replacement and aggregate within the concrete production.

Revised Manuscript Received on July 05, 2019

T. Santhosh kumar, Assistant Professor & Research Scholar, Department of Civil Engineering, GITAM (Deemed to be University)

Dr. Balaji, kvgd, Professor, Department of Civil Engineering, GITAM (Deemed to be University)

P.Narasimha Murthy, PG student, Department of Civil Engineering, GITAM (Deemed to be University)

Flyash enhanced industrial additionally as technical feasibility directed many researchers to utilize alternative waste and ashes in concrete. These resulted within the utilization of silica fume, rock dust, sludge, SCBA, siliceous stone powder, egg shell powder, and alternative such materials in concrete. The bagasse ash utilization in concrete effectively serves to conserve the natural resources and lowers the cement consumption. To alleviate the rising price of materials particularly cement for the assembly of concrete, maximized waste utilization is needed through utilizing sugarcane bagasse ash.

II. EXPERIMENTAL INVESTIGATION MATERIALS:

CEMENT: Ultra-tech cement of OPC 53 grade, accordance with BIS: 12269-1987 was used.

FINE AGGREGATE:

Fine aggregate regarding to Zone-2, accordance with BIS: 2386-1963 was used.

COARSE AGGREGATE:

Coarse aggregate of size 20mm, accordance with BIS: 2386-1963 was used.

SUGARCANE BAGASSE ASH:

SCBA collect from NCS sugar limited, Vizianagaram district, Andhra Pradesh, India, was used as mineral admixture.

SILICA FUME:

Commercially accessible densified silica fume from Vizag chemicals private limited, Visakhapatnam district, Andhra Pradesh, India was used as mineral admixture.

MIX PROPORTION:

During this work, W/C ratio of 0.45 was used for M30 grade concrete. Silica fume of 10% and SCBA of 0%, 5%, 10%, 15%, 20% and 25% were partially replaced by cement in concrete.

MIXING PROCESS AND SAMPLE MOLDING:

The blending process was choosing to take up by trial and error technique. Within the starting cement, silica fume and SCBA were mixed completely till uniform colour and so coarse aggregate and fine aggregate was added supplementary to cement mix together by adding water and mix it for 10 minutes.

Impact Resistance of Ternary Concrete using Scba and Silica Fume as Partial Substitute of Cement in Concrete

Every mixture of newly TBASF concrete mix was then cast into cylinders (150 x 300mm), cubes (100 x 100 x 100mm) and prisms (500 x 100 x 100mm) that were utilized in the splitting tensile, compressive and flexural tests respectively. Cylindrical discs (96 x 50mm) be cut as of the cylindrical concrete samples be used for the impact test.

For drop weight impact test, count the blows until the concrete sample completely failure. The 13.5 kg hammer was dropped constantly at a height of 413 mm on top of a concrete sample that was located at the bottom shield of the impact testing machine.

III. IMPACT TEST:

The impact resistance of the concrete samples ascertain in a manner in accordance with to the process within the ACI committee 544.2R-89. The deliberations are specified within the subsequent section.

IV. RESULTS AND DISCUSSION

RESULTS:

The average compressive strength, split tensile strength, flexural strength and impact strength results be graphically shown in fig 2, fig 3, fig 4 and fig 5.

Compressive strength:

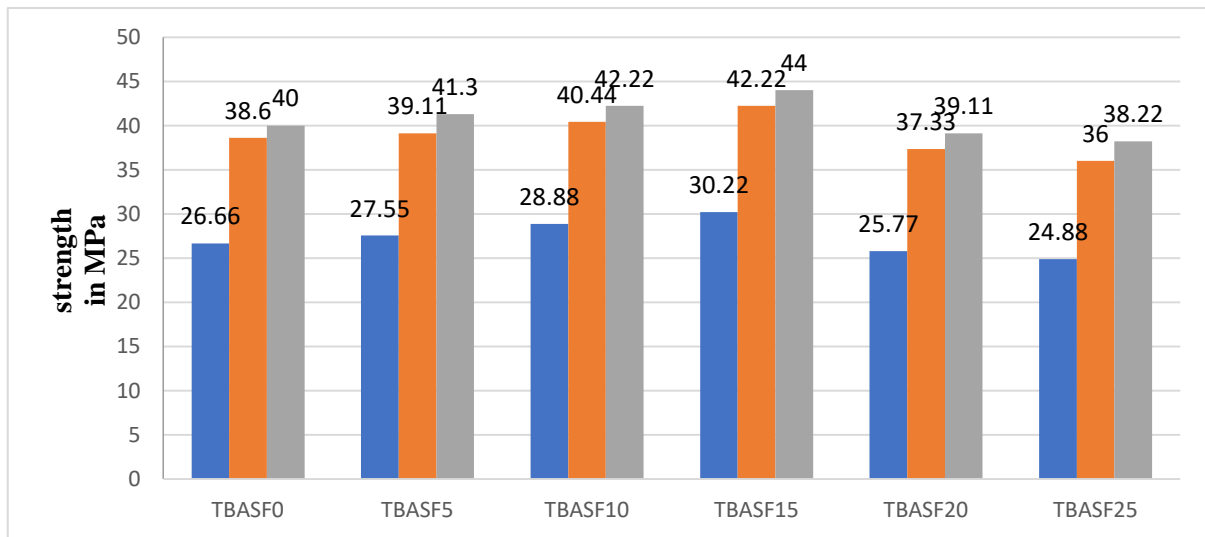


Fig 1: compressive strength of TBASF mix

Flexural strength:

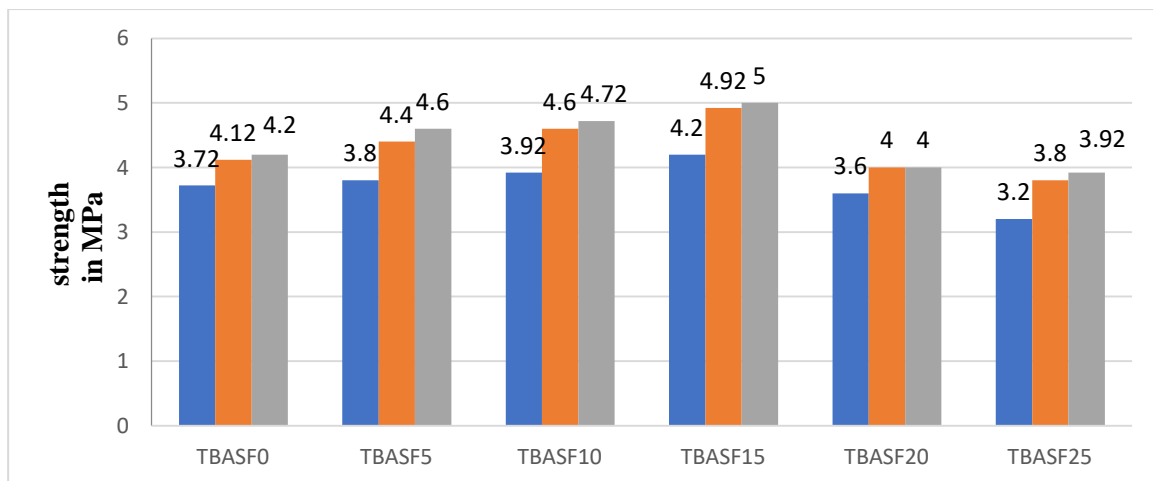


Fig 2: flexural strength of TBASF mix

Split tensile strength:

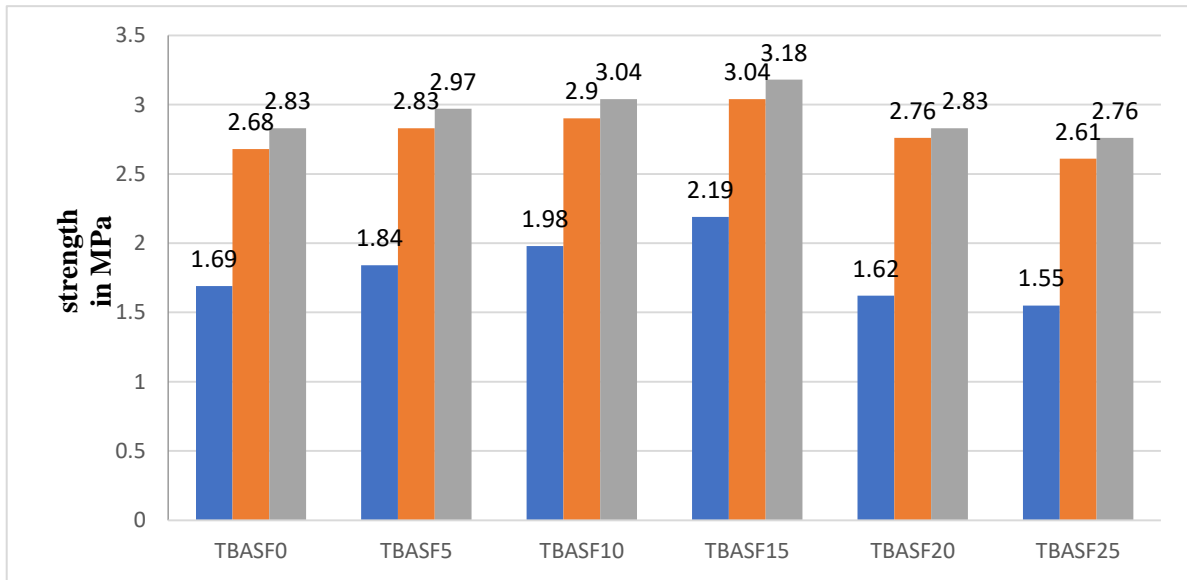


Fig 3: split tensile strength of TBASF mix

V. IMPACT TEST:

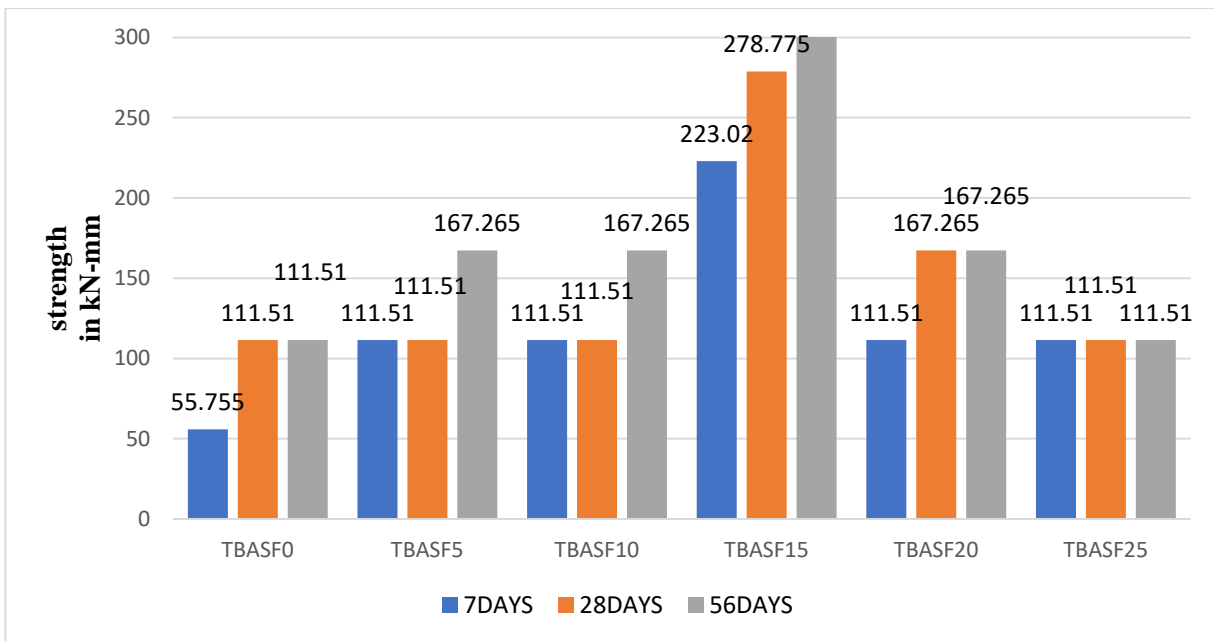


Fig 4: Impact strength of TBASF mix

VI. Optical microscopic analysis:

VIII. CONCLUSIONS:

From the test result of the experimental investigations the following observations were drawn for optimum concrete mix TBASF15:

- TBASF15 concrete mix showed much higher compressive strength when compared TBASF0 by 11.83%.
- TBASF15 concrete mix showed significantly higher flexural strength when compared TBASF0 by 14.4%.
- TBASF15 concrete mix showed significantly higher split tensile strength when compared TBASF0 by 18.8%.
- TBASF15 concrete mix showed the energy absorption significantly higher when compared TBASF0.
- TBASF15 concrete mix showed the good bonding between aggregates and cement paste and SiO_2 was the only component identified as pure silica fume by observing through optical microscope and XRD.
- The utilization of agriculture waste like SCBA reduce the utilization of cement thus reduces the possible greenhouse emission. In addition, this would help in reduction of disposal of bagasse and health problems near the sugar manufacturing industry.

REFERENCES:

1. Farshad Ameri, Nasollah Bahramji, Seyed Alireza Zareei, (June 2018), "Microscope structure, strength and Durability of ecofriendly concretes containing sugarcane bagasse ash", "Concrete and Building Materials" Vol 184, PP 258-268.
2. K.Ganesan, K.Raj Gopal and K.Thangavel, (Jan 2007), "Evaluation of bagasse ash as supplementary cementitious material", "Cement and concrete composites", Vol 29, PP 515-524.
3. Madhurima Battacharaya, Venkatanarayana Harish, (Aug 2018), "An integrated approach for studying the hydration of portland cement systems containing silica fume", "Concrete and Building Materials", Vol 184, PP 1179-1192.
4. A. Muller, H.R. Roman, and P.J.P. Gleize, (Jan 2003), "Microstructural investigation of a silica fume-cement-lime mortar", "Cement and concrete composites", Vol 25, PP 171-175.
5. Niel Thaulow, Sadananda Sahu and Sidney Diamond, (Jan 2004), "Reaction products of densified silica fume agglomerates in concrete", "Cement and concrete Research", Vol 34, PP 1625-1632.
6. Medhat H. Shehata and Michael D.A. Thomas, (Sep 2002), "Use of ternary blends containing silica fume and fly ash to suppress expansion due to alkali-silica reaction in concrete", "Cement and concrete Research", Vol 32, PP 341-349.
7. Tahir C, Ozgur Eren, and Khaled Marar, (Jan 2001), "Relationship between impact energy and compression toughness energy of high-strength fiber-reinforced concrete", "Materials Letters", Vol 47, PP 297-304.
8. A S Santhi, G Murali, and G Mohan Ganesh, (July 2014), "Empirical relationship between the impact energy and compressive strength for fiber reinforced concrete", "Journal of Scientific and Industrial Research", Vol 73, PP 469-473.
9. K. Sharma, Ravi, Sandeep Chaudhary and Trilok Gupta, (Sept 2015), "Impact resistance of concrete containing waste rubber fiber and silica fume", "International Journal of Impact Engineering", Vol 83, pages 76-87.
10. Mahmoud nil and V. Afroyghsabet, (April 2010), "Combined effect of silica fume and steel fibers on the impact resistance and mechanical properties of concrete", "International Journal of Impact Engineering", Vol 337, PP 879-886.