

Experimental and Simulation Analysis of Thermal Vertical Directional Solidification Grown Ni Doped Bulk GASB



Sushanta K. Kamilla, Farida A. Ali

Abstract: Due to high hole mobility, p-GaSb is an attractive III-V semiconducting material for high performance p-channel metal-oxide semiconductor field effect transistor (p-MOSFET). For that growth of undoped and Ni doped GaSb bulk crystal by thermal vertical directional solidification has been reported in this paper. Both structural and electrical characterization was carried out for both the samples. X-ray diffraction (XRD) analysis confirms that the compound grown is polycrystalline in nature which has been supported by scanning electron microscope (SEM) image. The carrier charge density and mobility were measured by Hall Effect measurement in the temperature range 78K and 300K. From the sign of Hall co-efficient the grown material was confirmed p-type. The Current-Voltage (I-V) characteristic was studied for the sample i.e. experimentally grown and also simulated using TCAD at 78K and 300K. The temperature dependence of the hole mobility were also investigated by TCAD tool using the models Auger recombination, Shockley-Read-Hall (SRH) and Band-gap narrowing (BGN). Comparison of experimental and simulated temperature dependencies of mobility shows good agreement, while their difference at some points suggests the contribution of compensating impurities.

Keywords: -I-V study, p-GaSb, SILVACO, Thermal Vertical Directional Solidification (TVDS).

I. INTRODUCTION

Gallium Antimonide (GaSb) is an attractive candidate for future high performance III-V p-channel metal-oxide semiconductor field effect transistor (p-MOSFET) because of its high hole mobility (~1000 cm²/V. Sec) which is higher than those of most of the other III-V semiconductors. Apart from that it is used as high speed electronic devices due to its narrow and direct band gap of 0.7 eV at 300K (Dutta, Bhat, & Kumar, 1997),(Ancona, Bennett, & Boos, 2010),(Yuan et al., 2013)(Communication & Communication, 2008),(Ali, Pattnaik, & Kamilla, 2011).

Revised Manuscript Received on November 30, 2019.

* Correspondence Author

Sushanta K. Kamilla*, Department of Physics, Faculty of Engineering, Sikhsha 'O' Anusandhan University, Bhubaneswar, Odisha, India. Email: sushantakamilla@soa.ac.in

Farida A. Ali, Department of Electronics & communication, Faculty of Engineering, Sikhsha 'O' Anusandhan University, Bhubaneswar, Odisha, India

© The Authors. Published by Blue Eyes Intelligence Engineering and Sciences Publication (BEIESP). This is an [open access](http://creativecommons.org/licenses/by-nc-nd/4.0/) article under the CC-BY-NC-ND license <http://creativecommons.org/licenses/by-nc-nd/4.0/>

Also, the trap neutral level (E₀) of GaSb is located 0.1eV above the valence band, which is helpful in making Ohmic contacts to p-type GaSb for the p-MOSFET applications. These properties are advantageous for choosing GaSb and GaSb-based alloys also as promising channel materials in p-MOSFETs (Brongersma et al., 2010). Thus, development of p-MOSFETs using new material sets is an important goal to provide further scaling of CMOS circuits. Intense research activity also has been going on transition metals doped GaSb for spintronic device applications i.e. combination of both magnetic as well as semiconducting properties(Šestáková & Štěpánek, 1995), (Ganesan, Rao, Bhat, & Bhat, 2011), (Akiba et al., 2000), (Hidalgo, Méndez, Piqueras, Plaza, & Diéguez, 1999), (Karar & Basu, 1999). So far there are limited numbers of literatures present on the study of Ni in GaSb (S. K. Kamilla, Ali, Samantaray, Basu, & Mohanty, 2014). For both spintronic and high-speed device applications Ni is essential due to its strong ferromagnetic property. Growth of bulk Ga_{1-x}Ni_xSb with different Ni concentrations by vertical Bridgman method and then its detail electrical and magnetic characterization at 78K and 300K has been reported in one of our papers (S. K. Kamilla, Hazra, Samantaray, & Basu, 2011).

In this paper we report on large grain polycrystals of Ni doped GaSb was grown by thermal vertical directional solidification designed and developed in our laboratory. The structural characterization was done by X-ray diffraction (XRD) analysis and surface morphology was analyzed by using scanning electron microscope (SEM). The resistivity of the sample was determined by van der Pauw technique. Hall measurement was performed to determine the type of charge carriers, the carrier concentration and mobility. Undoped GaSb crystal was also grown using the same growth technique and characterized for comparison, with Ni doped GaSb. Later on simulation was carried out to study the ideal behavior of the undoped and Ni doped GaSb material so that comparison can be made with that of our grown materials. SILVACO-TCAD the simulation software which is the state-of-the-art available for academic purpose has been used for this study. This software tool is comprised of several modules designed to generate the geometry, doping, mesh, and perform the simulation by finite element method.

II. GROWTH & SIMULATION

Using the thermal vertical directional solidification method two samples were grown. One is undoped GaSb for which the starting elements chosen are Gallium (5N) and Antimony (5N). For the second sample the starting elements chosen were Gallium (5N), Antimony (5N) and Nickel (4N) to grow Ni-doped GaSb. The starting elements for both the samples were taken from Johnson Matthey Co, USA. They were degreased by dipping in warm trichloroethylene, acetone and methanol and to remove the surface oxides. The starting elements were leached in dilute HCl solution with the help of ultrasonic vibrator (JULABO, Germany) followed by repeatedly washed with de-ionized water (10 MΩ) and then vacuum dried in an oven. They were then put into capsules high purity quartz ampoules and vacuum-sealed to a pressure of 8×10^{-4} Pa using a Hind high vacuum system model VS-65 (India) separately. The quartz capsules were then placed inside a horizontal resistively heated furnace and were kept at 850°C for 3 hours with constant stirring with the help of rotational motor and nicrome net for a homogeneous mixture for the synthesis. Both the synthesized charges were then taken out from the capsules and again put inside two new conical tip quartz ampoules with inner diameter of 0.8cm separately, followed by vacuum sealing to a pressure of 6×10^{-6} Torr. For growth the ampoule with synthesized material was then placed inside the vertical Bridgman furnace. Both undoped and Ni doped GaSb crystals were grown at the same growth conditions. The total process of maintaining the temperature profile of the vertical Bridgman growth technique to growing ingots from the synthesized charges has been well explained by us earlier (Sushanta K. Kamilla, Samantaray, & Basu, 2006). Then the ingots were taken out by breaking the ampoules without any sticking problem to the wall for further processing and characterizations. Ingots of nearly 4cm length and 0.8cm diameter were obtained as shown in Figure 1.

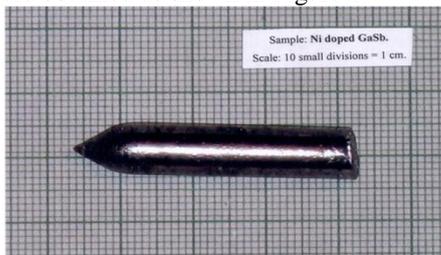


Fig. 1. Photograph of grown Ni doped GaSb ingot

Finally, the wafers were cut perpendicular to the axis of the ingots with a slow speed diamond saw cutter. The saw damages were removed by mechanical polishing followed by chemical polishing to obtain a clean and smooth surface. The polished wafers were then chemically cleaned by dilute HCl to remove the instable native oxide layers and then washed to remove the traces of the chemicals and were finally vacuum dried in oven. The appropriate etchant is prepared by mixing proper proportional combination of HNO_3 , HF and H_2O to reveal the grains and grain boundaries that can be observed by using scanning electron microscope (SEM). Formation of the grown material was verified by X-ray diffraction (XRD) analysis. The XRD pattern of the material was taken by Rigaku mini flex X-Ray Diffraction Analyzer system by using a $\text{CuK}\alpha_1 = 1.5405 \text{ \AA}$ radiation. Resistivity and Hall Effect measurements with van der Pauw configurations were conducted for all samples using the Hall Instrument

LAKESHORE 7504. The experiment was performed in the temperature range 78K–300K. The electrical properties were also obtained from the simulation analysis of Ni doped GaSb by SILVACO-TCAD software tool. The simulation results obtained were then used for making comparisons with that of the experimental data. For this reason, the size of simulation structure was taken of exact dimension (i.e. 5mm x 5mm) that corresponds to the experimental sample under test. Similarly, various material parameters at room temperature like doping type, doping level, carrier concentration etc. have been taken into consideration from experimental data. As the carrier concentration of the sample is about 10^{17} cm^{-3} and the electrical characterization has been studied under the influence of temperature variation therefore the choice of Auger recombination for simulation study was essentially vital. Similarly, the Shockley-Read-Hall (SRH) or trap related recombination is also dependent on material quality. Therefore, to study the ideal behavior of Ni doped GaSb, inclusion of these models to the simulated structure was necessary. Apart from these, model for band-gap narrowing (BGN model) is also essential to include since the band-gap variation is dependent on intrinsic concentration, which in turn depends on temperature (Sushanta K. Kamilla et al., 2006), (Stollwerck, 2000). Thus, these three models Auger recombination, Shockley-Read-Hall (SRH) and Band-gap narrowing (BGN) play an important role in this simulation for the electrical characterizations of the Ni doped GaSb structured sample. Finally to characterize the I-V analysis, a DC potential was applied and current at different temperatures ranging from 78K to 300K were calculated. Later the variation of hole mobility was found for the same range of temperature.

III. UNITS

The formation of Ni doped GaSb compound was confirmed by X-ray powder diffraction (XRD) technique. The typical XRD pattern of Ni doped GaSb is shown in Figure 2. The compounds were observed to be polycrystalline and zinc blend structure. The possible reasons for the polycrystallinity of the grown ingot might be due to (i) shape of the tip of the ampoule not appropriately fabricated for single nucleation (ii) unavoidable minimal mechanical vibration at the time of growth (iii) thermal convection. The lattice parameter of the cubic crystals was calculated and was found $a = 6.092 \text{ \AA}$ for Ni doped GaSb and $a = 6.097 \text{ \AA}$ for undoped GaSb ingot. The reported value of lattice constant for undoped sample is 6.095 \AA [JCPDS-070215]. The decrease in a value may be due to addition of Ni in the crystal lattice indirectly indicates inclusions of Ni in the GaSb lattice.

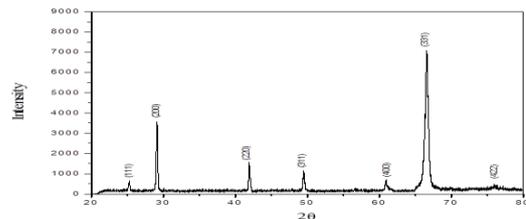


Fig. 2. Typical X – Ray diffraction pattern using Cu Kα radiation for Ni doped GaSb sample.

The surface morphology of polished wafer of grown Ni doped GaSb sample is shown in Figure 3. The clear demarcations of grain and grain boundaries of the polycrystalline sample are shown.

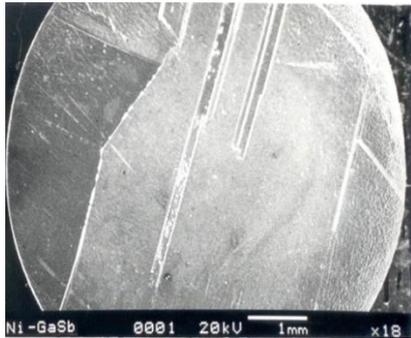


Figure 3. The photograph of polished wafer of grown Ni doped GaSb sample

The average grain size of the ingot is nearly 2.6 cm. Both Roy and Basu (Roy & Basu, 1988) and Harsy et.al (Hársy, Görög, Lendvai, & Koltai, 1981) have reported that the grain size strongly depends upon the ampoule diameter. The decrease in grain size with lower ampoule diameters was explained as due to the wall effect, whereas for large ampoule diameter non uniformity of heat conduction from the crystal to the melt interface results in decrease in grain size. The presence of dopant impurity Ni has also strong influence on the grain size of the ingot grown by vertical Bridgman method. Furthermore, the growth temperature may also be one of the reasons for the formation polycrystalline Ni doped GaSb sample i.e. the thermo mechanical stress occurring during the cooling condition. This suggests that observed morphology was probably due to the stress and the defects joined up to produce a higher number of grains and grain boundaries. Secondly, due to the incorporation of dopant atoms strain develops because of the difference in the atomic radius of the dopants and the host atoms.

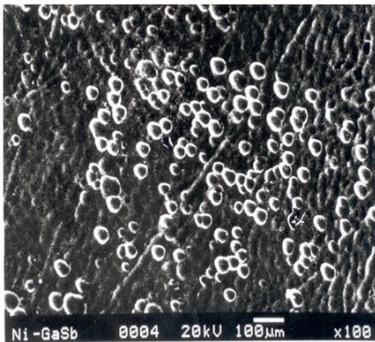


Figure 4. Cross sectional view of Ni doped GaSb sample showing the EPDs

The etched wafer of grown sample was analyzed by SEM and the average EPD was found to be $1.5 \times 10^9/m^2$. This suggests that probably due to stress and strain at the time of growth grains and grain boundaries were formed. The etch rate of an anisotropic etchant on zinc blende type materials are slowest and also the pits are triangular on [111] surface as observed in Figure 4.

I. 3.1 Electrical Characterizations of both experimental & simulated sample

The resistivity of the sample was determined by Van Der Pauw technique. The first step for preparing the sample was to make a proper ohmic contact by melting high purity

Indium metal dots on the corners of the rectangular sample and it was verified. Hall measurement was performed to determine the type of charge carriers, carrier concentration and mobility using the same configuration. The sample was found to be p-type as confirmed by the sign of Hall co-efficient and Hall co-efficient also decreases from $111.6 \text{ cm}^3/\text{C}$ to $25.3 \text{ cm}^3/\text{C}$ with the rise of temperature from 78K to 300K. The study of I-V characteristics of the experimental sample at 78K and 300K is found to be linear and passes through origin as shown in Figure 5(a). The simulated I-V characteristic was also studied for a similar rectangular sized Ni doped GaSb sample shown in Figure 5(b) at both 78K and 300K. The resistance of the simulated sample was found out from the slopes of the two curves. The result shows that at 78K i.e. at low temperature the charge carrier holes are not free for conduction thus the sample showing lower conductivity as compared to the experimental sample. For a higher temperature the hole concentration increases rapidly because the charge carriers are thermally excited into the conduction band and as a result the conductivity increases rapidly. At 78K and 300K the electrical parameters for both experimental and simulated samples of Ni doped GaSb have been summarized in Table 1. The results indicate that resistivity, mobility, while the hole concentration increases for both the samples.

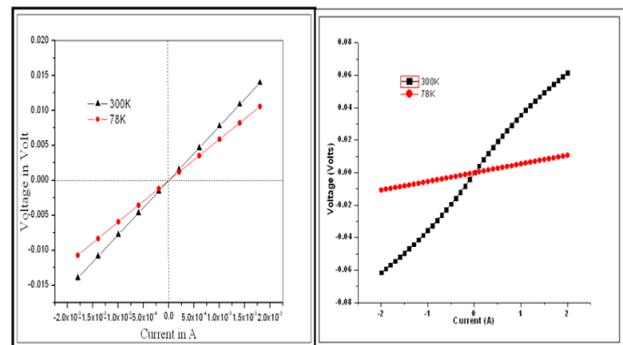


Figure 5. Current (I) - voltage (V) characteristics for the Indium ohmic contact to Ni doped GaSb at 300 K and 78K (a) Experimental (b) Simulation results

Table 1. Electrical parameters at 300 K and 78K

Samples	Resistivity (Ωcm)		hole concentrations (cm^{-3})		hole mobility ($\text{cm}^2/\text{V}\cdot\text{sec}$)	
	300K	78K	300K	78K	300K	78K
Ni doped GaSb	0.05	0.09	2.5×10^{17}	5.6×10^{16}	434	1083
Simulated Ni doped GaSb	0.032	0.005	5.3×10^{18}	2.72×10^{15}	395	1386

Figure 6(a) shows a variation of mobility in the temperature range 78 K -300 K for the experimental sample. The mobility of the hole does not show any significant change between 78K and 240K and after that the mobility decreases with temperature. The reason for this behavior can be attributed to the fact that as temperature increases, phonon scattering starts increasing and it reduces the drift of the carriers and thus the mobility. At 300K the hole mobility of Ni doped GaSb is $434 \text{ cm}^2/\text{V}\cdot\text{sec}$.

whereas the hole mobility for the simulated Ni doped sample is found to be 395 cm²/V.sec. The simulated result of hole mobility of undoped bulk GaSb was reported as 458 cm²/V.sec earlier. This variation in simulated undoped and doped GaSb indicates that the hole mobility decreases due to the impurity scattering effect of Ni concentration. Here we have observed the highest mobility of 1096 cm²/V.sec at 93K for the experimental sample of Ni doped GaSb. Our experimental observation agrees with the reported results by Stollwerck. (Stollwerck, 2000).

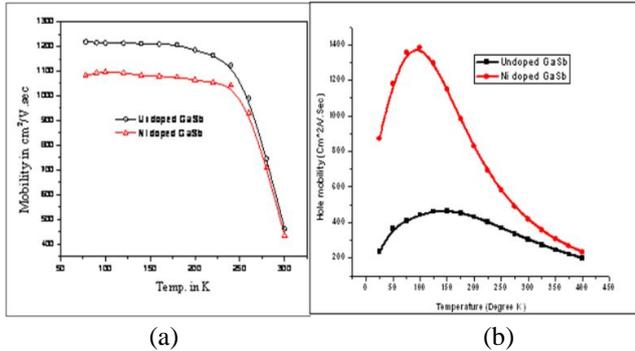


Figure 6. Variation of mobility with temperature of Undoped and Ni doped GaSb at 300 K and 78K(a) Experimental (b) Simulation results.

Whereas Figure 6 (b) shows a variation of mobility in the temperature range 78 K -300 K for the simulated one. In general, the undoped GaSb samples show higher peak mobility than the doped GaSb samples due to the compensation mechanism present (Stollwerck, 2000). But our simulated Ni doped sample, though it shows the similar trend but shows higher mobility than that of undoped sample, this is because we have not included any model to take care the compensation mechanism. Therefore, the sample shows a mobility of 1371 cm²/V.sec at 93K which is much higher than our experimental mobility.

IV. CONCLUSION

From the presented study the thermal vertical directional solidification growth technique of both undoped and Ni doped GaSb have been analyze. The presence of dopant impurity Ni has strong influence on the polycrystallinity nature and grain size of the ingot grown by thermal vertical directional solidification. This has been confirmed from the XRD study and the photograph of etched wafer from the grown ingot respectively. Later on, both experimentally and by simulation electrical characterization was done considering Nickel as a dopant in bulk GaSb for 78K and 300K. Nickel behaves as an acceptor impurity and also reduces the hole mobility of GaSb. Experimental and simulation results were compared for the temperature dependencies of mobility. The results show good agreement, while the differences may be due to the scattering and compensation mechanisms.

ACKNOWLEDGMENT

The corresponding authors, Dr. S. K. Kamilla is thankful to Indian Institute of Technology (IIT), Kharagpur, India for doing laboratory and other facility during his research time.

REFERENCES

1. Akiba, N., Chiba, D., Nakata, K., Matsukura, F., Ohno, Y., & Ohno, H. (2000). Spin-dependent scattering in semiconducting ferromagnetic (Ga,Mn)As trilayer structures. *Journal of Applied Physics*. <https://doi.org/10.1063/1.372730>. Ali, F. A., Pattnaik, P., & Kamilla, S. K. (2011).
2. Characterisation of bulk GaSb using TCAD. *TechSym 2011 - Proceedings of the 2011 IEEE Students' Technology Symposium*. <https://doi.org/10.1109/TECHSYM.2011.5783847>
3. Ancona, M. G., Bennett, B. R., & Boos, J. B. (2010). Scaling projections for Sb-based p-channel FETs. *Solid-State Electronics*. <https://doi.org/10.1016/j.sse.2010.06.022>
4. Brongersma, M. L., Shalaev, V. M., Brongersma, M. L., Fleischmann, M., Hendra, P. J., McQuillan, A. J., ... Engheta, N. (2010). Applied physics. The case for plasmonics. *Science (New York, N.Y.)*. <https://doi.org/10.1126/science.1186905>
5. Communication, R., & Communication, R. (2008). *Chinese Physics B. Ultramicroscopy*. <https://doi.org/10.1088/1674-1056/18/7/053>
6. Dutta, P. S., Bhat, H. L., & Kumar, V. (1997). The physics and technology of gallium antimonide: An emerging optoelectronic material. *Journal of Applied Physics*. <https://doi.org/10.1063/1.365356>
7. Ganesan, K., Rao, S. S., Bhat, S. V., & Bhat, H. L. (2011). Electron paramagnetic resonance studies on Mn doped GaSb. *Journal of Applied Physics*. <https://doi.org/10.1063/1.3543983>
8. Hársy, M., Görög, T., Lendvai, E., & Koltai, F. (1981). Direct synthesis and crystallization of GaSb. *Journal of Crystal Growth*. [https://doi.org/10.1016/0022-0248\(81\)90070-1](https://doi.org/10.1016/0022-0248(81)90070-1)
9. Hidalgo, P., Méndez, B., Piqueras, J., Plaza, J., & Diéguez, E. (1999). Scanning tunneling spectroscopy study of erbium doped GaSb crystals. *Journal of Applied Physics*. <https://doi.org/10.1063/1.370910>
10. Kamilla, S. K., Ali, F. A., Samantaray, B. K., Basu, S., & Mohanty, M. (2014). Crystal growth of bulk Ga_{1-x}Ni_xSb ternary alloy and its characterization between 78 K to 300 K. *Advanced Science Letters*. <https://doi.org/10.1166/asl.2014.5437>
11. Kamilla, S. K., Hazra, S. K., Samantaray, B. K., & Basu, S. (2011). Electrical and magneto resistance studies of bulk Ga_{1-x}Ni_xSb ternary alloys. *Solid State Sciences*. <https://doi.org/10.1016/j.solidstatesciences.2010.11.020>
12. Kamilla, Sushanta K., Samantaray, B. K., & Basu, S. (2006). Effect of Ni concentrations on the microhardness of GaNiSb ternary alloys. *Journal of Alloys and Compounds*. <https://doi.org/10.1016/j.jallcom.2005.06.074>
13. Karar, N., & Basu, S. (1999). Synthesis and growth of Ga_{1-x}Fe_xSb, a new III-V diluted magnetic semiconductor. *Materials Science and Engineering B: Solid-State Materials for Advanced Technology*. [https://doi.org/10.1016/S0921-5107\(99\)00018-5](https://doi.org/10.1016/S0921-5107(99)00018-5)
14. Roy, U. N., & Basu, S. (1988). Etch pit density variation and electrical properties of GaSb single crystals grown by the Bridgman method. *Materials Letters*. [https://doi.org/10.1016/0167-577X\(88\)90029-8](https://doi.org/10.1016/0167-577X(88)90029-8)
15. Šestáková, V., & Štěpánek, B. (1995). Doping of GaSb single crystals with various elements. *Journal of Crystal Growth*. [https://doi.org/10.1016/0022-0248\(94\)00485-4](https://doi.org/10.1016/0022-0248(94)00485-4)
16. Stollwerck, G. (2000). Characterization and simulation of GaSb device-related properties. *IEEE Transactions on Electron Devices*. <https://doi.org/10.1109/16.822293>
17. Yuan, Z., Kumar, A., Chen, C. Y., Nainani, A., Bennett, B. R., Boos, J. B., & Saraswat, K. C. (2013). Antimonide-based heterostructure p-channel MOSFETs with Ni-alloy source/drain. *IEEE Electron Device Letters*. <https://doi.org/10.1109/LED.2013.2280615>