

# Dry Sliding Friction of Al-Si-B<sub>4</sub>C Composites Prepared Through Powder Metallurgy using Taguchi Design



Abraham Subaraj. M, Bensam Raj. J, Naveenchandran. P, Christopher Ezhil Singh. S, G.Glan Devadhas

**Abstract:** This research paper discuss about the friction behavior of Al-12Si-xB<sub>4</sub>C composites prepared through powder metallurgy method by varying the weight percentage of reinforcement (x = 2, 4, 6, 8, and 10) content. The samples were prepared by using die and punch assembly and the lubricant used to eject the sample from the die was molybdenum disulfide. The compaction was done by using compression testing machine by applying a pressure of 800MPa. The dry sliding friction behavior of the sample was conducted on Pin-on-Disc machine and the experimental values of friction were calibrated. Taguchi design experiment was done by applying L25 orthogonal array for 3 factors at 5 levels for the response parameter coefficient of friction. Analysis of Variance demonstrated by Mean and S/N ratio table for coefficient of friction was discussed and from the table it can be seen that the reinforcement plays a main role, when the compared with load and sliding distance. The normal probability plot shows that the residuals falls near to the red line, it indicate that the error values were less in the model.

**Keywords:** Al-Si-B<sub>4</sub>C, ANOVA, P/M, Taguchi design, CoF.

## I. INTRODUCTION

Aluminium based composites is commonly utilized in manufacturing to variety appropriates variations to improve the tribological in addition to mechanical properties. Al based composites is strengthened to afford extra strength to metal [1]. The light weight metal Al alloy is strengthened by some of carbide or oxide materials. Among Al alloy is the best utilized matrix metal for the planning of light weight commercial products [2]. The CoF have been conceded out in this effort. Taguchi technique is utilized for optimization of factors and ANOVA is conceded out [4]. The friction

behaviour on Al based composites utilizing Taguchi technique with load, reinforcement, sliding distance as input and output as CoF. ANOVA demonstrates the significant factors for controlling the friction. This research work the friction behavior of Al-12Si-xB<sub>4</sub>C composites prepared through powder metallurgy method by varying the weight percentage of reinforcement (x = 2, 4, 6, 8, and 10) content. Taguchi design experiment was done by applying L25 orthogonal array for 3 factors at 5 levels for the response parameter coefficient of friction. Analysis of Variance demonstrated by Mean and S/N ratio table for coefficient of friction was discussed and from the table it can be seen that the reinforcement plays a main role, when the compared with load and sliding distance. The normal probability plot shows that the residuals falls near to the red line, it indicate that the error values were less in the model.

## II. EXPERIMENTAL PROCEDURE

The aluminium and silicon powder was purchased from metal powder company, Thirumagal, Madurai, Tamilnadu, India. The particle sizes of the two powders were 40µm with purity 99.5%. The powders were mixed in high energy ball mill for 30min for homogenous mixing. The mixed powder were compacted in die and punch assembly with a pressure of 800MPa in compression testing machine. The samples with 10mm diameter and 30mm height were used for the dry sliding friction and wear on pin-on-disc machine.

## III. TAGUCHI DESIGN

The influence of input parameters on the friction parameters was deliberate utilizing the Taguchi's method. Next leading the trial test, it was obvious to select the levels of experiments. For the current circumstance, process parameters deliberated are reinforcement, load, and SD changing at 5 levels. Friction trials were showed in agreement to say trial plan and response was measured as specified in Table 1. The input parameters such as reinforcement (A), load (B) and SD (C) at 5 levels were deliberated for this current work. With the design plan of L25 orthogonal array, the trial levels were obvious and revealed in Table 2.

Table 1 trials and levels

Factors	Levels				
	1	2	3	4	5
wt.% B <sub>4</sub> C	2	4	6	8	10

Revised Manuscript Received on October 30, 2020.

\* Correspondence Author

**Abraham Subaraj. M<sup>1</sup>**, Mechanical, Bharath Institute of Higher Education and Research, Bharath University, India. Email: masubaraj@gmail.com

**Bensam Raj. J<sup>2</sup>**, Mechanical, Muthayammal Engineering College, Rasipuram, India. Email: bensmech@yahoo.co.in

**NAVEENCHANDRAN. P<sup>3</sup>**, Automobile, Bharath Institute of Higher Education and Research, Bharath University, Chennai, Tamilnadu, India. Email: asriyan@gmail.com.

\***Christopher Ezhil Singh. S<sup>4</sup>**, Mechanical, Vimal Jyothi Engineering College, Kannur, India. Email: christopher0420@vjec.ac.in

**Glan Devadhas. G<sup>5</sup>**, Applied Electronics and Instrumentation, Vimal Jyothi Engineering College, Kannur, India. Email: glandeva@vjec.ac.in

© The Authors. Published by Blue Eyes Intelligence Engineering and Sciences Publication (BEIESP). This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>)

Load (N)	8	16	24	32	40
SD (m)	400	800	1200	1600	2000

Table 2 experimental run and response parameters

wt.% B <sub>4</sub> C	Load (N)	SD (m)	CoF	S/N ratio
2	8	400	0.46452	6.65991
2	16	800	0.51484	5.76650
2	24	1200	0.54194	5.32098
2	32	1600	0.57129	4.86279
2	40	2000	0.61293	4.25172
4	8	800	0.4877	6.23694
4	16	1200	0.5235	5.62167
4	24	1600	0.553	5.14550
4	32	2000	0.58333	4.68162
4	40	400	0.54954	5.19995
6	8	1200	0.49033	6.19010
6	16	1600	0.54020	5.34888
6	24	2000	0.57621	4.78826
6	32	400	0.52565	5.58593
6	40	800	0.56721	4.92509
8	8	1600	0.4977	6.06065
8	16	2000	0.53404	5.44852
8	24	400	0.474	6.48443
8	32	800	0.5135	5.78919
8	40	1200	0.54954	5.19995
10	8	2000	0.48441	6.29564
10	16	400	0.41712	7.59478
10	24	800	0.45883	6.76693
10	32	1200	0.48664	6.25584
10	40	1600	0.52382	5.61624

IV. ANOVA FOR COEFFICIENT OF FRICTION OF S/N RATIO

The ANOVA for coefficient of friction of S/N ratio was discussed in Table 3 the most influencing factor that influences the CoF were reinforcement B<sub>4</sub>C compared to load and SD with the confidence level 95% for the S/N ratio ANOVA. The F-test value was 2.7763 which is less than the F-table value therefore all the input factors are significant. The response table for S/N ratio of CoF was discussed in Table 4. Figure 1 shows the S/N ratio plot for CoF.

Table 3 Analysis of Variance for SN ratios of CoF

Source	DF	Seq SS	Adj SS	Adj MS	F	P
Wt.% B <sub>4</sub> C	4	4.8976	4.8976	1.22439	60.04	0.000
Load (N)	4	4.5922	4.5922	1.14804	56.29	0.000
SD (m)	4	4.2903	4.2903	1.07257	52.59	0.000
Residual Error	12	0.2447	0.2447	0.02039	-	-
Total	24	14.0247	-	-	-	-

Table 4 Response Table for Signal to Noise Ratios of CoF Smaller is better

Level	Wt.% B <sub>4</sub> C	Load (N)	SD (m)
1	5.372	6.289	6.305
2	5.377	5.956	5.897
3	<b>5.368</b>	5.701	5.718
4	5.797	5.435	5.407
5	6.506	<b>5.039</b>	<b>5.093</b>
Delta	1.138	1.250	1.212
Rank	3	1	2

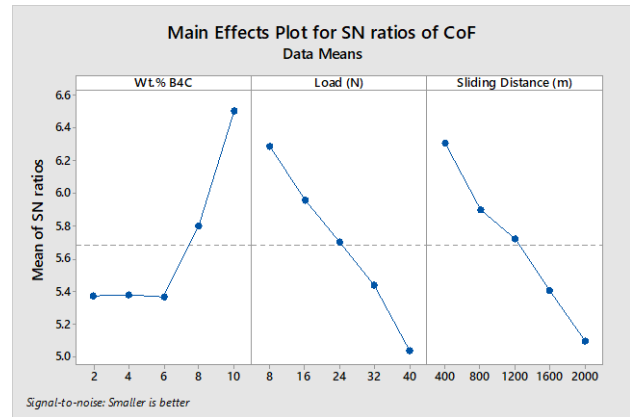


Figure1 shows the S/N ratio plot for CoF

V. ANOVA FOR COEFFICIENT OF FRICTION OF MEANS

The ANOVA for coefficient of friction of means was discussed in Table 5 the most influencing factor that influences the CoF were reinforcement B<sub>4</sub>C compared to load and SD with the confidence level 95% for the means ANOVA. The F-test value was 2.7763 which are less than the F-table value therefore all the input factors are significant. The response table was discussed in Table 6. Figure 2 shows the mean plot for CoF

Table 5 Analysis of Variance for Means

Source	DF	Seq SS	Adj SS	Adj MS	F	P
Wt.% B <sub>4</sub> C	4	0.01672	0.01672	0.00418	95.87	0.000
Load (N)	4	0.01661	0.01661	0.00415	95.21	0.000
SD (m)	4	0.01510	0.01510	0.00377	86.60	0.000
Residual Error	12	0.00052	0.00052	0.00004	-	-
Total	24	0.04896	-	-	-	-

Table 6 Response Table for Means of CoF

Level	Wt.% B <sub>4</sub> C	Load (N)	SD (m)
1	0.5411	<b>0.4849</b>	<b>0.4862</b>
2	0.5394	0.5059	0.5084
3	0.5399	0.5208	0.5184
4	0.5138	0.5361	0.5372
5	<b>0.4742</b>	0.5606	0.5582
Delta	0.0669	0.0757	0.0720
Rank	3	1	2


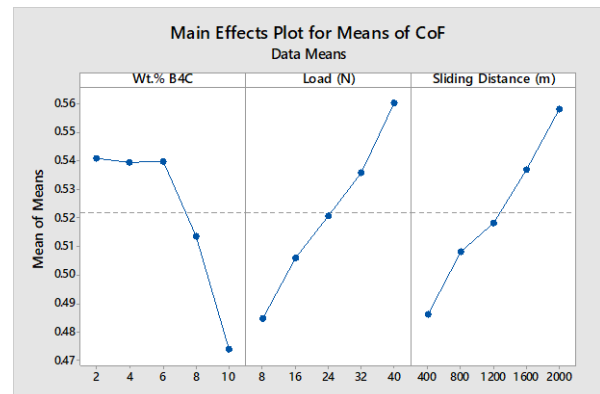


Figure 2 shows the mean plot for CoF




**VI. INTERPRETATION OF RESIDUAL GRAPHS**

The normal probability plot of the residuals to check the normality of the S/N ratio and means CoF of figures 3(i) & 4(i) show the normal probability plot for Al-Si-B<sub>4</sub>C composite. This probability plots evidently specifies that the perceived trial values lies very close to the red line deducing that the errors are ignored and the model is sufficient. The dissemination of residuals for all the elucidation (25 runs) is demonstrated in the histogram. Nearly bell formed symmetrical histogram could be incidental from Figs. 3(ii) & 4(ii). The residuals versus the fitted values for the S/N ratio and means CoF are plotted in Figs. 3(iii) & 4(iii). The sprinkling of the residuals are arbitrarily about zero which designates that the errors are negligible having constant variance. Figures 3(iv) & 4(iv) demonstrate the plots of the residual value and the order of the conforming trial values. The outcomes are effect by the order of the runs that takes place when a line order is utilized to gather the data.

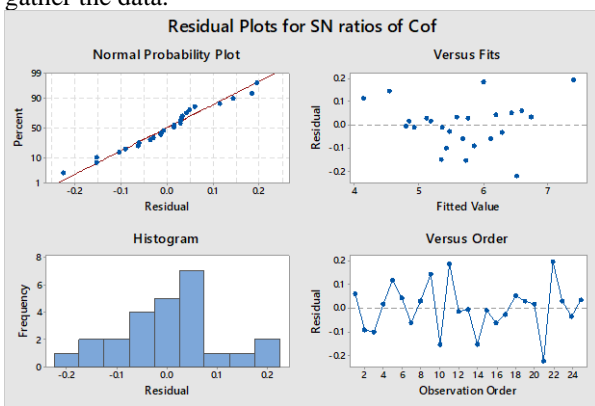

**Figure 3 demonstrates the S/N ratio of CoF for normal probability, residual vs fits, histogram and Residual vs order**

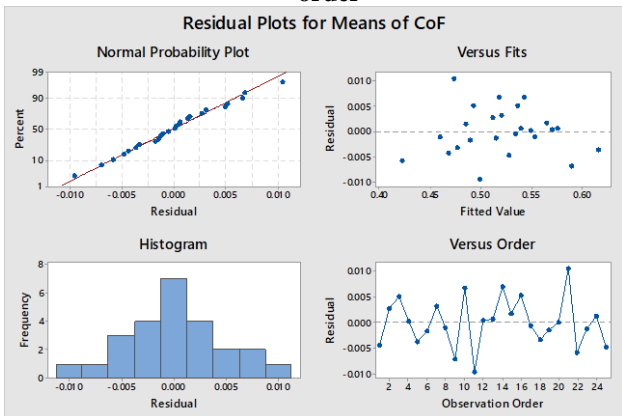


**Figure 4 demonstrates the Means of CoF for normal probability, residual vs fits, histogram and Residual vs order**


**VII. INTERACTION EFFECT OF COEFFICIENT OF FRICTION**

Figure 5(a-c) demonstrates the collaborating influence of B<sub>4</sub>C wt% and the loads of 8, 16, 24, 32 and 40 N on CoF. Figure 5(a) is the CoF map for reinforcement vs load. The perceived CoF region was low and medium, the violet distribution was dominant. While increasing the B<sub>4</sub>C wt% at loads, the CoF is less for the 400 m SD and marginally rises in CoF for all SD. Figure 5(b) demonstrates the map for reinforcement vs SD, the brown and violet distributions are


identified. In lower sliding distance and higher reinforcement the brown region was identified, which confirms that increasing the SD, CoF also improved. Figure 5(c) shows the joined influence of load and SD on CoF for map at all reinforcements, the violet and brown region performed. Higher CoF for lower wt% of B<sub>4</sub>C at different loads is owing to the rise in SD. This another time authorizes that the B<sub>4</sub>C is the main supervisory factor on the CoF of the composites. For the entire Al-Si- B<sub>4</sub>C composite samples the CoF improved with the rise in the SD and load.

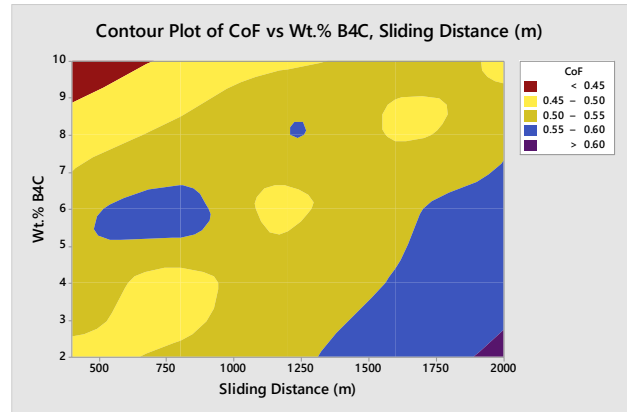

**a**

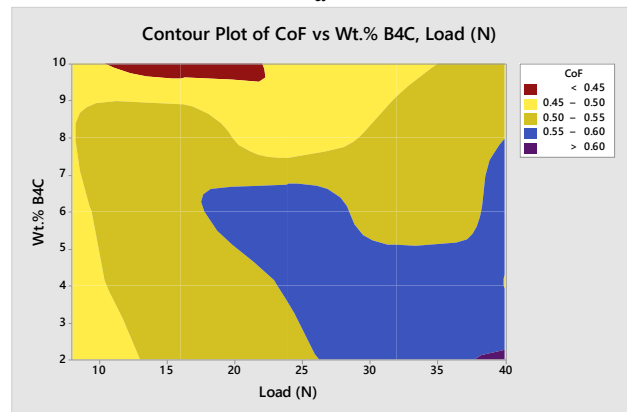

**b**

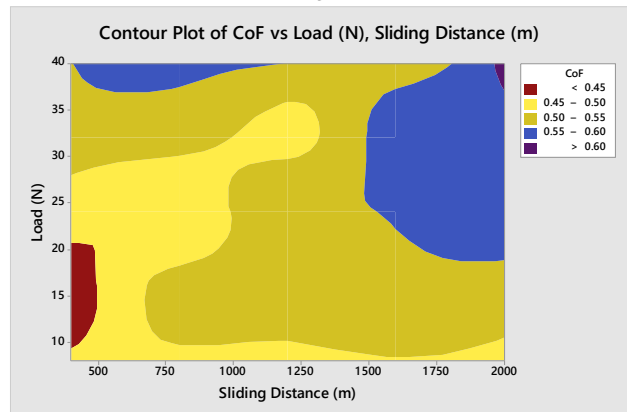

**c**

**VIII. CONCLUSION**

This current research work was focused on the dry sliding wear and friction of Al-Si-B<sub>4</sub>C composites under powder metallurgy method using Taguchi method.



Analysis of Variance demonstrated by Mean and S/N ratio table for coefficient of friction was discussed and from the table it can be seen that the reinforcement plays a main role, when the compared with load and sliding distance. The normal probability plot shows that the residuals falls near to the red line, it indicate that the error values were less in the model.

## REFERENCE

1. M. Abraham Subraj, J. Bensam Raj, R.Malkiya Rasalin Prince, G.Glan Devadhas, S. Christopher Ezhil Singh, "Corrosion Rate of Al-Si Alloy Reinforced with B<sub>4</sub>C Nanoparticle Prepared by Powder Metallurgy Method using RSM", International Journal of Innovative Technology and Exploring Engineering, Vol. 9, No.1, 2019, pp.4677-4682.
2. S. Christopher Ezhil Singh, and N. Selvakumar, "Optimization and effect of dry sliding wear and friction behavior, electrical resistivity and mechanical properties of Cu-4Cr-xZrC composites", Journal of Applied Research and Technology, Vol.16, No.4, 2019, pp. 299-311.
3. M. Abraham Subraj, J. Bensam Raj, S. Christopher Ezhil Singh, "Friction Behavior of Al-Si-B<sub>4</sub>C Composites Prepared by Powder Metallurgy Technique Using RSM", International Journal of Mechanical Engineering and Technology, Vol.9, No.11, 2018, pp. 1339 – 1349.
4. M. Abraham Subraj, J. Bensam Raj, S. Christopher Ezhil Singh, "Effect of Wear Behavior on B<sub>4</sub>C Particles Reinforced with Al-Si Alloy Prepared Through Powder Metallurgy Method Using Response Surface Methodology", International Journal of Mechanical and Production Engineering Research and Development, Vol. 9, No.1, 2018, pp. 41-50.
5. C. Fradaric John, R. Christu Paul, S. Christopher Ezhil Singh, "Weight Loss Method for corrosion behaviour of Al-12Si-ZrC Composites Using Response Surface Methodology", International Journal of Applied Engineering Research, Vol.13, No.6, 2018, pp. 4428-4433.
6. C. Fradaric John, R. Christu Paul, S. Christopher Ezhil Singh, "Optimization of Corrosion Performance on nano ZrC particles reinforced with Al-12si alloy Using RSM Design", International Journal of Applied Engineering Research, Vol. 13, No. 6, 2018, pp. 4459-4463.
7. C.Sankar, K.Gangatharan, S.Christopher Ezhil Singh, "Optimization on Tribological Behavior of Milled Nano B<sub>4</sub>C Particles Reinforced with AZ91 Alloy Through Powder Metallurgy Method", Transactions of the Indian Institute of Metals, Springer, Vol.72, No.5, 2019, pp. 1255-1275.
8. C. Fradaric John, R. Christu Paul, S. Christopher Ezhil Singh, "Tribological behavior, mechanical properties and microstructure of Al-12Si-ZrC composite prepared by powder metallurgy", Bulletin of the Polish Academy of Sciences: Technical Sciences, Vol. 65, No.2, 2017, pp. 149-154.

## AUTHORS PROFILE



**Abraham Subaraj. M** joined as Research Scholar in the year 2014 as a part time scholar in Department of Mechanical Engineering, Bharath Institute of Higher Education and Research, India. I have completed my Bachelor Degree in Mechanical Engineering from MVJ College of Engineering, Bangalore, Karnataka from Bangalore University in the year 1990 and I have worked in VILCO Coimbatore as Production Engineer from 1999 to 2000 and Master Degree in Thermal Engineering from Mohamed Sathek Engineering College, Kilakarai, Tamilnadu under Madurai kamaraj University in the year 1999. I am currently working as Associate Professor in Bethelatham Institute of Engineering, Karungal, Kanyakumari, Tamilnadu, India. I have Published 5 Journal Papers in reputed journals.



**Bensam Raj. J.** Professor in the Department of Mechanical Engineering, Muthayammal Engineering College, Rasipuram, India. I have completed my Bachelor Degree in Mechanical Engineering from RVS College of Engineering and Technology, Dindugal, Tamilnadu from Madurai Kamarajar University in the year 1999 and Master of Engineering from Annamalai University, Chidambaram, Tamilnadu in thr year 2000. I have pursued my Ph.D from Anna University. I have worked as Professor in Nadar Saraswathi Engineering College, Rasipuram, Tamilnadu, India. Under my guidance 13 Ph.D scholars

pursuing and registered under reputed universities. Eight Scholars completed Ph.D under my guidance. I have Published 17 Journal Papers in reputed journals.



**Dr.Naveenchandran. P.** Professor & Head, Department of Automobile Engineering, Bharath Institute of Higher Education and Research, Bharath University, Chennai, Tamilnadu, India. I have completed my Bachelor Degree in Mechanical Engineering from Annamalai University, Chidambaram, Tamilnadu, India and Master of Engineering in Thermal Power from Annamalai University, Chidambaram, Tamilnadu, India. I have completed my Ph.D from Universiti Teknologi, Petronas, Malaysia. I have worked as Lecturer in Department of Mechanical Engineering, Bharath Institute of Higher Education and Research, Tamilnadu, India. I have worked as lecturer in Department of Mechanical/Automotive Engineering, Kolej WIT, Port Kiang, Malaysia. I have worked as Professor & Head in Department of Mechanical Engineering, Loyola Institute of Technology, Tamilnadu, India. I have published more than 40 Journal Papers in reputed journals.



**Dr.S.Christopher Ezhil Singh,** Professor, Department of Mechanical Engineering, Vimal Jyothi Engineering College, Kannur, Kerala, India. I have completed my Bachelor Degree in Mechanical Engineering from Noorul College of Engineering, Thuckalay, from Manonmaniam Sundaranar University, Tirunelveli and Master of Engineering in Computer Aided Design from Hindustan College of Engineering, Chennai, Tamilnadu under University of Madras, Chennai. I have completed my Ph.D from Mepco Schelnk College Engineering, sivakasi, Tamilnadu, India under Anna University. I have worked as Associate Professor in Bethelatham Institute of Engineering, Karungal, Kanyakumari, Tamilnadu, India. I have worked as Associate Professor in Maria College of Engineering and Technology, Attoor, Kanyakumari, Tamilnadu, India. I have Published 35 Journal Papers in reputed journals.



**Dr G.Glan Devadhas** is presently working as a Professor in the Department of Electronics & Instrumentation at Vimal Jyothi Engineering College, Kerala. He has received his B.E. degree in Instrumentation and Control Engineering, M.E. degree in Process Control and Instrumentation and Ph.D in Intelligent Controller Design during 1998, 2001, 2013 respectively. He is having more than 15 Years of experience in teaching and research as Lecturer, Assist Professor, Associate Professor, HOD, Board of studies chairman, Academic council member, Research Supervisor, Doctoral committee member and Professor in various Engineering Colleges and Universities. He is the reviewer of many journals includes International Journal of Naval Architecture and Ocean Engineering, Journal of Water Process Engineering, Int. J. of Modeling, Simulation & Scientific Comp etc. He has published 130 articles in various indexed journals. He has attended more than 50 seminars in national and international level. He has organized three IEEE international Conferences, 1 national conference and 10 national level seminars. He has guided 30 B.E projects 12 ME projects and guiding 8 Ph.D scholars. He is the member ISA,ISTE, IEEE professional bodies. He is the executive member of IEEE India CAS Chapter. He has involved in the project of Developed Attitude and Orbit Control System (AOCS) for a Nano Satellite. His main area of interest are Soft computing, Intelligent controller Design, System Identification, Adaptive systems, Smart Systems.