

# Abrasive Wear Behaviour of Plasma Sprayed Al<sub>2</sub>O<sub>3</sub> / TiO<sub>2</sub> Coatings

Arunkumar T, Jebasingh C, Venkatachalam P, Sajin J B, Anish M

**Abstract:** Premature failure due to abrasive wear is observed in high powered engine in recent decades, despite of stringent maintenance procedures comparative to older engine. Plasma spray coatings are recurrently used to circumvent the abrasive wear in aerospace, defense and certain automotive applications like piston pump, cylinder bore etc. This work is to identify the most influencing wear parameters namely sliding speed ( $S_s$ ), applied load ( $A_L$ ) and sliding distance ( $S_D$ ) of the composite coated steel. Initially the surface morphology and elemental analysis was carried out to analyze the surface roughness and homogeneous distribution of the composites. Furthermore wear analyzes results indicates that the composite coating has high wear resistance and specific wear rates are ranging from  $0.52346 \times 10^{-5} \text{ m}^3 / \text{N-m}$  to  $3.25711 \times 10^{-5} \text{ m}^3 / \text{N-m}$ .

**Keywords :** Plasma spray coating, specific wear rate, cylinder bore, Taguchi.

## I. INTRODUCTION

In industrial application like automobile, aircraft, agricultural and marine vehicles the usage of piston pumps are inevitable [1]. The abrasive wear is major problem in the cylinder bore due to continuous sliding of surfaces, which leads to the premature failure of the engine [2]. In addition wear rates are associated with fluctuating critical processing temperature, high pressure and relative velocity [3]. Abrasive wear accounts for almost 44% premature engine failure as well as failure of cylinder bore [4]. This implies high adherent and smooth surface coating is to improve the engine life against wear rate. Plasma spray coating is widely used to prevent degradation of various parts like turbine blade, cylinder bore under severe conditions. Plasma spray coating method offers various thickness ranges 10  $\mu\text{m}$  to 1 mm with high deposition rate and good adherence to the substrate. [5]. Furthermore this method extensively ropes the ceramic material coating to improve the life span of numerous components in industrial equipment's [6]. Plasma sprayed Aluminium Oxide (Al<sub>2</sub>O<sub>3</sub>) and Titanium Oxide (TiO<sub>2</sub>) coatings are recurrently used for wear resistance in various applications [7], [8]. Al<sub>2</sub>O<sub>3</sub> coating has predominated wear resistant property but it is used in limited application due to poor brittle nature [9], [10]. In addition of TiO<sub>2</sub> with

Al<sub>2</sub>O<sub>3</sub> leads the wear resistance due to very strong adhesion and low porosity [11]. The accumulation of 3-40 wt% TiO<sub>2</sub> with alumina has become very common in plasma spraying method to improve the mechanical properties. In this study, specified combination of Al<sub>2</sub>O<sub>3</sub> + 13% TiO<sub>2</sub> was deliberated from established literature [12]. The work is focus on identifying the most influencing wear parameters (by pin on disk method) of the plasma sprayed composite (Al<sub>2</sub>O<sub>3</sub> + 13% TiO<sub>2</sub>) coating.

## II. MATERIALS AND METHODS

Mild steel rod (ASTM A36 -  $\varnothing$ 12 mm) used as substrates, which is roughened by blasting quartz sands of 16-20 mesh. All the samples were cleaned carefully with acetone then surface were grit blasted using aluminium oxide blasting media. Herein, Ni + 5%wt Al powder and Al<sub>2</sub>O<sub>3</sub> + 13%wt TiO<sub>2</sub> were used as top and bond coating respectively [13]. The Ni + 5%wt Al and Al<sub>2</sub>O<sub>3</sub> + 13% TiO<sub>2</sub> composites were prepared separately by ball mill (SPEX 8000D, UKRAINE) for 5 hours with constant speed of 300 rpm and 12 ZrO<sub>2</sub> ball in the milling jar. The bond and top coating has done on mild steel substrate by Praxair plasma spray system with SG-100 gun. Prior to applying composites on the substrate, three trial were executed to optimize the powder flow rate and other conditions to obtain desired coating thickness (120  $\pm$  25  $\mu\text{m}$ ). The surface morphology and quantitative elemental analyses of coated samples ( Figure 1) were obtained using scanning electron microscope (ZEISS SUPRA 55) and EDAX (OXFORD measurements) as per ASTM D 4541 [14]-[17]. In order to determine surface roughness of the coating [18], the areas of 10  $\times$  10  $\mu\text{m}$  were scanned with 512  $\times$  512 data points using AFM NTEGRA PRIMA – NTMDT, Ireland. After confirming the presence of composite on the substrate, dry sliding wear analysis has been carried out by pin on disc tester (DUCOM TR-20LE-PHM-400) as per ASTM G99 [19]. Three trails were carried out to ensure its repeatability for the samples. The test was done under the room temperature 25  $^{\circ}\text{C}$ , ambient humidity, varying process parameter like sliding velocity (1.308 m/s 1.962 m/s, 2.610 m/s), load (30 N, 40 N, 50 N) and sliding distance (1200 m, 1800 m, 2400 m). The volume loss has been calculated from mass loss value which obtains from before and after the test by weighing machine. Finally the specific wear rate has been calculated by Equation 1. An orthogonal array and S/N ratio were employed to identify the wear influencing parameter. Considering all 3 parameters and 3 levels, the L<sub>9</sub> orthogonal array has chosen for this study. To identifying process parameter for this case, “smaller is the better” quality characteristic was chosen and

Revised Manuscript Received on December 05, 2019.

\* Correspondence Author

Arunkumar. T\*, Department of Mechanical Engineering, CMR Institute of Technology, Bengaluru, India. [arunkumar.t@cmrit.ac.in](mailto:arunkumar.t@cmrit.ac.in)

Jebasingh C, Department of Mechanical Engineering, Narayanaguru College of Engineering, Kanyakumari, India

Venkatachalam P, Department of Mechanical Engineering, MVJ College of Engineering, Bengaluru, India.

Sajin J B, Department of Mechanical Engineering, Sree Buddha College of engineering, Patoor Kerala, India

Anish.M, School of Mechanical Engineering, Sathyabama Institute of Science and Technology, Chennai, India.

calculated S/N ratio from Equation 2.

$$\text{Specific wear rate (Wsp)} = \frac{\text{Volume loss (m}^3\text{)}}{\text{Load (N)} \times \text{sliding distance(m)}} \quad (1)$$

$$\frac{S}{N} \text{ ratio} = -10 \log_{10} y^2 \quad (2)$$




**Figure 1.** Plasma sprayed composite (Al<sub>2</sub>O<sub>3</sub> + 13% TiO<sub>2</sub>) samples


### III. RESULTS AND DISCUSSION

#### A. Morphological Studies

The surface homogeneity of Al<sub>2</sub>O<sub>3</sub>, +13% TiO<sub>2</sub> composite is shown in Figure 2. Owing to good agglomeration of the composite coating (Figure 2a), the surface roughness was less and it can be reduces the wear rate. Figure 2b shows the equiaxed polygonal shape of composite embedded with few partially melted particles, which is due to the few TiO<sub>2</sub> particles were partially melted under the plasma spraying condition. However there is no porosity in the coating surface, which means Al<sub>2</sub>O<sub>3</sub> +13% TiO<sub>2</sub> composites being uniformly distributed in the entire surface. Figure 3 shows that the quantitative analysis of Al<sub>2</sub>O<sub>3</sub> +13% TiO<sub>2</sub> composite coatings, which reveals alumina and titanium dioxide were uniformly blended and distributed on the whole surface and turn into Al<sub>2</sub>TiO<sub>5</sub> composite.

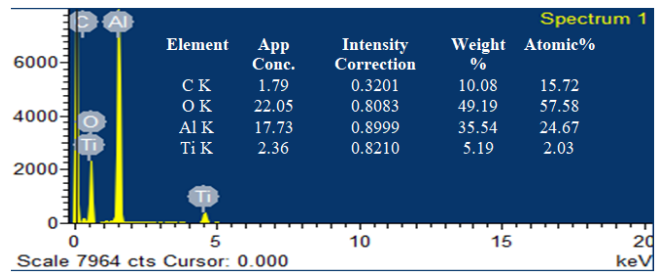



**Figure 3.** Quantitative analysis of Al<sub>2</sub>O<sub>3</sub> +13% TiO<sub>2</sub> composite

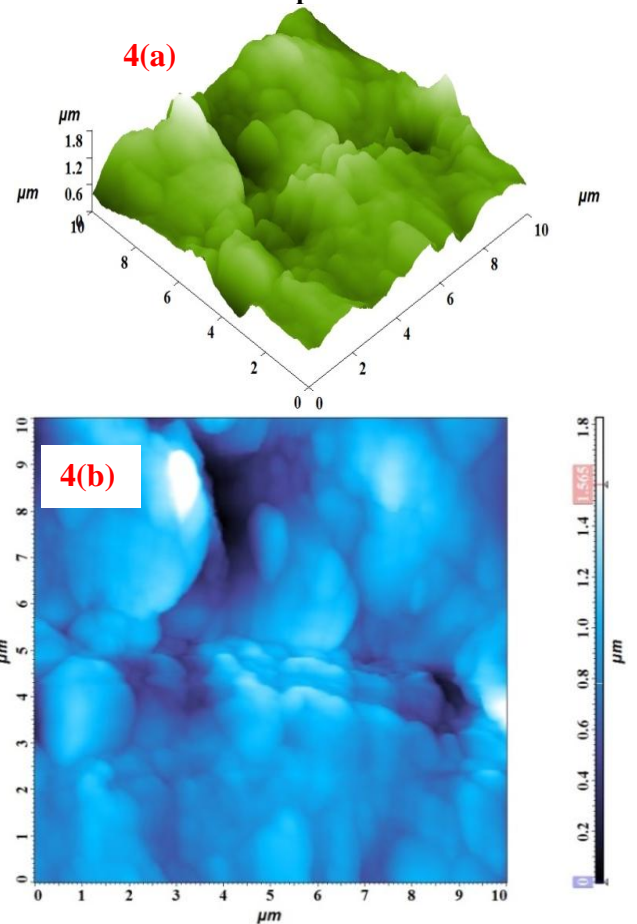

**Figure 4.** Al<sub>2</sub>O<sub>3</sub> +13% TiO<sub>2</sub> composite (a) Three Dimensional topography (b) Surface Structure by AFM  
The atomic force microscope image shows (Figure. 4) the 3-dimensional topography of the Al<sub>2</sub>O<sub>3</sub> + 13% TiO<sub>2</sub> composite coated surfaces. It describes the Peak-to-peak (S<sub>y</sub>) is 1824.61 nm, Ten Point height (S<sub>z</sub>) is 912.966 nm, Surface Skewness (S<sub>sk</sub>) of -0.128403, Coefficient of Kurtosis (S<sub>ka</sub>) of 1.47615, Entropy is 12.9892, Redundance is -0.199084 and average surface roughness is 167.63. From these results it has been concluded that the degree of discontinuity is very less which means composite has less porosity, good surface finish and perfectly clustered.

#### B. Wear Analysis

The dry sliding wear test was conducted by varying process parameter and calculated mass loss with the help of weighing machine. From mass loss, volume loss has been calculated and found the specific wear rate (W<sub>sp</sub>) by equation 1 and shown in Fig. 5. It has clear that specific wear rate is

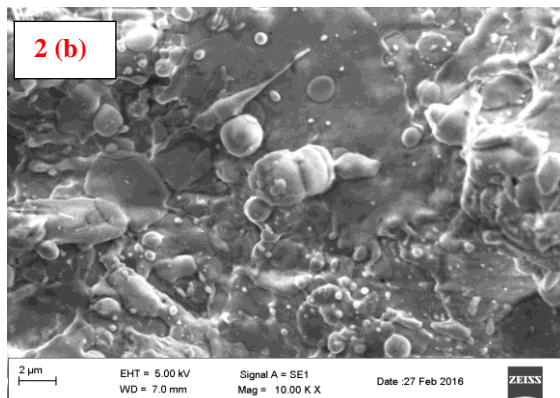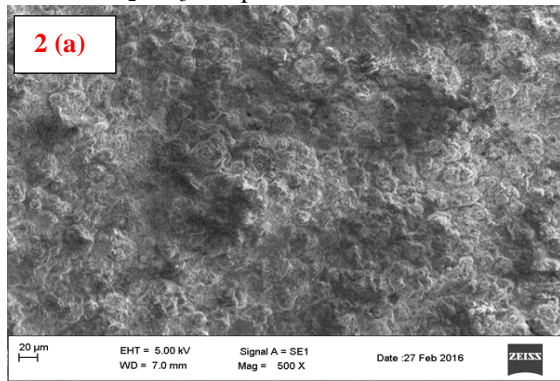

**Figure 2.**(a) Surface morphology of Al<sub>2</sub>O<sub>3</sub>, +13% TiO<sub>2</sub> composite; (b) Melted region of the Al<sub>2</sub>TiO<sub>5</sub> composite

increased when the load is increased which means the specific wear rate is directly proportional to the normal applied load (as per Archard's law). Likewise, when sliding distance increase wear also increased due to temperature rise and causes the delamination of coating surface. However specific wear rate is decreased when sliding a velocity increase which is due to high bonding strength of the coating interface. From specific wear rate values S/N ratio and mean values was calculated using Equation 2 and mentioned in table 1.

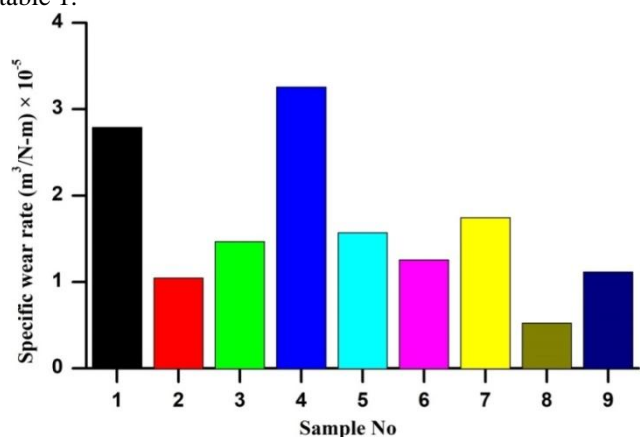


Figure 5 Specific wear rate of samples

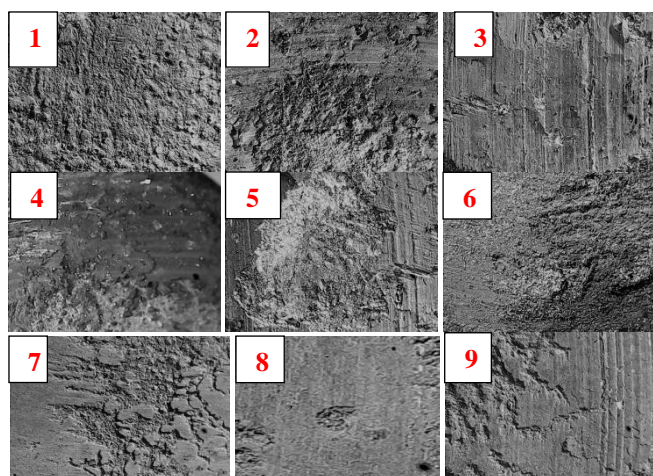


Figure 6. Worn tracks of the composite with effect of the various wear parameters

Table 1 Specific wear rate, SN ratio and mean values based on varying parameter

Sample No.	S <sub>s</sub> (m/s)	A <sub>L</sub> (N)	S <sub>D</sub> (m)	Specific wear rate (m³/N-m) × 10⁻⁵	S/N ratio	Mean
1	1.308	30	1200	2.79181	-8.9177	2.79181
2	1.308	40	1800	1.04693	-0.3983	1.04693
3	1.308	50	2400	1.4657	-3.3209	1.4657
4	1.962	30	1800	3.25711	-10.256	3.25711
5	1.962	40	2400	1.57039	-3.9202	1.57039
6	1.962	50	1200	1.25631	-1.982	1.25631
7	2.61	30	2400	1.74488	-4.8353	1.74488
8	2.61	40	1200	0.52346	5.6223	0.52346
9	2.61	50	1800	1.11672	-0.9589	1.11672

The effect of the various wear parameter of the Al<sub>2</sub>O<sub>3</sub> + 13% TiO<sub>2</sub> composite on steel are shown in Fig. 6 (1-9). The worn

tracks of fourth sample (Fig. 6.4) were much rougher than other samples. On the other hand eighth sample has very less worn tracks which mean it has high wear resistance than other samples. From table 2 it was clearly understand that the most influencing parameter of specific wear rate is A<sub>L</sub> followed by S<sub>S</sub> and S<sub>D</sub> respectively. From figure 7 it can be noted that the best combination for obtaining least specific wear rate is 2.610 m/s of sliding speed (Level 3), 40 N load (Level 2), and sliding distance of 1200m (Level 1). The lowest specific wear rate of eighth sample is 0.52346 × 10<sup>-5</sup> m<sup>3</sup>/N-m which is under tried combination.

Table 2 Response table for SN Ratios

Level	S <sub>S</sub> (m/s)	A <sub>L</sub> (N)	S <sub>D</sub> (m)
1	-4.21231	-8.00322	-1.75913
2	-5.38625	0.43459	-3.87129
3	-0.05732	-2.08725	-4.02545
Delta	5.32894	8.43781	2.26632
Rank	2	1	3

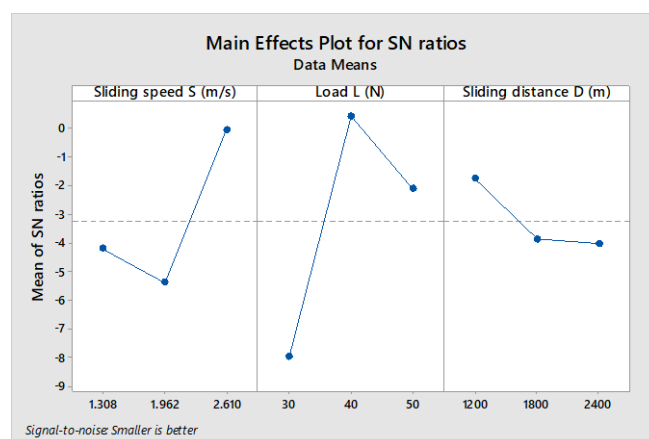


Figure 7. Main effect plot for SN ratios of Al<sub>2</sub>O<sub>3</sub> + 13% TiO<sub>2</sub> composite

#### IV. CONCLUSION

The purpose of this work is to identify the influence of wear parameters like S<sub>S</sub>, A<sub>L</sub> and S<sub>D</sub> of the (Al<sub>2</sub>O<sub>3</sub> + 13 % TiO<sub>2</sub> composite) coated steel. Initially quantitative analysis and surface morphology of composite coating has been analysed EDAX and SEM analysis, which has confirmed that the composite coating material presence and uniform deposition on the substrate. Also surface roughness of the composite is very less which decrease the specific wear rate. The design of experiment approach has been engaged and acquired data in controlled way using Taguchi method. From the results it has noted that the less specific wear rate is 8<sup>th</sup> combination (S<sub>S</sub> - 2.610 m/s, A<sub>L</sub> - 40 N and S<sub>D</sub> - 1200m). Taguchi analysis revealed that the most influencing parameter is applied load followed by sliding speed and sliding distance. As sum up the Al<sub>2</sub>O<sub>3</sub> + 13 % TiO<sub>2</sub> composite coating has high wear resistance due to adherence to the substrate. Therefore it can be used to reduce the wear loss due to abrasion which will increase the performance of the cylinder bore as well as engine life.

## REFERENCES

1. Y. Liu, D. Li, Z. Tang, Y. Deng, and D. Wu, "Thermodynamic modeling, simulation and experiments of a water hydraulic piston pump in water hydraulic variable ballast system," *Ocean Engineering*, vol. 138, pp. 35–44, Jul. 2017.
2. G. Haidak, D. Wang, and S. E., "Research on the thermo-elastic deformation and fracture mechanism of the slipper retainer in the axial piston pumps and motors," *Engineering Failure Analysis*, vol. 100, pp. 259–272, Jun. 2019.
3. N. W. Bolander, B. D. Steenwyk, A. Kumar, and F. Sadeghi, "Film Thickness and Friction Measurement of Piston Ring Cylinder Liner Contact With Corresponding Modeling Including Mixed Lubrication," *ASME 2004 Internal Combustion Engine Division Fall Technical Conference*, Jan. 2004.
4. R. A. DAY, "Piston Ring And Liner Wear," *Industrial Lubrication and Tribology*, vol. 34, no. 2, pp. 44–69, Feb. 1982.
5. S. A. Musmar, A. Alrousan, and I. Tlili, "Effect of cylinder-liner rotation on wear rate: An experimental study," *Heliyon*, vol. 5, no. 7, p. e02065, Jul. 2019.
6. Y. Yang, Y. Wang, W. Tian, D. Yan, J. Zhang, and L. Wang, "Influence of composite powders' microstructure on the microstructure and properties of Al<sub>2</sub>O<sub>3</sub>-TiO<sub>2</sub> coatings fabricated by plasma spraying," *Materials & Design* (1980-2015), vol. 65, pp. 814–822, Jan. 2015.
7. X. Lin, Y. Zeng, C. Ding, and P. Zhang, "Effects of temperature on tribological properties of nanostructured and conventional Al<sub>2</sub>O<sub>3</sub>-3 wt.% TiO<sub>2</sub> coatings," *Wear*, vol. 256, no. 11–12, pp. 1018–1025, Jun. 2004.
8. P. Bansal, N. P. Padture, and A. Vasiliev, "Improved interfacial mechanical properties of Al<sub>2</sub>O<sub>3</sub>-13wt%TiO<sub>2</sub> plasma-sprayed coatings derived from nanocrystalline powders," *Acta Materialia*, vol. 51, no. 10, pp. 2959–2970, Jun. 2003.
9. W. Deng, S. Li, G. Hou, X. Liu, X. Zhao, Y. An, H. Zhou, and J. Chen, "Comparative study on wear behavior of plasma sprayed Al<sub>2</sub>O<sub>3</sub> coatings sliding against different counterparts," *Ceramics International*, vol. 43, no. 9, pp. 6976–6986, Jun. 2017.
10. G. Bolelli, V. Camillo, L. Lusvardi, and T. Manfredini, "Wear behaviour of thermally sprayed ceramic oxide coatings," *Wear*, vol. 261, no. 11–12, pp. 1298–1315, Dec. 2006.
11. X.S. Gao, Y.H. Huang, Z.J. Tian, Z.D. Liu, D.L. Shen, D.S. Wang "Characteristics and mechanism analysis of nano-sized TiO<sub>2</sub> in Al<sub>2</sub>O<sub>3</sub> coating", *J. Mater. Eng.*, vol.12, pp. 45-48, 2009.
12. N. H. N. Yusoff, M. J. Ghazali, M. C. Isa, A. R. Daud, A. Mughtar, and S. M. Forghani, "Optimization of plasma spray parameters on the mechanical properties of agglomerated Al<sub>2</sub>O<sub>3</sub>-13%TiO<sub>2</sub> coated mild steel," *Materials & Design*, vol. 39, pp. 504–508, Aug. 2012.
13. K. B. Sachidananda, K. Mahesha, and A. Dey, "Effect of powder particle size on vibration damping behaviour of plasma sprayed alumina (Al<sub>2</sub>O<sub>3</sub>) coating on AISI 304 stainless steel substrate," *Ceramics International*, vol. 44, no. 1, pp. 158–163, Jan. 2018.
14. T. Arunkumar, R. Karthikeyan, R. Ram Subramani, K. Viswanathan, and M. Anish, "Synthesis and characterisation of multi-walled carbon nanotubes (MWCNTs)," *International Journal of Ambient Energy*, pp. 1–5, May 2018.
15. T. Arunkumar and S. Ramachandran, "Investigation of Morphological and Mechanical Features of Polyurea," *Applied Mechanics and Materials*, vol. 766–767, pp. 606–611, Jun. 2015.
16. T. Arunkumar, S. Sunitha, J. Theerthagiri, J. Jeevagan, M. Anish, and T. Tatarchuk, "Effect of Polyurea Coating on Corrosion Resistance Over Mild Steel and Aluminium Substrates for Liquid Storage Applications," *Molecular Crystals and Liquid Crystals*, vol. 670, no. 1, pp. 60–73, Jul. 2018.
17. T. Arunkumar and S. Ramachandran, "Surface coating and characterisation of polyurea for liquid storage" *International Journal of Ambient Energy*, vol. 38, no. 8, pp. 781–787, Aug. 2016.
18. T. Arunkumar, S. Ramachandran, Muthumanickam M.A, Malik S.A., "Study of surface roughness analysis of polyurea coating", *Journal of the Balkan Tribological Association* vol. 22, no 4, 3528–3537, 2016.
19. P. Arivalagan, G. Chandramohan, Arunkumar, and N. Palaniappan, "Studies on dry sliding wear behaviour of hybrid composites," *Frontiers in Automobile and Mechanical Engineering* -2010, Nov. 2010. <http://dx.doi.org/10.1109/fame.2010.5714796>.

## AUTHORS PROFILE



**Dr. Arunkumar.T** Indian citizen, born in Gingee, Villupuram District, TamilNadu. He is specialized in the field of Mechanical Engineering, with his Bachelor Degree in Mechanical Engineering, Master Degree in Engineering Design and PhD in Mechanical engineering (Coating). He has 10 years of teaching experience and is currently working as an Associate Professor in the Department of Mechanical Engineering, CMR Institute of Technology, Bengaluru, India. His research interests cover ceramic, polymeric, nano materials, surface coating, tribological behaviour, corrosion, and mechanical testing. He as a co-investigator has successfully completed a funded research project from the Ministry of Defense, CVRDE, Chennai, India. He has published more than 25 research articles in various SCI/WoS and Scopus indexed Journals.



**Mr. Jebasingh.C** Indian citizen, born in kulasekharam, Kanyakumari District, Tamilnadu. He is specialized in the field of mechanical Engineering with his bachelor degree in Mechanical engineering, Master Degree in Computer Aided Design and Computer Aided manufacturing. He has more than 5 years of teaching experience as assistant professor in the Department of mechanical engineering, Narayanaguru college of Engineering, Kanyakumari District, India. His research interests cover composite materials, nano materials, surface coating, tribological behaviour and mechanical testing. He has guided more than 15 projects UG students in his career. He is a member of various international and national science and technology bodies.



**Dr. Venkatachalam P** is specialized in the field of Materials Science, with his Bachelor Degree in Physics, Master Degree in Materials Science and PhD in Metallurgical and Materials Engineering. He has 12 years of teaching experience and is currently working as an Associate Professor in the Department of Mechanical Engineering, MVJ College of Engineering, Bengaluru, India. His research interests are severe plastic deformation processes, texture engineering and structure property correlations. He completed one sponsored project funded by DST, New Delhi under fast track scheme for young scientist. He has guided one Ph.D research scholar registered under ANNA University, Chennai and more than 20 academic projects for UG and PG students in his career. He is life member of IIM.



**Dr. J.B.Sajin** is presently working as an Associate Professor in Sree Buddha college of Engineering, Pattoor, Kerala. He acquired B.Tech in Mechanical Engineering from Dr.M.G.R Educational and Research institute and ME in Manufacturing from Anna University and PhD in Advanced composite materials from Anna University. He has 10 years of teaching experience and published more than 15 research papers in various International and National journals. His research interest covers composite materials, bio-composites, Nanomaterial's and bio diesel. He has guided a good number of Academic Projects for UG and PG students in his career. He is also a reviewer for several International Journals.



**Dr. M.Anish** has obtained his Bachelor's degree in Mechanical Engineering, Master's degree in Thermal Engineering and Doctor of philosophy in Mechanical Engineering (Nuclear Reactor). He has more than 08 years of teaching experience at various levels and is presently working as an Assistant Professor in the Department of Mechanical Engineering, Sathyabama Institute of science and Technology, Chennai, TamilNadu, India. He has guided a good number of Academic Projects for UG and PG students in his career. He has published/presented several papers in various national and international journals / conferences. He is also a reviewer for several International Journals and active member in various bodies.