

Experimental Works on Self-Compacting Concrete By Partial Replacement of Rice Husk Ash with Subjected To Acid Attack



R. Ramya Swetha, M. Swaroopa Rani, U.RangaRaju

Abstract: The objectives of this work is effect of Rice husk ash (AWM) in self-compaction concrete (SCR) in order to increase in strength and a better bonding between aggregate and cement paste. SCR had an improvement over conventional concrete so that it can be placed easily without vibration or mechanical consolidation. The properties of SCR have been studied in several researches due to its importance and ability to solve the problems of concrete mix. AWM was used to substitute cement in stepped concentration of 0 %, 5%, 10%, 15%, 20% and used to gain characteristic CS of M₄₀ grade concrete mix. It is cured normal water and sulphuric acid solution (H₂SO₄) in for different ages (7days, 28days and 60days) and the strengths were determined. Sulphuric acid used in the percentages of 0%, 1%, 3%, 5%.

Index Terms: Self compacting concrete, cement replacement, rice husk ash, acid solution.

I. INTRODUCTION

Self-compacting concrete (SCR) is a new approach to high performance concrete (HPC) developed in the year 1986 by Japan. Congested reinforcement and reduction of concrete expedient is also one the reason to develop SCR. SCR flows into the formwork and around obstructions under its own weight to fill it completely and self-compacting, without any segregation and blocking. SCR mixes normally have a much higher content of fine fillers, including cement, and produce excessively high CS concrete, which restricts its field of application to special concrete only. This paper, it explores about the use of AWM to raise the number of fines and consequently reach self-compact ability in capable way and focuses on comparison of fresh and hardened properties of SCR containing different percentages of 0%, 5%, 10%, 15% and 20% AWM as an admixture. Sulphuric acid (H₂SO₄) is one of the violent natural threats to concrete structures. Acid show aggression is exaggerated by the process of corrosion and escape of cement paste constituents. Important volume of admixtures in SCR paste can really control its resistance to acid aggression.

Revised Manuscript Received on January 30, 2020.

* Correspondence Author

R.Ramya Swetha*, Civil Engineering Department, DNR College Of Engineering and Technology (DNR CET), Bhimavaram, India.

Dr M. Swaroopa Rani, Civil ENgeering Department, JNTUK-Kakinada, Kakinada, India.

Dr. U.Ranga Raju, Civil Engineering Department, DNR College Of Engineering and Technology (DNR CET), Bhimavaram, India.

© The Authors. Published by Blue Eyes Intelligence Engineering and Sciences Publication (BEIESP). This is an [open access](https://creativecommons.org/licenses/by-nc-nd/4.0/) article under the CC-BY-NC-ND license [http://creativecommons.org/licenses/by-nc-nd/4.0/](https://creativecommons.org/licenses/by-nc-nd/4.0/)

Curing H₂SO₄ acid as 0%, 1%, 3% and 5% in SCR to avoid the acid rain effects, higher durability, no difficulty to place, no vibration, reduced noise levels and good surface finishing of concrete.

II. STUDY AREA

In present study a concrete mix design is made for M₄₀ and is taken as normal concrete. In the normal concrete cement is replaced with (5%, 10%, 15% and 20%) of AWM. This study was conducted for the duration of 7, 28 and 60 days. Specimens of two types, namely specimens casted with normal concrete and on concrete by partial replacement of cement with AWM, were exposed to three percentages of H₂SO₄ solutions with concentrations of 0%, 1%, 3% and 5%. It is well known that the concrete under acidic environment is deteriorated due to a chemical attack. For example, acid rains cause concrete unexpectedly short service life due to the damages concrete cover.

III. METHODOLOGY

A. Concrete Mix design (as per is 10269: 1982)

In this analysis mix proportioning is done using BIS method for, M₄₀ grade of concrete. The consequential mixes are modified after conducting trials at laboratory by duly the Indian standards guidelines and test result values are satisfied.

B. Mix Proportions by Weight

W/C ratio = 0.39, Cement = 1, Fine aggregate = 1.12, Coarse aggregate = 2.28.

Testing of hardened properties:

After getting final results of mix proportions, cubes are been casted.



Fig(a) Casted cubes M₄₀ grade of SCR

IV. SPRCIMENS CURING

The specimens are gone in moulds at intact room temperature about to 24 hours. The specimens are then divide from the moulds and instantaneously transfer to curing ponds contains H₂SO₄ (0%, 1%, 3%, 5%) and cured for 7, 28 and 60 days. Find out the PH value of dilute acid day by day. In this concentration of acid decreases, so maintain the equal level PH to previous concentration for entire curing period as per IS: 516-1969.



Fig (b) Curing Cubes of M₄₀ grade of SCR

Testing for specimens : The specimen has been ensuring to undergo proper testing on schedule point in time. The casted specimens are tested as per Indian standard measures, directly away following they are detached from curing pond and wiped off the surface water, as per IS 516-1959.

A. Compressive Strength (CS) values of concrete:

The CS of M₄₀ grade SCR containing percentage replaced cement by AWM with different percentages tabulated below the strength of specimen determined after 7, 28 and 60 days.

B. Sulphate Attack (H₂SO₄)

Most of the soils contain various sulphates like calcium, magnesium, potassium and sodium in different forms. Ground water includes less calcium sulphate when compare to rest of sulphates because of its low solubility. In Agricultural soil, Ammonium sulphate is more due to the usage of fertilizers in the form water. Therefore sulphate attack is a common occurrence in natural or industrial situations. For tests in the present experimental work is conducted on specimen size of 150 mm X 150 mm X 150 mm cubes for 7, 28 and 60 days curing in different concentration solutions. Then after, assess the weight loss due to the assailment.

V. EXPERIMENTAL RESULTS

In this present analysis, replacing the cement in different percentages with AWM, compaction factor of the particular percentage is required to know about workability. Therefore, the results show that workability exits below as shown in table no: (a).

COMPACTION FACTOR TEST

Table (a): Workability of AWM (% Replacement of cement)

S. no.	Percentage of AWM replaced in cement (by weight)	Values of compaction factor
1	0	0.858
2	5	0.839

3	10	0.818
4	15	0.809
5	20	0.778

The experimental investigation was carried by making AWM concrete by replacing cement with rice husk ash in the range of 0% by weight, 5% by weight, 10% by weight, 15% by weight, and 20% by weight of cement and checked for 7, 28 and 60 days for CS when it was solution of H₂SO₄ solution of 1%, 3%, 5% was to evaluate attack by sulfuric acid.

Table (b): SCR M₄₀ grade of CS results for normal water curing

Name of the Specimen	Percentage of AWM	strength of specimen (N/mm ²)		
		7 Days	28 Days	60 Days
S-0	0	27.39	39.37	49.59
S-05	5	27.23	39.09	49.36
S-10	10	27.12	39.01	49.26
S-15	15	26.27	38.45	48.89
S-20	20	23.41	37.79	47.76

The above table (b) represents the CS of M₄₀ AWM concrete in normal hardening water with suitable replacements of AWM 0% to 20% with an interval of 5%l. During this 7 day period, the CS will gradually increase until 10% of the cement has been replaced by AWM. Thereafter, the CS will decreases to 15% and 20% of AWM replacement with cement. The graphical representation of the table is shown in following fig.(1).

Table (c): SCR M₄₀ grade of CS results for 1% H₂SO₄ solution

Name of the Specimen	Percentage of AWM	strength of specimen (N/mm ²)		
		7 Days	28 Days	60 Days
S-11	0	27.01	38.73	48.95
S-12	5	26.55	38.21	48.25
S-13	10	26.31	37.91	48.11
S-14	15	24.86	36.57	47.17
S-15	20	21.66	35.52	45.77

The above table (c) shows the CS of AWM M₄₀ concrete, which was hardened in a 1% H₂SO₄ solution with various replacements from AWM 0% to 20% with an interval of 5% . During this 7 day period, the CS will gradually increase until the 10% of cement has been replaced by AWM. Then the CS is reduced to 15% and the AWM to 20% by cement. In this table the CS values of concrete are less comparable with normal hardening conditions and with 1% H₂SO₄. The graphic representation of the table is shown in the following fig.(2).



Table (d): SCR M₄₀ grade of CS results for 3 % H₂SO₄ solution.

Name of the Specimen	Percentage of AWM	strength of specimen (N/mm ²)		
		7 Days	28 Days	60 Days
S-31	0	25.21	38.4	48.83
S-32	5	24.82	37.77	48.08
S-33	10	24.67	37.45	47.89
S-34	15	23.63	35.82	47.26
S-35	20	20.82	34.44	45.57

The above table (d) shows the CS of M₄₀ AWM concrete, which was hardened in a 3% H₂SO₄ Solution with different replacements of AWM 0% to 20% in an interval of 5%. In this CS, 7 days gradually increase until the 10% of cement is replaced by AWM. Thereafter, the CS is reduced 15% and its replacement by 20% the AWM. In this table, the CS values of concrete values are less comparable with normal hardening conditions and with 3% H₂SO₄. The graphical representation of the table is shown in following fig (3)

Table (e): SCR M₄₀ grade of CS results for 5 % H₂SO₄ solution.

Name of the Specimen	Percentage of AWM	strength of specimen (N/mm ²)		
		7 Days	28 Days	60 Days
S-51	0	24.94	37.56	47.82
S-52	5	24.64	36.68	46.72
S-53	10	24.43	36.47	46.46
S-54	15	23.43	35.26	45.34
S-55	20	20.46	33.7	43.32

The above table (e) shows the CS of AWM M₄₀ concrete, which was hardened in a 5% H₂SO₄ solution with various replacements from AWM 0% to 20% with an interval of 5%. During this 7 day period, the CS will gradually increase until the 10% of cement has been replaced by AWM. Then the CS is reduced to 15% and the AWM to 20% by cement. In this table the CS values of concrete are less comparable with normal hardening conditions and with 5% H₂SO₄. The graphic representation of the table is shown in the following fig.(4).

VI. CONCLUSIONS

1. The outcome caused by sulphuric acid (H₂SO₄) on the concrete is reduced by the replacement of AWM in the cement. In curing stage the concrete cubes are immersed 0%, 1%, 3%, 5% of sulphuric acid solution at 7, 28 and 60 days.
2. The strength of cubes with 5% and 10% replacement of AWM is higher than cubes with 15% and 20% replacement of AWM. Increasing replacement of AWM in the concrete, workability of concrete decreases.
3. Then 5% and 10% replacement of AWM concrete partially reduce to the acid rains effects and it gives better performance, improved quality of construction and

reduction of onsite repair substantial reduction of environmental noise loading and around a site.

4. SCR makes the level of durability and reliability of the structure. The high resistance to external segregation and the mixtures self-compacting ability allow the elimination of micro-defects, air bubbles and Self-compacting concrete gives more structural durability.

Analysis of CS values by graphs

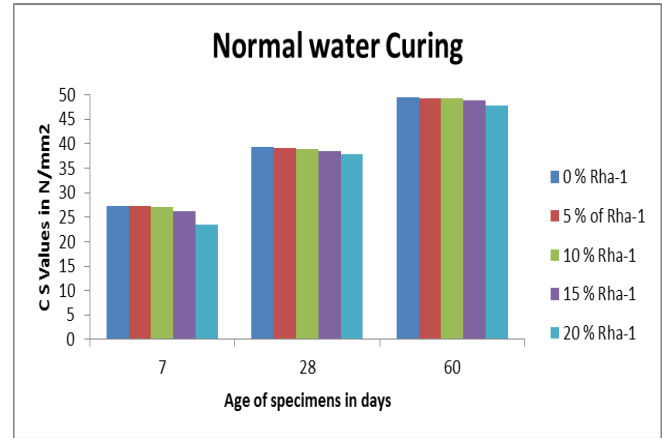


Fig 1: Represents CS results for normal water curing

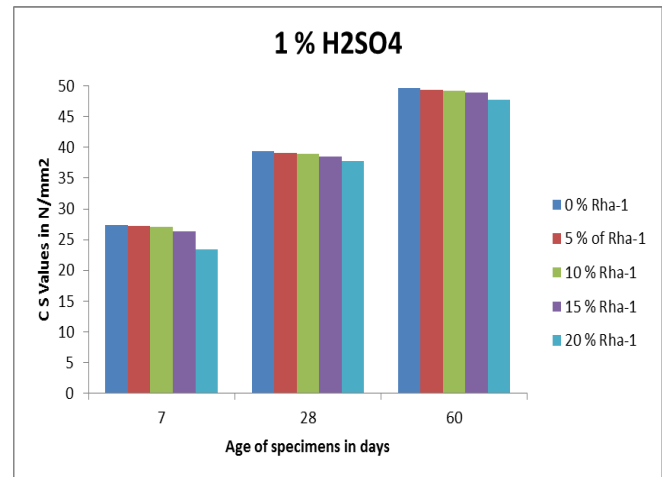


Fig 2: Represents CS results for 1% H₂SO₄ solution

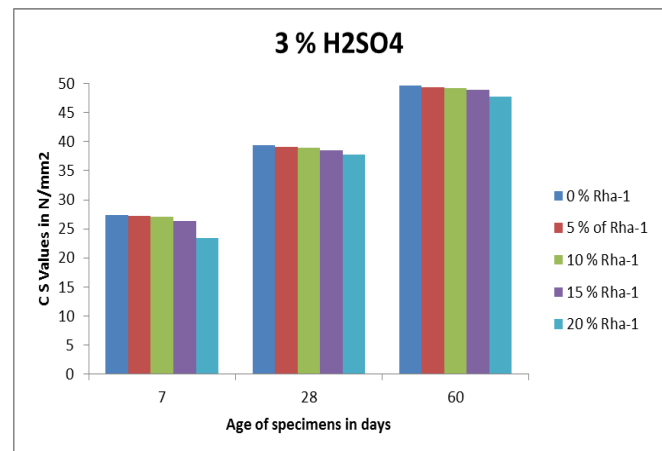


Fig 3: Represents CS results for for 3% H₂SO₄ solution

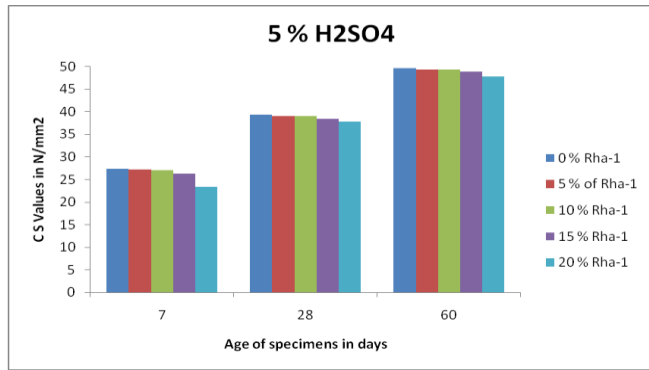


Fig 4:Represents CS results for for 5% H₂SO₄ solution

REFERENCES

1. ACI Committee Report NO. 226, BR8 "Use of Flyash" ACI Material Journal Sept/Oct 1987.
2. Andre Bisailon, Michael Rivest, and V.M.Malhotra "Performance of High - Volume Fly ash concrete in Large Experimental Monoliths" ACI Materials Journal, March/April, 1994
3. Alain Biloideau and V.Mohan Malhotra "High-Volume Fly ash system: Concrete Solution for Sustainable Development" ACI Material Journal, January-February, 2000.
4. Al-Tamimi, A. K. and Senobi, M. Assessment of self- compacting concrete immersed in acidic solutions, Journal of Materials in Civil Engineering, 2003. Vol.15, No.4, pp. 354-357.
5. Shetty, M.S. "Concrete Technology- Theory and Practice" fifth edition., S. Chand and Company Ltd. Ram Nagar, New Delhi. 110 055. India, 2004.
6. American Society of Testing and Materials manual ASTM, for standard procedures of cement, aggregates and concrete, 2006.
7. Neville, A.M. "Properties of concrete." fourth edition, Neville, A.M., Dorling Kindersley (India), Pvt Ltd, Patparganj, Delhi, India, 2006.
8. Sivakumar, V. and Murthi, P. Studies on acid resistance of ternary blended concrete. Asian Journal of Civil Engineering (Building and Housing), 2008. Vol. 9, No.5 pp. 473-486.
9. M. Safiuddin, J.S. West, K.A. Soudki, Hardened properties of self-consolidating high performance concrete including rice husk ash, Cem. Concr. Compos. 32 (9)(2010) 708-717.
10. G.R. de Sensale, Effect of rice husk ash on durability of cementitious materials, Cem. Concr. Compos. 32 (2010) 718-725.
11. Zerbino, R., Giaccio, G., Isaia, G.C., Concrete incorporating rice husk ash without processing. Constr. Build. Mater. 2011, 25 (1), 371-378.
12. Zain, M.F.M., Islam, M.N., Mahmud, F., Jamil, M.A., Production of rice husk ash for use in concrete as a supplementary cementitious material. Constr. Build. Mater. 25 (2), 2011, 798-805.
13. K. Kartini, Effects of Silica in Rice Husk Ash (RHA) in producing High Strength Concrete, ... of Engineering and ..., vol. 2, no. 12, 2012, pp. 1951-1956.
14. Zerbino, R., Giaccio, G., Marfil, S., Evaluation of alkali-silica reaction in concretes with natural rice husk ash using optical microscopy. Constr. Build. Mater. 2014, 71, 132-140.

AUTHORS PROFILE



R. Ramya Swetha, working as an assistant professor, civil engineering department in DNR college of Engineering and Technology (DNR CET) Bhimavaram, INDIA. Now pursuing PhD in JNTUK-Kakinada. Completed Master of Engineering (Structural Engineering) in the year 2013. Completed Bachelor of Engineering (Civil Engineering) in the year 2009. Publications:

"Studies of Nitric Acid Attack on Rice Husk Ash Concrete" International Journal of Civil Engineering & Technology, Scopus Indexed Journal Engineering and Technology, Volume 8, Issue 9, pp. 927-934, ISSN Print: 0976-6308 and ISSN Online: 0976-6316 September 2017. Life member in Indian Society for Technical Education (LM 122263). And also paper presentation is done in one international and two national conferences. Participated in FDP's also.



Dr. M. SWAROOPA RANI Associate Professor, Department of Civil Engineering UCEK, JNTUK, Kakinada, Presently working as a head of the department in UECK, JNTUK, Completed PhD in 011. Completed M.Tech (Structural Engineering) in the year 2001. Completed Under graduation (Civil Engineering) in the year 1992. published six international journals and participated as a chair person for session in conferences both national and international conferences conducted by various organizations and also conducted few workshops as a coordinator. And attended as a participant in few training programs and FDP's. Worked as an Additional Control of Examinations in UECK And also worked as a head of civil engineering department in UECK.



Dr. U. Ranga Raju, Principal of DNR College is an exceptional and the one who leads the college to a brighter future. He received Ph.D from IIT Madras, One of the most coveted colleges for technical education in India. He pledged to work his full potential in order to make this institute more productive and goal driven. He often encourages students to opt in for practicality in order to bring creativity in them and also he takes up projects. Member in FIE. He participated in various workshops, seminars, training programs, faculty development programs and seminars. And he delivered guest lectures for various institutions.